



Title	ACIDITY MEASUREMENT OF NICKEL SULFATE BY DTA AND TGA METHOD
Author(s)	TANABE, Kozo; MASUI, Satoshi; NISHIZAKI, Tadao
Citation	JOURNAL OF THE RESEARCH INSTITUTE FOR CATALYSIS HOKKAIDO UNIVERSITY, 19(1), 48-55
Issue Date	1971-04
Doc URL	<a href="http://hdl.handle.net/2115/24921">http://hdl.handle.net/2115/24921</a>
Type	bulletin (article)
File Information	19(1)_P48-55.pdf



[Instructions for use](#)

(Note)

## ACIDITY MEASUREMENT OF NICKEL SULFATE BY DTA AND TGA METHOD

By

Kozo TANABE,<sup>\*)</sup> Satoshi MASUI<sup>\*\*)</sup>  
and Tadao NISHIZAKI<sup>\*)</sup>

(Received December 22, 1970)

A number of methods have been presented for the measurement of surface acidity.<sup>1)</sup> The differential thermal analysis (DTA) was applied to differentiate between acid strengths by BREMER and STEINBERG.<sup>2)</sup> By observing the DTA diagram of SiO<sub>2</sub>-MgO catalysts coated with pyridine, they estimated the relative acid strengths of the catalysts heat-treated at various temperatures. Recently, SHIRASAKI *et. al.*<sup>3)</sup> have measured the acid amount together with the acid strength of SiO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> by analyzing the diagram of DTA and thermogravimetric analysis

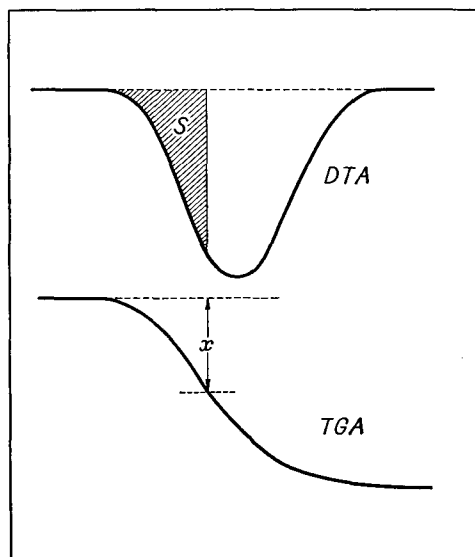


Fig. 1. A model of DTA and TGA diagram.

<sup>\*)</sup> Department of Chemistry, Faculty of Science, Hokkaido University, Sapporo.

<sup>\*\*)</sup> Research Institute for Catalysis, Hokkaido University.

*Acidity Measurement of Nickel Sulfate by DTA and TGA*

(TGA) of the catalyst on which organic bases had been adsorbed. Their method makes it possible to estimate continuously acid amounts at various acid strengths of even colored samples and the experiment is speedy and simple. In the present work, the acidic property of solid nickel sulfate which was fully studied previously<sup>4)</sup> was measured by employing the latter method and the observed values were compared with those measured by indicator method.

The principle of DTA and TGA method<sup>2)</sup> is as follows. A typical DTA and TGA diagram of a solid on which an organic base had been adsorbed is shown in Fig. 1. The amount  $x$  of the base retained on the solid is obtained from the TGA curve and the corresponding amount of heat absorbed from the area  $S$  defined by the DTA curve. From the curve of  $S$  against  $x$ ,  $dS/dx$  can be calculated. Plotting  $x$  against  $dS/dx$  gives the acid amounts at various acid strengths (or the heat required for the desorption of the base).

### Experimental

A heptahydrate of nickel sulfate was calcined at 350 or 600°C and the 100~200 mesh powders were immersed in pyridine or *n*-butylamine and then dried at 110°C for 15 hours. The DTA and TGA diagram was recorded at a heating rate of 5°C/min by using Shimadzu Differential Thermal Balance (MTG-11 type).

### Results and Discussions


The DTA and TGA diagrams of nickel sulfates calcined at 350 or 600°C on which pyridine or *n*-butylamine was adsorbed are shown in Figs. 2 and 3. It is seen in Fig. 2 that pyridine adsorbed on the sulfate calcined at 350°C begins to be desorbed at 300°C, the maximum endothermic peak being observed at 365°C, while no heat of absorption due to pyridine desorption is found for the sulfate calcined at 600°C, but a small exothermic peak which is probably due to the burning of pyridine appears at 365°C. Since the acid sites of the sulfate calcined at 350°C are stronger than those calcined at 600°C as shown in Table 1,<sup>4)</sup> pyridine

TABLE 1. Acidity of Nickel Sulfate<sup>\*)</sup>

Temp. of Calcination °C	Surface Area m <sup>2</sup> /g	Acid Amounts, mmol/g					
		pK <sub>a</sub> =6.8	pK <sub>a</sub> =4.8	pK <sub>a</sub> =4.0	pK <sub>a</sub> =3.3	pK <sub>a</sub> =1.5	pK <sub>a</sub> =-3.0
350	12.2	0.230	0.115	0.126	0.111	0.107	0.0561
600	6.6	0.0601	0.033	0.022	0	0	0

\*) Taken from ref. 4. Measured by *n*-butylamine titration method using various indicators of different pK<sub>a</sub>'s.

K. TANABE, S. MASUI and T. NISHIZAKI

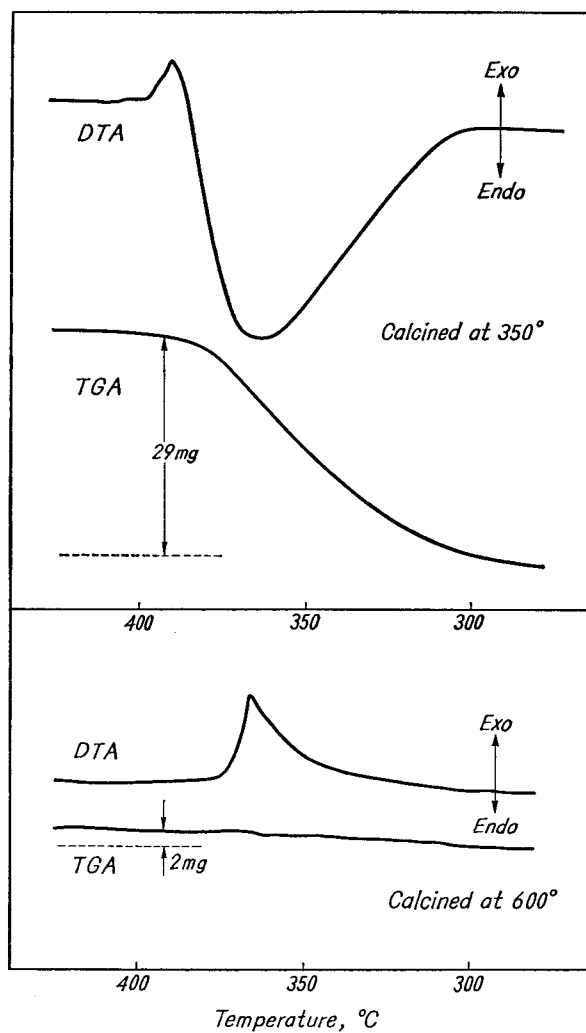

**Fig. 2.** DTA and TGA diagram of  $\text{NiSO}_4$  calcined at 350 or 600 $^{\circ}\text{C}$  on which pyridine was adsorbed. Sample weight: 300 mg.

## Acidity Measurement of Nickel Sulfate by DTA and TGA

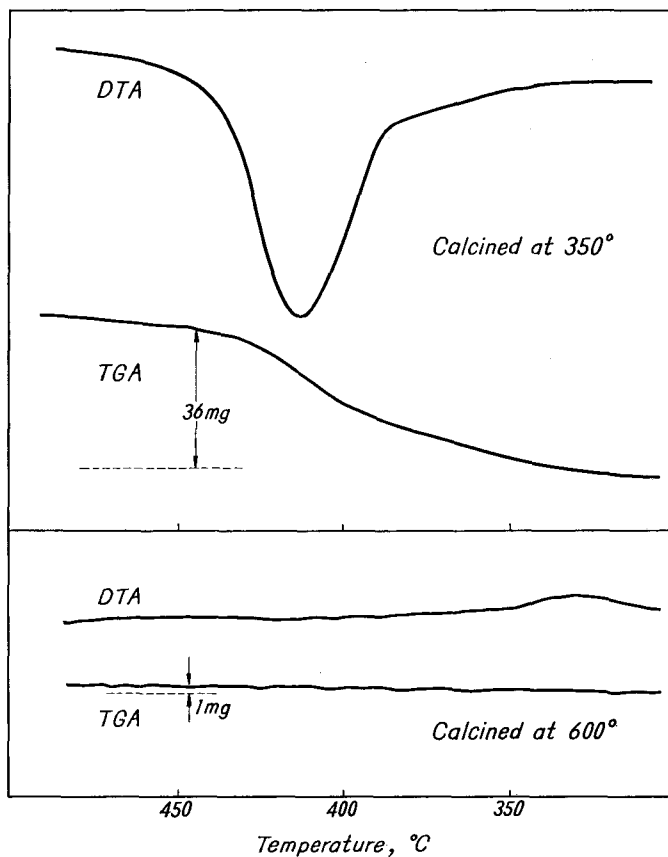


Fig. 3. DTA and TGA diagram of NiSO<sub>4</sub> calcined at 350 or 600°C on which *n*-butylamine was adsorbed. Sample weight: 300 mg.

adsorbed on stronger acid sites is desorbed at relatively high temperature, but that on weaker sites or physically adsorbed pyridine at low temperature, 9 mg of pyridine being desorbed up to 300°C. The pyridine adsorbed on stronger acid sites of the sulfate burns also at higher temperature.

In the case of *n*-butylamine-covered sample, the desorption peak appears at 415°C, a higher temperature than that in the pyridine-covered sample (see Figs. 2 and 3). This is due to that the pK<sub>a</sub> value (10.62) of *n*-butylamine is higher than that (5.17) of pyridine. The sulfate calcined at 600°C which has only weak acid sites does not much adsorb even a stronger base, *n*-butylamine, a small amount of the base being weakly adsorbed.

Since the endothermic peak in Fig. 2 consists of the peaks due to pyridine

K. TANABE, S. MASUI and T. NISHIZAKI

desorption and water dehydration, we obtained the peak of only pyridine desorption by reducing the peak of only water dehydration given in Fig. 4 from the peak in Fig. 2. The result is shown in Fig. 5, where the weight loss


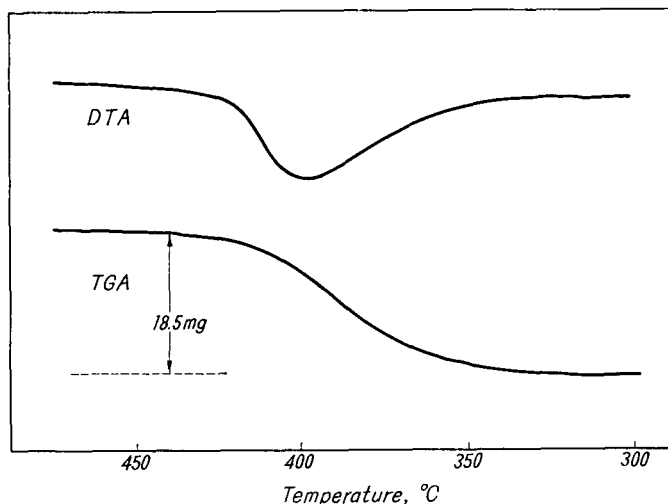


Fig. 4. DTA and TGA diagram of  $\text{NiSO}_4$  calcined at  $350^\circ\text{C}$ .  
Sample weight : 300 mg.

due to only pyridine desorption which was obtained similarly from TGA curves in Figs. 2 and 4 is also given. The curve of  $S$  against  $x$  (Fig. 6) is obtained from Fig. 5. The  $dS/dx$  calculated from the tangent of the curve was now plotted against  $x$  (mmol/g) in Fig. 7. The acid sites whose amount is less than 0.1 mmol/g have relatively high acid strength,  $dS/dx$  (the heat required for the desorption of pyridine). This result is in fairly good agreement with the result obtained by the amine titration method given in Table 1. Noting that the acid amount in a given  $H_0$  range is given by the difference between the acid amounts using the two indicators bracketing that  $H_0$  range, the acid strength of the sites less than 0.1 mmol/g corresponds to  $H_0 \leq +1.5$ . The acid strength of  $\text{SiO}_2\text{-Al}_2\text{O}_3$  is known to be much higher than that of  $\text{NiSO}_4$  calcined at  $350^\circ\text{C}$  according to the indicator method. The acid strength,  $dS/dx$  ( $\text{cm}^2\cdot\text{g}/\text{mmol}$ ), measured by DTA and TGA method using pyridine was 6.5,<sup>3)</sup> whose value is much higher than that (0.4) of  $\text{NiSO}_4$ . The total acid amount of  $\text{NiSO}_4$  calcined at  $350^\circ\text{C}$  is 0.23 mmol/g according to the amine titration method (see Table, 1), but the total amount of the sites corresponding to the desorption of pyridine is 0.87 mmol/g according to the present method (Fig. 7). This large value probably includes the sites on which pyridine was physically adsorbed. The amount

*Acidity Measurement of Nickel Sulfate by DTA and TGA*

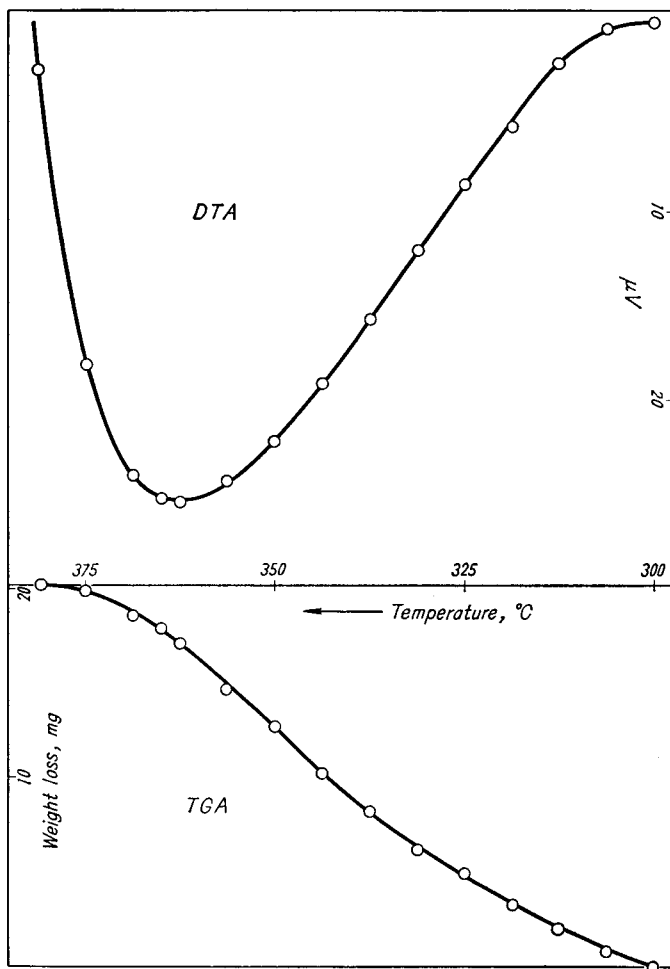

**Fig. 5.** Corrected DTA and TGA curves of  $\text{NiSO}_4$  calcined at  $350^\circ\text{C}$  and covered by pyridine.

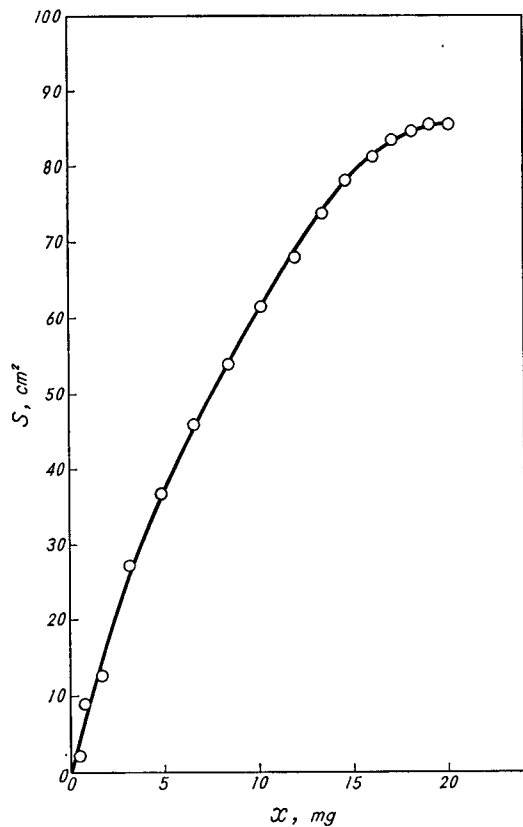


Fig. 6. Curve of  $S$ , area defined by DTA against  $x$ .

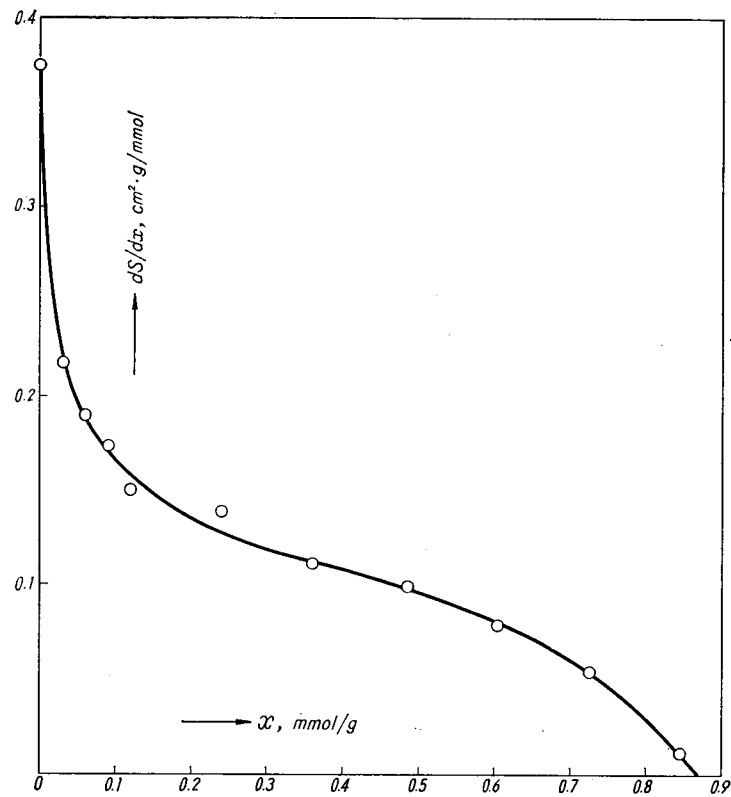


Fig. 7. Relative desorption heat of pyridine vs. amount of sites on  $\text{NiSO}_4$  calcined at  $350^\circ\text{C}$ .



*Acidity Measurement of Nickel Sulfate by DTA and TGA*

of sites which physically adsorb pyridine and the desorption heat on such sites may be obtained by using the sample poisoned with stronger base, as suggested by SHIRASAKI *et al.*<sup>3)</sup> In the case of *n*-butylamine-covered nickel sulfate, the curve of *S* against *x* was concave upwards in contrast with the case of pyridine-covered sulfate, though the case can be hardly interpreted.

**Acknowledgement:** We thank Drs. T. SHIRASAKI and K. MUKAIDA for their interest and discussions.

**References**

- 1) K. TANABE, *Solid Acids and Bases*, Kodansha Scientific Inc., Tokyo and Academic Press, New York and London, 1970, Chapter 2.
- 2) H. BREMER and K.-H. STEINBERG, 4th International Congress on Catalysis, Moscow, 1968, Preprint of paper No. 76.
- 3) T. SHIRASAKI, M. MIMURA and K. MUKAIDA, *Bunseki Kiki*, **5**, No. 7, 59, (1967).
- 4) K. TANABE and R. OHNISHI, *This Journal*, **10**, 229 (1962); K. TANABE and T. TAKESHITA, *Advances in Catalysis*, **17**, 315 (1967).