



|                  |   |
|------------------|---|
| Title            | FORMATION AND ACTIVITY OF CERTAIN CHROMITE CATALYSTS                              |
| Author(s)        | FAHIM, R. B.; ZAKI, M. I.; EL-ROUDI, A. M.; HASSAAN, A. M. A.                     |
| Citation         | JOURNAL OF THE RESEARCH INSTITUTE FOR CATALYSIS HOKKAIDO UNIVERSITY, 29(1), 25-36 |
| Issue Date       | 1981-11   |
| Doc URL          | <a href="http://hdl.handle.net/2115/25112">http://hdl.handle.net/2115/25112</a>   |
| Type             | bulletin (article)  |
| File Information | 29(1)_P25-36.pdf  |



[Instructions for use](#)

## FORMATION AND ACTIVITY OF CERTAIN CHROMITE CATALYSTS

By

R. B. FAHIM,\*<sup>1)</sup> M. I. ZAKI,\*<sup>1)</sup> A. M. EL-ROUDI\*<sup>1)</sup>  
and A. M. A. HASSAAN\*<sup>1)</sup>

(Received January 7, 1981; in revised form June 30, 1981)

### Abstract

Atomic absorption spectrophotometry in conjunction with a conventional solvent technique was used to study the kinetics of interaction between MO and Cr<sub>2</sub>O<sub>3</sub> in powder mixtures (where M stands for Zn<sup>2+</sup>, Mg<sup>2+</sup> or Ni<sup>2+</sup>). The kinetics of interaction can best be described by a rate equation developed by the geometrical model of Ginstling-Brounshtein and/or Jander. Formation of MCr<sub>2</sub>O<sub>4</sub> proceeds through an intermediate chromate. The step formation of the intermediate chromates is hindered in hydrogen atmosphere, while retarded when curing medium was nitrogen. Catalytic activity of the formed chromites was tested for the decomposition of H<sub>2</sub>O<sub>2</sub>. It was found to depend on the availability of an electron transfer cycle between two different valency states of M-Cr surface pairs. Data are presented for kinetic parameters of both solid state formation and catalyzed reactions.

### § 1. Introduction

Recently<sup>1)</sup> it was shown that the electron transfer between two different valency states of copper as well as manganese in hopcalite catalysts is possible within the spinel lattice without a change of structure. Such a concept would indicate an activity of spinel catalysts for redox reactions.<sup>2,3)</sup> Chromites seem to be a unique example for such a surface electron transfer cycle. The efficiency of this cycle is favoured by the easiness of establishing the known redox process Cr<sup>3+</sup>→Cr<sup>6+</sup>→Cr<sup>3+</sup>.<sup>4)</sup> Meanwhile, it is controlled by the extent to which the divalent cation (M) can exchange electrons with surface chromium ions.

The aim of the present article is to extend the applicability of the preceeding concept on chromites, thus correlating the pertaining formation structural changes of these catalysts and their activity towards the decomposition of H<sub>2</sub>O<sub>2</sub> as an acceptor reaction.<sup>1)</sup> Therefore the kinetics of chromites

\* ) Chemistry Department, Faculty of Science, University of El-Minia, El-Minia, A. R. E.

R. B. FAHIM *et al.*

reaction formation were studied with elaboration on the effect of reactivity of MO (where M stands for  $Mg^{2+}$ ,  $Zn^{2+}$  or  $Ni^{2+}$ ) on the mechanism of the reaction.

## § 2. Experimental

### (2-1) *Catalyst used*

The raw materials used in this investigation were NiO, ZnO, MgO and  $Cr_2O_3$  obtained by thermal decomposition, at  $700^\circ C$  for 10 hr in air, of AR-grade nickel hydroxide, zinc hydroxide, magnesium hydroxide and chromia gel respectively. Chromia gel was prepared according to the method described by Burwell *et al.*<sup>5</sup>  $MCr_2O_4$  was prepared by calcining for 10 hr a powder mixture of  $M(OH)_2$  and chromia gel (providing an equimolar MO :  $Cr_2O_3$  system) at  $400^\circ$ - $1200^\circ C$  in air and at  $1000^\circ C$  in purified nitrogen or hydrogen atmospheres, according to the procedure described by Hulbert *et al.*<sup>6</sup> Catalysts were characterized by differential thermal analysis (DTA), differential scanning calorimetry (DSC), infrared spectrophotometry (IRA) and x-ray diffractometry (XRD). Water extractable surface  $Cr^{6+}$  ions concentration was determined colorimetrically.<sup>7</sup>

### (2-2) *Kinetics of catalysts formation*

Kinetics of the reaction between fine powders of MO and  $Cr_2O_3$  to form  $MCr_2O_4$  were studied isothermally between  $400^\circ$  and  $1000^\circ C$  in air. Atomic absorption spectrophotometry in conjunction with conventional solvent techniques was adopted to monitor the fraction reaction completed (the fraction of reaction completed is a quantity relating the amount of reaction product formed to the amount of complete reaction (calculated)) as a function of time.<sup>8</sup> The details of the analytical procedure are described elsewhere.<sup>8</sup> Kinetic analysis was performed using models adopted earlier.<sup>9</sup>

### (2-3) *Catalytic measurements*

Kinetics of catalytic decomposition of  $H_2O_2$  in solution (35.5%) were followed gasometrically.<sup>7</sup> The analysis of experimental data has been carried out on the assumption<sup>7</sup> that the decomposition of  $H_2O_2$  is a first order process. As the maximal conversion observed after 30 min never exceeded 0.05, it may be assumed in the first approximation that the reaction runs at the constant concentration of  $H_2O_2$ . At such conditions the integration of the first order equation gives that  $v = v_0 + kt$ , where  $v$  represents the volume of oxygen evolved and  $v_0$ , the volume of oxygen evolved of the moment at which the time measurements started.

*Formation and Activity of Certain Chromite Catalysts*

§ 3. Results and Discussion

(3-1) *Kinetics of solid state reaction formation*

Reaction rate curves ( $x$ , fraction reaction completed vs.  $t$ , time) were constructed (Fig. 1). Adjoining the kinetic analysis of solid state reaction in powder mixtures,<sup>9</sup> reaction rate data from each isothermal reaction were

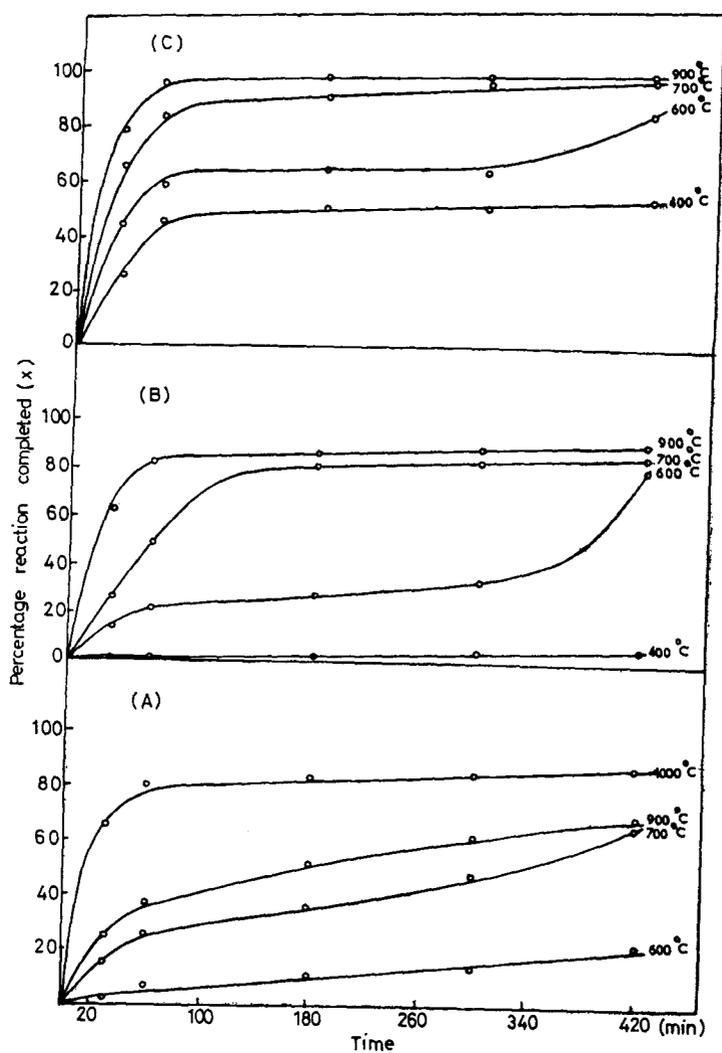


Fig. 1. Effect of temperature on the rate of the reaction in ZnO+Cr<sub>2</sub>O<sub>3</sub> (A), MgO+Cr<sub>2</sub>O<sub>3</sub> (B) or NiO+Cr<sub>2</sub>O<sub>3</sub> (C) system.

R. B. FAHIM *et al.*

analysed using equations corresponding to four reaction mechanism of basically different types and rate constants calculated. The calculated rate constants were then plotted vs. fraction reaction completed (Table 1 and Fig. 2). For a rate equation to represent a reaction, the rate constant should

TABLE 1. Rate constants ( $k$ ) of solid state reaction formation of  $M\text{Cr}_2\text{O}_4$  at different temperatures and the corresponding activation energies ( $\Delta E_a$ )

| $\text{MgCr}_2\text{O}_4$ | $k_{400^\circ\text{C}}$ | $k_{600^\circ\text{C}}$ | $k_{700^\circ\text{C}}$ | $k_{900^\circ\text{C}}$  | $\Delta E_a$<br>kcal/mole |
|---------------------------|-------------------------|-------------------------|-------------------------|--------------------------|---------------------------|
| Jander                    | $6.2 \times 10^{-7}$    | $6.4 \times 10^{-5}$    | $5.7 \times 10^{-4}$    | $1.7 \times 10^{-3}$     | 35.8                      |
| Ginstling-Brounshtein     | $6.1 \times 10^{-7}$    | $6.0 \times 10^{-5}$    | $4.3 \times 10^{-4}$    | $1.2 \times 10^{-3}$     | 30.6                      |
| $\text{ZnCr}_2\text{O}_4$ | $k_{600^\circ\text{C}}$ | $k_{700^\circ\text{C}}$ | $k_{900^\circ\text{C}}$ | $k_{1000^\circ\text{C}}$ | $\Delta E_a$<br>kcal/mole |
| Jander                    | $7.7 \times 10^{-6}$    | $11.8 \times 10^{-5}$   | $2.5 \times 10^{-4}$    | $13.5 \times 10^{-4}$    | 47.6                      |
| Ginstling-Brounshtein     | $7.5 \times 10^{-6}$    | $10.5 \times 10^{-5}$   | $2.2 \times 10^{-4}$    | $10.1 \times 10^{-4}$    | 44.3                      |
| $\text{NiCr}_2\text{O}_4$ | $k_{400^\circ\text{C}}$ | $k_{600^\circ\text{C}}$ | $k_{700^\circ\text{C}}$ | $k_{900^\circ\text{C}}$  | $\Delta E_a$<br>kcal/mole |
| Jander                    | $3.1 \times 10^{-4}$    | $7.8 \times 10^{-4}$    | $2.3 \times 10^{-3}$    | $3.9 \times 10^{-3}$     | 25.8                      |
| Ginstling-Brounshtein     | $2.8 \times 10^{-4}$    | $6.4 \times 10^{-4}$    | $1.6 \times 10^{-3}$    | $2.4 \times 10^{-3}$     | 25.3                      |

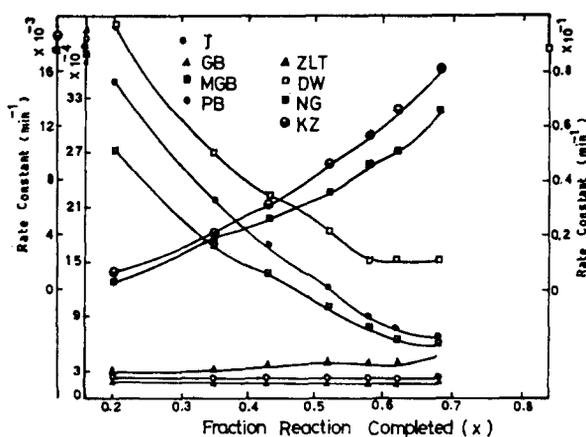


Fig. 2. Analysis of rate constants for 900°C isothermal reaction of ZnO with chromia calculated from: Jander ( $\circ$ ), Ginstling-Brounshtein ( $\blacktriangle$ ), modified Ginstling-Brounshtein ( $\blacksquare$ ), Phase Boundary controlled ( $\bullet$ ), Zhuravlev-Lesokhin-Tempel ( $\triangle$ ), Dünwald-Wagner ( $\square$ ), Kröger-Ziegler ( $\odot$ ) or Nuclei growth controlled ( $\blacksquare$ ) kinetic equation.

*Formation and Activity of Certain Chromite Catalysts*

be independent of the amount of reaction completed under isothermal conditions. All of the rate constants calculated by the reviewed models<sup>9)</sup> drift over several orders of magnitude for the three reaction systems. This is with the exception of:

$$\begin{aligned} \text{Jander,} & & k_J t &= [1 - (1-x)^{1/3}]^2 \text{ and/or} \\ \text{Ginstling-Brounshtein,} & & k_{BG} t &= 1 - 2/3x - (1-x)^{2/3} \end{aligned}$$

equations which assign a product growth controlled by diffusion of reactants through a continuous product layer. This finding copes with ideas of Greskovich<sup>10)</sup> who suggested that the reaction formation of nickel and magnesium chromites should follow the same kinetics.

It was indicated<sup>9)</sup> that the rate of the reaction between MgO and Cr<sub>2</sub>O<sub>3</sub> is controlled by the rate of the unidirectional lattice diffusion of chromium ions with vapour transport of oxygen. On the other hand, it was reported<sup>11)</sup> that the mechanism of nickel chromite formation from its component oxides follows a counter-current diffusion of Ni<sup>2+</sup> and Cr<sup>3+</sup> through the spinel layer. In case of ZnO:Cr<sub>2</sub>O<sub>3</sub> system, one can suggest that the mass transport is most likely unidirectional lattice diffusion of zinc ions with vapour transport of oxygen, since the vaporization rate of zinc oxide is greater than that of chromium oxide.<sup>12)</sup> Branson,<sup>13)</sup> working on ZnO:Al<sub>2</sub>O<sub>3</sub> solid reaction, concluded that diffusing Zn<sup>2+</sup> ions would recombine with atmospheric oxygen at the spinel/Al<sub>2</sub>O<sub>3</sub> interface to form the spinel. Consequently one can ascribe the low activation energy (Table 1) obtained for ZnO:Cr<sub>2</sub>O<sub>3</sub> reaction (47.6 kcal/mole) compared to that for ZnO:Al<sub>2</sub>O<sub>3</sub> reaction system (57.3 kcal/mole),<sup>13)</sup> to the presence of excess oxygen in Cr<sub>2</sub>O<sub>3</sub> lattice which would accelerate the diffusion of the zinc ions through the spinel layer.

### (3-2) Catalyst characterization


Table 2 presents structural information obtained by correlating the results of DTA, DSC, XRD and IRA. Magnesium chromite formation proceeds through an intermediate chromate which decomposes to the initial oxides that then would react giving eventually the spinel. This finding copes with that of Charcosset,<sup>14)</sup> thus contradicting the ideas of Hulbert.<sup>6)</sup> At the stage of decomposition of the intermediate chromate giving the initial oxides, magnesium oxide is not detected (Fig. 3). This phenomenon was observed by Haber<sup>15)</sup> who claimed that chromia shields the MgO grains through the vapour-transport mechanism. This formation mechanism is applicable in case of NiCr<sub>2</sub>O<sub>4</sub> (Fig. 3). On the other hand, the mechanism of the solid state reaction formation of ZnCr<sub>2</sub>O<sub>4</sub> is temperature dependent. Thus at relatively low temperature ( $\leq 400^\circ\text{C}$ ), the intermediate hydroxy zinc chromate<sup>16)</sup>

TABLE 2. Some structural information of calcined MO:Cr<sub>2</sub>O<sub>3</sub> mixtures

| Calcination Temperature<br>°C | Calcination Media | Crystalline phase present   |  |  | Extractable concentration | surface CrO <sub>4</sub> <sup>2-</sup><br>(mg/gm catalyst) |  |  | C/a*                                   |  |  |
|-------------------------------|-------------------|---|--|--|---------------------------|--|--|--|--|--|--|
|                               |                   | NiO:<br>Cr <sub>2</sub> O <sub>3</sub>  | ZnO:<br>Cr <sub>2</sub> O <sub>3</sub>   | MgO:<br>Cr <sub>2</sub> O <sub>3</sub>   |                           | NiO:<br>Cr <sub>2</sub> O <sub>3</sub>                     | ZnO:<br>Cr <sub>2</sub> O <sub>3</sub> | MgO:<br>Cr <sub>2</sub> O <sub>3</sub> | NiO:<br>Cr <sub>2</sub> O <sub>3</sub> | ZnO:<br>Cr <sub>2</sub> O <sub>3</sub> | MgO:<br>Cr <sub>2</sub> O <sub>3</sub> |
| 400                           | Air               | Cr <sub>2</sub> O <sub>3</sub> (J),<br>NiO(m),<br>NiO.CrO <sub>3</sub> (m).   | Cr <sub>2</sub> O <sub>3</sub> (J),<br>ZnO(J),<br>ZnO.CrO <sub>3</sub> (m),<br>ZnCr <sub>2</sub> O <sub>4</sub> (m). | Cr <sub>2</sub> O <sub>3</sub> (J),<br>MgO(m),<br>MgO.CrO <sub>3</sub> (m),<br>MgCr <sub>2</sub> O <sub>4</sub> (m). | 133.1                     | 180.6  | 250.2                                  | —                                      | 1.00                                   | 1.00                                   |  |
| 600                           | Air               | Cr <sub>2</sub> O <sub>3</sub> (m),<br>NiO.CrO <sub>3</sub> (m),<br>NiCr <sub>2</sub> O <sub>4</sub> (J).   | Cr <sub>2</sub> O <sub>3</sub> (m),<br>ZnO(m),<br>ZnO.CrO <sub>3</sub> (m),<br>ZnCr <sub>2</sub> O <sub>4</sub> (J). | Cr <sub>2</sub> O <sub>3</sub> (m),<br>MgO.CrO <sub>3</sub> (m),<br>MgCr <sub>2</sub> O <sub>4</sub> (J).            | 90.9                      | 60.6   | 120.3                                  | 1.00                                   | 1.00                                   | 1.00                                   |  |
| 800                           | Air               | Cr <sub>2</sub> O <sub>3</sub> (m),<br>NiO.CrO <sub>3</sub> (m),<br>NiCr <sub>2</sub> O <sub>4</sub> (J).   | ZnO.CrO <sub>3</sub> (m),<br>ZnCr <sub>2</sub> O <sub>4</sub> (J).   | Cr <sub>2</sub> O <sub>3</sub> (m),<br>MgCr <sub>2</sub> O <sub>4</sub> (J).   | 50.1                      | 15.8   | 20.6                                   | 1.00                                   | 1.00                                   | 1.00                                   |  |
| 1000                          | Air               | Cr <sub>2</sub> O <sub>3</sub> (m),<br>NiCr <sub>2</sub> O <sub>4</sub> (J),<br>NiCrO <sub>3</sub> (m),<br>Ni <sub>2</sub> O <sub>3</sub> .3CrO <sub>3</sub> (m).                 | ZnCr <sub>2</sub> O <sub>4</sub> (J),<br>ZnO.CrO <sub>3</sub> (m).   | Cr <sub>2</sub> O <sub>3</sub> (m),<br>MgCr <sub>2</sub> O <sub>4</sub> (J).   | 142.7                     | 5.5  | 10.8                                   | 1.00                                   | 1.00                                   | 1.00                                   |  |
|                               | Nitrogen          | Cr <sub>2</sub> O <sub>3</sub> (m),<br>NiCr <sub>2</sub> O <sub>4</sub> (J),<br>NiCr <sub>2</sub> O <sub>4</sub> (tr),<br>Ni <sub>2</sub> O <sub>3</sub> .3CrO <sub>3</sub> (tr). | ZnCr <sub>2</sub> O <sub>4</sub> (J),<br>ZnO.CrO <sub>3</sub> (m).   | Cr <sub>2</sub> O <sub>3</sub> (m),<br>MgCr <sub>2</sub> O <sub>4</sub> (J).   | 63.3                      | 15.9   | 8.9                                    | 1.04                                   | 1.03                                   | 1.04                                   |  |
| 1200                          | Hydrogen          | Cr <sub>2</sub> O <sub>3</sub> (J),<br>NiO(m),<br>NiCr <sub>2</sub> O <sub>4</sub> (m).   | Cr <sub>2</sub> O <sub>3</sub> (J),<br>ZnO(J),<br>ZnCr <sub>2</sub> O <sub>4</sub> (m),<br>ZnO.CrO <sub>3</sub> (m). | Cr <sub>2</sub> O <sub>3</sub> (m),<br>MgO(m),<br>MgCr <sub>2</sub> O <sub>4</sub> (J).                              | 10.5                      | 4.3  | 2.5                                    | 1.03                                   | 1.03                                   | 1.04                                   |  |
|                               | Air               | NiCr <sub>2</sub> O <sub>4</sub> (m),<br>NiCrO <sub>3</sub> (m),<br>Ni <sub>2</sub> O <sub>3</sub> .3CrO <sub>3</sub> (m).  | ZnCr <sub>2</sub> O <sub>4</sub> (J)   | MgCr <sub>2</sub> O <sub>4</sub> (J)   | 171.3                     | 2.00   | —                                      | 1.00                                   | 1.02                                   | 1.00                                   |  |

m=minor, J=major, tr=trace, \*calculated from X-ray diffraction patterns.

*Formation and Activity of Certain Chromite Catalysts*

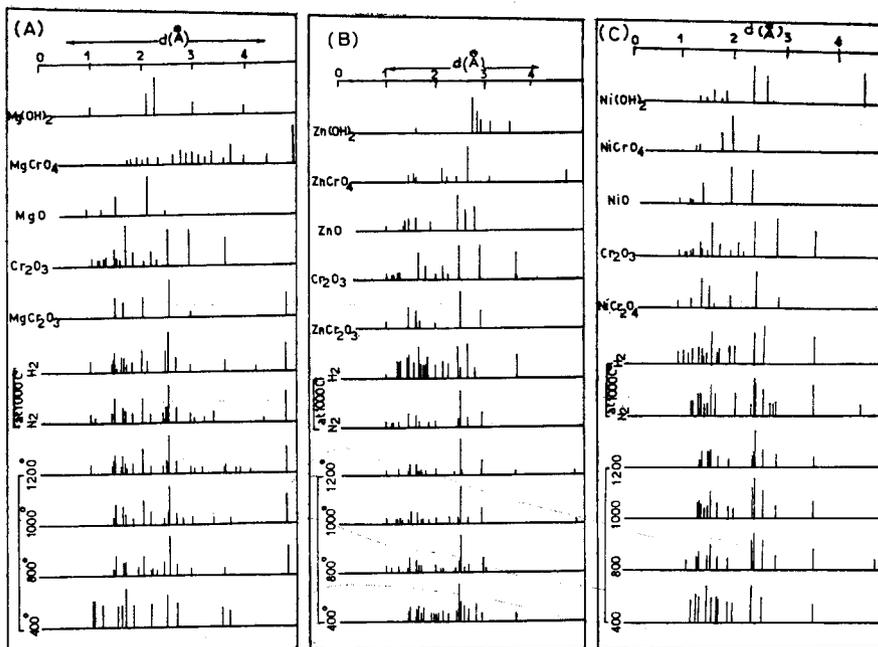

**Fig. 3.** X-ray diffraction patterns of the calcination products of the mixtures of chromia gel with  $\text{Mg}(\text{OH})_2$  (A) or  $\text{Zn}(\text{OH})_2$  (B) or  $\text{Ni}(\text{OH})_2$  (C) at different temperatures in air, nitrogen or hydrogen atmosphere.

decomposes giving the parent oxides that would then react giving the chromite. While at temperature  $\geq 800^\circ\text{C}$ , the formed hydroxy chromates give directly the chromite (Table 2).

The step formation of the intermediate chromates is hindered in hydrogen atmosphere, while retarded when curing medium is nitrogen (Table 2). This indicates that oxygen is necessary for this intermediate formation and hence for the spinel itself. However, curing in  $\text{N}_2$  atmosphere ( $1000^\circ\text{C}$ ) did not hinder formation of spinel crystallites as a minor component. Hence it is plausible to suggest that the limited supply of oxygen resulting from lateral hydroxyl group condensation of chromia gel partner,<sup>4</sup> taking place during heating up the solid mixture, contributes to oxidation.

Detection of extractable  $\text{Cr}^{6+}$  ions from reaction products indicates that rise of calcination temperature is accompanied by a drastic drop in its concentration as well as that of chromate intermediate (Table 2). This picture is not applicable for nickel chromite formation. Thus in latter case, there is a mild drop in concentration of  $\text{Cr}^{6+}$  starting from  $400^\circ\text{C}$  to  $600^\circ\text{C}$ , followed by a marked increase with temperature rise. The persistence of

stable  $\text{Cr}^{6+}$  ions above  $600^\circ\text{C}$  (which should be unstable at such temperature range<sup>4)</sup>) taking into consideration of possible existence of  $\text{Ni}^{3+}$  ions,<sup>10</sup> would suggest the formation of  $\text{Ni}_2\text{O}_3 \cdot 3\text{CrO}_3$  chromate intermediate. Such an intermediate when formed in minor amounts would decompose to form  $\text{NiCrO}_3$  spinel as referred to in IRA by strong absorption below  $500\text{ cm}^{-1}$  (Fig. 4). Such absorption was used to assign the formation of  $\text{SmCrO}_3$ ,  $\text{LaCrO}_3$  and  $\text{NdCrO}_3$  in similar systems.<sup>17</sup>

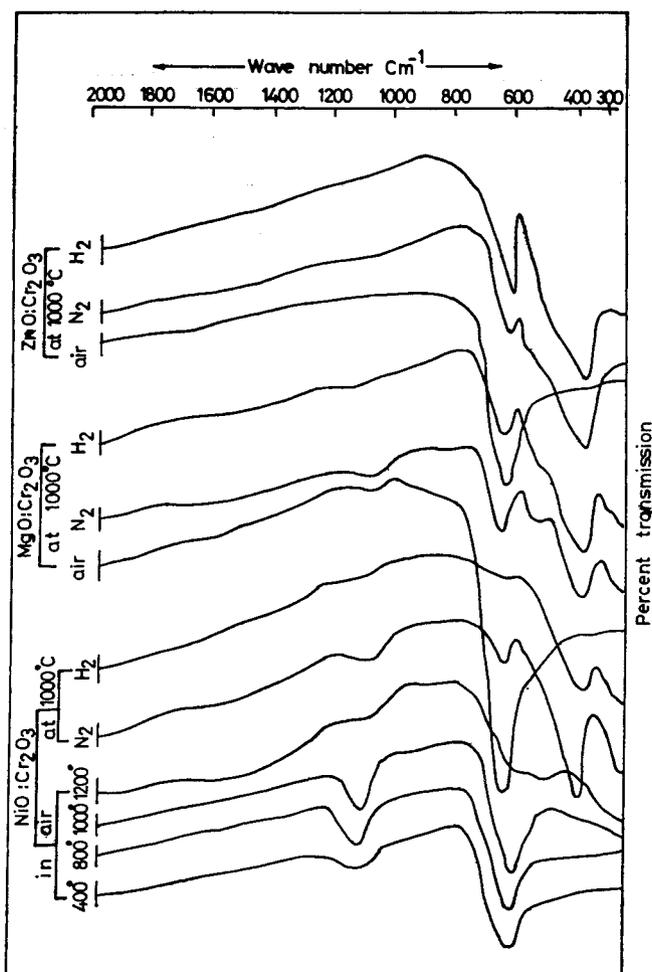


Fig. 4. IR-spectra for the calcination products of chromia gel mixtures with  $\text{Mg}(\text{OH})_2$ ,  $\text{Zn}(\text{OH})_2$  or  $\text{Ni}(\text{OH})_2$  at different calcination temperatures in air, nitrogen or hydrogen atmosphere.

*Formation and Activity of Certain Chromite Catalysts*


The observed  $\nu_4$ -ir absorption splitting in spectrum of  $\text{MgO}:\text{Cr}_2\text{O}_3$  sample cured at  $1000^\circ\text{C}$  in nitrogen or hydrogen atmospheres (Fig. 4) as well as the elongation of the unit cell (Table 2) of the corresponding chromite lattice along c-axes (viz.,  $c/a > 1$ ) would indicate a tetragonal distortion. Greskovich and Stubican<sup>19</sup> showed that a new spinel-type crystalline solution with cell formula  $(\text{Mg}_{8-x}\text{Cr}_x^{2+})^{\text{IV}}\text{Cr}_{16}^{3+\text{VI}}\text{O}_{32}$  was obtained on heating a mixture of  $\text{MgO}$  and  $\text{Cr}_2\text{O}_3$  in a reducing atmosphere. They observed such a distortion when a critical value of  $\approx 1$   $\text{Cr}^{2+}$  ( $3d^4$ ) ion per unit cell formula in the tetrahedral sites was reached. This interpretation can be safely adopted to the observed distortion in case of both  $\text{NiO}:\text{Cr}_2\text{O}_3$  (Fig. 4) and  $\text{ZnO}:\text{Cr}_2\text{O}_3$  mixtures.



Combining the foregoing results with conclusions cited for kinetic treatments on solid state reactions, the mechanism of magnesium chromite formation can be postulated as follows: the first step is the formation of a thin layer of spinel on  $\text{MgO}$  grains ( $\leq 600^\circ\text{C}$ ). This step takes place through two consecutive stages, a rapid surface reaction then a slower growth of product layer. At temperature  $> 600^\circ\text{C}$ , these two consecutive stages would overlap kinetically. The foregoing picture can also be applied in case of  $\text{NiO}:\text{Cr}_2\text{O}_3$  system (Fig. 1). The only difference which could be observed is that  $\text{NiO}$  is more reactive than  $\text{MgO}$ . Such a phenomenon can tentatively be ascribed to the difference in the mode of diffusion during chromite formation.

Due to similar reaction kinetics as well as diffusion models for both reactions of  $\text{ZnO}$  with  $\text{Cr}_2\text{O}_3$  or  $\text{Al}_2\text{O}_3$ , one can suggest a three steps reaction sequence for  $\text{ZnCr}_2\text{O}_4$  formation (Fig. 1): i) the formation of a solid solution of  $\text{ZnO}$  in  $\text{Cr}_2\text{O}_3$  (between  $600^\circ$  to  $700^\circ\text{C}$ ); ii) the formation of disordered spinel structure between  $700^\circ$  and  $900^\circ\text{C}$ ; and iii) the formation of an ordered spinel when mixtures are heated at  $900^\circ\text{C}$  and above.

### (3-3) *Catalytic activity*

Checking on the results of catalytic data (Table 3), it can be noticed that nickel chromite has exceptionally high activity as compared to that of both  $\text{MgCr}_2\text{O}_4$  and  $\text{ZnCr}_2\text{O}_4$ . This fact may be attributed to the presence of both  $\text{Cr}$  and  $\text{Ni}$  ions co-existence, each with different valency, at the surface (viz.,  $\text{Ni}^{2+}$ ,  $\text{Ni}^{3+}$ ,  $\text{Cr}^{3+}$ ,  $\text{Cr}^{6+}$ ). One would then expect a possible existence of various redox systems that can contribute in the surface electron transfer cycle. If we take the system  $\text{Ni}^{2+}/\text{Cr}^{6+}$  as being the most active redox centres, one can present the following mechanism<sup>13</sup>:



R. B. FAHIM *et al.*

Such a mechanism can also be applicable as well to  $\text{Cr}^{3+}/\text{Cr}^{6+}$  redox centres.<sup>10</sup> In case of  $\text{MgCr}_2\text{O}_4$  and  $\text{ZnCr}_2\text{O}_4$ , the  $\text{Cr}^{3+}/\text{Cr}^{6+}$  system would be the only available active sites for the decomposition of  $\text{H}_2\text{O}_2$ . Hence, one would expect the relatively low activity of these catalysts.

TABLE 3. Rate constants ( $k$ ), pre-exponential factors ( $k_0$ ) and activation energies ( $\Delta E_a$ ) of  $\text{H}_2\text{O}_2$  decomposition on  $\text{MCr}_2\text{O}_4$  catalysts

| Calcination temperature              | Calcination medium | $k_{25^\circ\text{C}}$ | $k_{30^\circ\text{C}}$ | $k_{35^\circ\text{C}}$ | $k_{40^\circ\text{C}}$ | $\Delta E_a$ kcal/mole | $k$      |
|--------------------------------------|--------------------|------------------------|------------------------|------------------------|------------------------|------------------------|----------|
| <b>NiCr<sub>2</sub>O<sub>4</sub></b> |                    |                        |                        |                        |                        |                        |          |
| 400°C                                | Air                | 16.250                 | 21.430                 | 35.290                 | 58.040                 | 16.30                  | 591.10   |
| 600                                  | Air                | 2.950                  | 5.860                  | 9.890                  | 13.280                 | 20.40                  | 246.60   |
| 800                                  | Air                | 11.540                 | 16.670                 | 30.770                 | 83.330                 | 17.50                  | 591.10   |
| 1000                                 | Air                | 38.880                 | 87.880                 | 133.590                | 173.330                | 18.30                  | 3102.70  |
| 1000                                 | Nitrogen           | 40.260                 | 95.260                 | 150.630                | 210.620                | 16.20                  | 3232.50  |
| 1000                                 | Hydrogen           | 1.210                  | 1.300                  | 2.210                  | 3.410                  | 31.30                  | 22.50    |
| 1200                                 | Air                | 45.830                 | 106.250                | 233.330                | 383.330                | 9.40                   | 3318.20  |
| <b>ZnCr<sub>2</sub>O<sub>4</sub></b> |                    |                        |                        |                        |                        |                        |          |
| 400°C                                | Air                | 11.590                 | 17.640                 | 26.660                 | 39.390                 | 15.20                  | 364.50   |
| 600                                  | Air                | 3.330                  | 6.250                  | 10.000                 | 15.620                 | 15.70                  | 159.10   |
| 800                                  | Air                | 1.510                  | 1.190                  | 2.080                  | 5.160                  | 27.60                  | 182.70   |
| 1000                                 | Air                | 0.568                  | 0.800                  | 0.454                  | 1.570                  | 12.10                  | 11.52    |
| 1000                                 | Nitrogen           | 2.110                  | 1.000                  | 1.900                  | 3.570                  | 22.60                  | 60.50    |
| 1000                                 | Hydrogen           | —                      | —                      | 0.080                  | 1.470                  | —                      | —        |
| 1200                                 | Air                | —                      | 0.250                  | 1.250                  | 1.428                  | 18.30                  | 20.60    |
| <b>MgCr<sub>2</sub>O<sub>4</sub></b> |                    |                        |                        |                        |                        |                        |          |
| 400°C                                | Air                | 450.000                | 633.330                | 1600.000               | 2900.00                | 28.10                  | 91563.00 |
| 600                                  | Air                | 16 000                 | 29.230                 | 43.330                 | 75.000                 | 18.40                  | 1100.70  |
| 800                                  | Air                | 3.330                  | 4.170                  | 7.570                  | 16.700                 | 14.70                  | 91.56    |
| 1000                                 | Air                | 0.779                  | 1.482                  | 4.176                  | 4.722                  | 25.80                  | 120.70   |
| 1000                                 | Nitrogen           | 3.125                  | 6.347                  | 11.100                 | 26.920                 | 31.50                  | 1100.70  |
| 1000                                 | Hydrogen           | 2.499                  | 4.443                  | 9.256                  | 18.050                 | 29.40                  | 694.60   |
| 1200                                 | Air                | —                      | 0.769                  | 1.071                  | 1.785                  | 14.70                  | 19.13    |

*Formation and Activity of Certain Chromite Catalysts*

Similar trend of variation between either  $k$ ,  $k_0$  or concentration of surface  $\text{CrO}_4^-$  and catalyst calcination temperature (Table 2 and 3) would indicate that i) each of  $k$  or  $k_0$  can be used as a base for activity classification of nickel chromite catalysts towards  $\text{H}_2\text{O}_2$  decomposition and ii) surface Cr(VI)-intermediates are the active sites for this reaction. Similar conclusion was given using chromia catalysts.<sup>10)</sup>

The non-linear dependence of  $k$  values on concentration of extractable surface  $\text{CrO}_4^-$  ions (Table 2 and 3), considering calcination products of NiO :  $\text{Cr}_2\text{O}_3$  system, can be ascribed to a compensation effect.<sup>19)</sup> Such an effect can be due to the coexistence of different surface, Cr(VI)-intermediates, viz.  $\text{NiO}\cdot\text{CrO}_3$  (major low temperature intermediate) and  $\text{Ni}_2\text{O}_3\cdot 3\text{CrO}_3$  (major high temperature intermediate).

From Table 3, it can be seen that the activity of a catalyst depends on the curing medium, thus being in the order  $\text{N}_2 > \text{Air} \gg \text{H}_2$ . Such an order may be interpreted in terms of the contribution of tetragonal distortion, being responsible for creation of additional surface energetic domains. However, the poor activity of tetragonally distorted  $\text{H}_2$ -cured catalyst is due to the disappearance of surface  $\text{Cr}^{6+}$  ions, being effectively the dominant co-sharing active acceptor centres.

### References

- 1) G.-M. Schwab and S. B. Kanungo, *Z. phys. Chem. NF*, **107**, 109 (1977).
- 2) D. E. R. Bennet and R. A. Ross, *J. Catalysis*, **18**, 122 (1970).
- 3) R. J. Rennard, Jr. and W. L. Kehl, *J. Catalysis*, **21**, 282 (1971).
- 4) R. B. Fahim, R. M. Gabr, M. I. Zaki and S. A. A. Mansour, *J. Collid Inter. Sci.*, **81**, 468 (1981).
- 5) R. L. Burwell, Jr., G. L. Haller, K. C. Taylor and J. F. Read, *Adv. in Catalysis*, **20**, Academic Press, New York, 1969, p. 2.
- 6) S. F. Hulbert, D. A. Brosman and R. H. Smoak, *Reactivity of Solids*, John Wiley & Sons, New York, 1969, p. 573.
- 7) R. B. Fahim, M. I. Zaki and R. M. Gabr, *J. Surface Technology*, in press, 1980.
- 8) A. M. A. Hassaan, M. Sc. thesis, Minia Univ., Egypt, 1980.
- 9) S. F. Hulbert and J. J. Klawitter, *J. Am. Ceram. Soc.*, **50**, 484 (1967).
- 10) C. Greskovich, *J. Am. Ceram. Soc.*, **53**, 498 (1970).
- 11) J. S. Armijo, D. L. Douglass and R. A. Huggins, *J. Electrochem. Soc.*, **120**, 825 (1973).
- 12) G. V. Samsonov, *The Oxide Handbook*, Plenum Press, London, 1973, p. 194.
- 13) D. L. Branson, *J. Am. Ceram. Soc.*, **48**, 591 (1964).
- 14) H. Charcosset, P. Turlier and Y. Trambouze, *J. de Chimie Physique*, **61**, 1249 (1964).
- 15) J. Burzyk and J. Haber, *Bull. Acad. Polon. Sci.*, **9**, 531 (1969).

R. B. FAHIM *et al.*

- 16) R. B. Fahim, R. M. Gabr and M. I. Zaki, *J. Surface Technology*, **11**, 215 (1980).
- 17) R. G. Darrie, W. P. Doyle and I. Kirkpatrick, *J. Inorg. Nucl. Chem.*, **29**, 979 (1967).
- 18) C. Greskovich and V. S. Stubican, *J. Phys. Chem. Solids*, **27**, 1379 (1966).
- 19) E. Cremer, *Adv. in Catalysis*, **7**, Academic Press, New York, 1955, p. 75.