



Title	Transfer hydrogenation of cellulose to sugar alcohols over supported ruthenium catalysts
Author(s)	Kobayashi, Hirokazu; Matsuhashi, Hisateru; Komanoya, Tasuku; Hara, Kenji; Fukuoka, Atsushi
Citation	Chemical Communications, 47(8), 2366-2368 https://doi.org/10.1039/c0cc04311g
Issue Date	2011-02-28
Doc URL	http://hdl.handle.net/2115/47501
Rights	Chem. Commun., 2011, 47, 2366-2368 - Reproduced by permission of The Royal Society of Chemistry (RSC)
Type	article (author version)
File Information	CC47-8_2366-2368.pdf



[Instructions for use](#)

Transfer hydrogenation of cellulose to sugar alcohols over supported ruthenium catalysts

Hirokazu Kobayashi,^a Hisateru Matsuhashi,^a Tasuku Komano,^{ab} Kenji Hara^a and Atsushi Fukuoka^{*a}

Received (in XXX, XXX) Xth XXXXXXXXX 200X, Accepted Xth XXXXXXXXX 200X

5 First published on the web Xth XXXXXXXXX 200X


DOI: 10.1039/b000000x

Ru/C catalysts are active for the conversion of cellulose using 2-propanol or H₂ of 0.8 MPa as sources of hydrogen, whereas Ru/Al₂O₃ catalyst is inactive in both reactions, indicating that the
10 Ru/C catalysts are remarkably effective for the cellulose conversion.

The conversion of renewable biomass to useful chemicals is one of the most important goals in green and sustainable chemistry.¹ In order to avoid competition with food
15 production, as seen in the last few years, non-food biomass should be used as a biomass resource for the manufacture of chemicals. Cellulose is the most abundant non-food biomass resource produced via photosynthesis,² and therefore the conversion of cellulose has attracted significant attention as a
20 key issue in the utilisation of biomass.³ Cellulose is a water-insoluble polymer composed of glucose units linked by β-1,4-glycosidic bonds,^{2,4} and the hydrolysis-hydrogenation (abbreviated as hydrogenation) of cellulose gives sugar alcohols, which are versatile precursors to plastics, fuels and
25 pharmaceuticals. Therefore, sugar alcohols are among the major targets in the transformation of cellulosic biomasses.

Since we reported the conversion of cellulose to sorbitol and mannitol by supported Pt and Ru catalysts under H₂ pressure,⁵ other groups have also reported the degradation of
30 cellulose to sorbitol⁶ or ethylene glycol⁷ using various supported metal catalysts under high pressures of H₂ (≥ 5 MPa). These solid catalysts have the advantage of easy separation and produce the desired chemicals in good yields under aqueous conditions. However, one of their
35 disadvantages is the need for pressurised H₂. As an alternative to H₂ pressure, we investigated the transfer hydrogenation of cellulose using an alcohol and found that sugar alcohols are obtained as major products using the carbon-supported Ru catalysts (Scheme 1). To the best of our knowledge, the
40 transfer hydrogenation of cellulose using heterogeneous catalysts has not previously been reported.

Table 1 summarises the results of the transfer hydrogenation of cellulose by various supported Ru catalysts using 2-propanol as a source of hydrogen without bases.‡
45 Among the catalysts, the Ru/carbons [Ru/AC(N), Ru/C-Q10 and Ru/CMK-3] gave the highest yields of sugar alcohols (entries 3, 8, 9). For example, the yields in the reaction using Ru/C-Q10 were 37% sorbitol and 9.0% mannitol for a total of 46% (0.87 mmol). The turnover number (TON) based on bulk
50 Ru (0.01 mmol) for the sum of the sugar alcohols was 87. The conversion of cellulose was 80%, which was determined from the weight difference of the solid after the reaction.

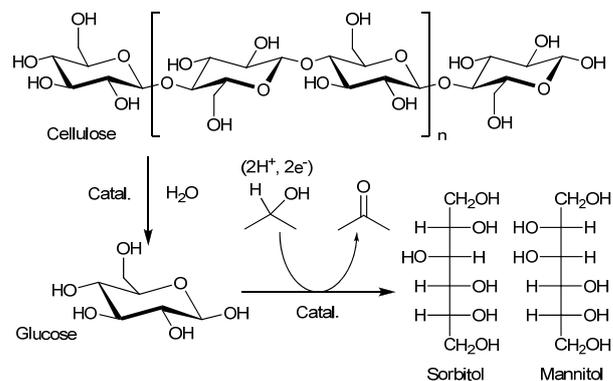

Scheme 1 Transfer hydrogenation of cellulose to sugar alcohols.

Accordingly, the selectivity based on the cellulose conversion for the sum of the sugar alcohols was 57%. 1,4-Sorbitan (1.4%), C₂-C₄ polyols (total 5.3%: ethylene glycol 0.8%, propylene glycol 1.8%, glycerine 1.2% and erythritol 1.5%), and glucose (0.7%) were produced as minor products. As the
60 source of hydrogen, 15% of 2-propanol (20 mmol) was converted to acetone, which was 22 times as much as the yield of the sugar alcohols (0.87 mmol). Thus, only 4.5% of the hydrogen species was utilised for the production of the sugar alcohols and the other part evolved as H₂ gas during the reaction (see below). Ru/AC(W) (sugar alcohol yield 23%), Ru/BP2000 (14%) and Ru/XC72 (3.0%) were less active than
65 Ru/AC(N), Ru/C-Q10 and Ru/CMK-3 (entries 7, 10, 11). Ru/TiO₂, Ru/ZrO₂ and Ru/Al₂O₃ were inactive for the reaction (entries 12-14), which indicates that the catalytic activity of
70 Ru greatly depends on the supports. It is notable that Ru/Al₂O₃ is an active catalyst for the hydrogenation of cellulose to sugar alcohols using H₂ gas of 5 MPa,⁵ while it is completely inactive for the transfer hydrogenation (entry 14). Thus, we suggest that the active Ru species in this transfer
75 hydrogenation is different from that in the typical hydrogenation reaction with H₂. In the reactions using the inactive catalysts (entries 12-14), glucose and 5-hydroxymethylfurfural (5-HMF) formed instead of the hydrogenated products with almost no conversion of 2-propanol. This is the same tendency as in the reactions
80 without Ru catalysts (entries 1, 2), indicating that the hydrolysis of cellulose to glucose proceeds with or without catalysts^{6a, 8-10} and that an active Ru species hydrogenates glucose to the sugar alcohols using a hydrogen species derived
85 from 2-propanol. Carbon-supported Rh, Ir, Pd, Pt and Au catalysts were also tested for the reaction (entries 16-20), but the sugar alcohols were not obtained. Therefore, we chose

Table 1 Transfer hydrogenation of cellulose by supported metal catalysts.^a

Entry	Catalyst	Yield based on carbon /%								Cellulose conv. ^e /%	Yield of acetone /%
		Sorbitol	Mannitol	Sum of sorbitol and mannitol	Sorbitan	C ₂ -C ₄ polyols ^b	Glucose	5-HMF ^c	Others ^d		
1	None	0	0	0	0	0	3.8	19.0	42.2	65.0	<0.1
2	AC(N)	0	0	0	0	0	1.5	12.8	50.6	64.9	<0.1
3	Ru/AC(N)	33.5	9.0	42.5	0.6	6.1	0.9	0	24.3 ^h	74.4	15 (24) ^j
4 ^f	Ru/AC(N)	36.3	10.6	46.9	0.9	6.7	1.1	0	29.6	85.2	15 (22) ^j
5 ^f	Ru/AC(N)	2.0	0.4	2.4	0	0	4.4	11.6	88.6	107	1.6 (46) ^j
6 ^g	Ru/AC(N)	29.5	8.3	37.8	1.4	6.9	0.7	0.3	35.8	82.9	–
7	Ru/AC(W)	18.5	4.2	22.7	0.4	4.8	1.2	0	32.7	61.8	15 (45) ^j
8	Ru/C-Q10	36.8	9.0	45.8	1.4	5.3	0.7	0	27.0	80.2	15 (22) ^j
9	Ru/CMK-3	35.7	9.3	45.0	1.4	7.1	0.8	0	26.9	81.2	15 (23) ^j
10	Ru/BP2000	11.6	2.4	14.0	0.3	3.0	1.3	2.1	59.1	79.8	14 (68) ^j
11	Ru/XC72	2.7	0.3	3.0	0.1	0	1.0	1.6	72.0	77.7	8.4 (190) ^j
12	Ru/TiO ₂	0.1	0	0.1	0	0	3.5	12.8	60.0	76.4	0.6
13	Ru/ZrO ₂	0	0	0	0	0	2.5	13.0	62.9	78.4	0.4
14	Ru/Al ₂ O ₃	0	0	0	0	0	2.5	14.0	55.6 ⁱ	72.1	0.7
15 ^g	Ru/Al ₂ O ₃	2.6	0.8	3.4	0	6.5	0.9	0.7	65.2	76.7	–
16	Rh/AC(N)	0	0	0	0	0	2.7	10.1	61.8	74.6	0.5
17	Ir/AC(N)	0	0	0	0	0	1.3	4.6	67.9	73.7	2.3
18	Pd/CMK-1	0	0	0	0	0	0.4	5.7	74.5	80.6	<0.1
19	Pt/CMK-3	0	0	0	0	0	1.1	0	80.9	82.0	4.9
20	Au/AC(N)	0	0	0	0	0	1.6	14.6	42.6	58.8	1.4


^a Cellulose 324 mg (1.90 mmol), catalyst 50 mg (metal 2 wt%), water 30 mL, 2-propanol 10 mL (130 mmol), 463 K, 18 h. ^b Sum of erythritol, glycerine, propylene glycol and ethylene glycol. ^c 5-Hydroxymethyl furfural. ^d Others include soluble sugar compounds and unidentified ones. ^e Based on the carbon balance calculated from the weight difference after the reaction. ^f The reuse experiment using the residue of the experiment of the previous entry number and fresh cellulose of 324 mg. The conversion and yields are based on the fresh cellulose. ^g H₂ of 0.8 MPa was used instead of 2-propanol. Water 40 mL. ^h Cello-oligosaccharides 1.5%, cellobitol 1.0%, hexanetetrol 4.0% and unidentified 17.8% (Fig. S1). ⁱ Cello-oligosaccharides 1.9%, fructose 2.3%, levoglucosan 0.6%, furfural 1.3% and unidentified 49.5%. ^j Ratio of acetone yield against the sugar alcohols yield (mol/mol).

Ru/AC(N) as the typical catalyst hereafter because of its significant catalytic activity, good reproducibility and easy availability of the support.¹¹

Reuse experiments of Ru/AC(N) were performed to verify its durability. The catalyst was separated by centrifugation from the reaction mixture and reused after drying at 383 K. The yields of sorbitol and mannitol were 36% and 11%, respectively, in the second use (entry 4), which were almost the same as those in the first run (sorbitol 34%, mannitol 9.0%). However, the catalyst was deactivated in the third run (entry 5). EDX and XRD analyses of the spent catalyst showed no change of the catalyst after the third use. Thus, the deactivation might be due to the strong adsorption of by-products on the active sites. The catalyst was usable twice and total TON of Ru for the production of the sugar alcohols was 170 in the reactions. In addition, the filtrate separated by polytetrafluoroethylene (PTFE) membrane (0.1 μm pore) after the first reaction was completely inactive for the transfer hydrogenation. Accordingly, we conclude that Ru/AC(N) is a heterogeneous catalyst for the transfer hydrogenation.

As described above, H₂ was produced during the transfer hydrogenation reactions, whose partial pressure reached 0.8 MPa in the closed reactor from the chemical equilibrium (Eq. 1) at 463 K in the initial period of 0.5 h. It is noteworthy that the reduction of the dead volume in the reactor decreases the evolution of H₂ and improves the utilisation efficiency of 2-propanol as the equilibrium shifts to the left-hand side. Considering this phenomenon, we expected that the hydrogenation of cellulose would proceed at a H₂ pressure as low as 0.8 MPa without 2-propanol by using Ru/AC(N) catalyst. In fact, the reaction gave good yields of the sugar

alcohols (sorbitol 30%, mannitol 8.3%, entry 6), whereas Ru/Al₂O₃, which is a typical active catalyst for the hydrogenation of cellulose with H₂ of 5 MPa, was significantly less active (sorbitol 2.6%, mannitol 0.8%, entry 15) under the same reaction conditions. This result indicates that the active species of Ru/AC(N) is different from that of Ru/Al₂O₃.



To identify the active species for the transfer hydrogenation, XRD analysis was performed for Ru/AC(N) and Ru/Al₂O₃. Fig. 1 represents the XRD patterns of AC(N), Ru/AC(N) and the differential pattern of Ru/AC(N) minus AC(N). AC(N) gave a broad scattering pattern of amorphous carbon (2θ = 23°, 43° and 80°) and sharp diffraction peaks of quartz, which is an impurity of AC(N) [Fig. 1(a)]. After the impregnation of Ru, no diffraction peaks of Ru metal appeared in the XRD [Fig. 1(b, c)], even when the Ru loading was increased to 10 wt% (Fig. S2). These data show that the Ru species on AC(N) was highly dispersed and/or not fully reduced to zero-valent particles during the catalyst preparation. We performed H₂-temperature programmed reduction (TPR) of Ru/AC(N) (Fig. S3), and 4 peaks appeared at 410, 530, 670 and 860 K with the H/Ru atomic ratios of 13, 3.5, 2.9 and 11, respectively. The second or the third peaks might be assigned to the reduction of the Ru species by correlating the peak areas with the Ru concentration, suggesting tri- or tetra-valent Ru. Other peaks are due to the reduction of the surface functional groups on the carbon support such as quinones and aromatic rings. In the XPS analysis, the electron binding energy of Ru 3p_{3/2} for

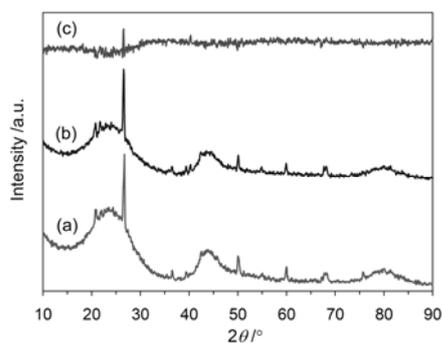


Fig. 1 XRD patterns of (a) AC(N), (b) Ru/AC(N) and (c) the differential pattern of (b)–(a).

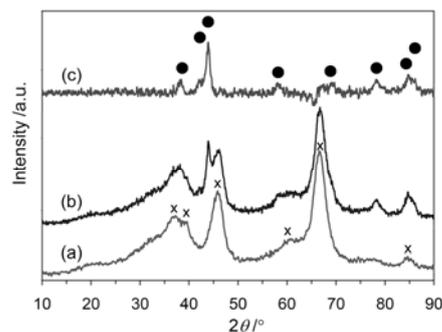


Fig. 2 XRD patterns of (a) Al₂O₃, (b) Ru/Al₂O₃ and (c) the differential pattern of (b)–(a). Circles: Ru metal. x: γ -Al₂O₃.

Ru/AC(N) catalyst was 463.1 eV, which is in the range of tri- to tetra-valent states and higher than that for Ru metal (461.9 eV, Fig. S4). Fig. S5 shows the curve fitting of the XPS data for Ru/AC(N), and the spectrum was fitted by those of RuO₂ (99.7%) and Ru metal (0.3%), giving a similar electron state to that of RuO₂. It is thus indicated that the Ru species on AC(N) is not metal but tetra- or tri-valent. Fig. 2 shows the XRD patterns of Al₂O₃, Ru/Al₂O₃ and the differential pattern of Ru/Al₂O₃ minus Al₂O₃. The pattern of Al₂O₃ indicated the presence of γ -Al₂O₃ phase [Fig. 2(a)]. After the loading of Ru, the diffraction pattern of Ru metal was observed with the peaks of γ -Al₂O₃ [Fig. 2(b)]. The differential pattern [Fig. 2(c)] clearly showed the peaks of Ru metal, marked with black circles. The mean diameter of Ru particles was 9 nm, calculated by the Scherrer's equation, which was reported as the best particle size for the selective hydrogenation of cellobiose using H₂ of 5 MPa.¹² Therefore, we conclude that the highly dispersed cationic Ru species is active for the transfer hydrogenation reaction, whereas Ru metal nanoparticles are inactive for this reaction.

In summary, Ru/AC(N), Ru/C-Q10 and Ru/CMK-3 catalysts were active for the transfer hydrogenation of cellulose to sugar alcohols. Ru/AC(N) also catalysed the hydrogenation of cellulose at a H₂ pressure as low as 0.8 MPa. The catalytic activity of Ru/AC(N) is significantly different from those of the typical catalysts for the cellulose hydrogenation such as Ru/Al₂O₃, which require high pressures of H₂. It is proposed that the active species for the transfer hydrogenation is a cationic Ru species.

We thank Prof. W. Ueda for the H₂-TPR study. This work was financially supported by JSPS KAKENHI (20226016).

Notes and references

^a Catalysis Research Centre, Hokkaido University, Kita 21 Nishi 10, Kita-ku, Sapporo 001-0021, Japan. Fax: (+81) 11 706 9139; E-mail: fukuoka@cat.hokudai.ac.jp

^b Division of Chemical Sciences and Engineering, Graduate School of Chemical Sciences and Engineering, Hokkaido University, Kita 13 Nishi 8, Kita-ku, Sapporo 060-8628, Japan.

[†] Electronic Supplementary Information (ESI) available: [analysis methods of products, characterisation procedures of the catalysts, XRD, H₂-TPR, XPS, optimisation of the reaction]. See DOI: 10.1039/b000000x/

[‡] The catalyst supports used in this study are as follows. CMK-1 and CMK-3 were synthesised according to procedures in the literature.¹³ Carbon (C-Q10, BET surface area 840 m² g⁻¹) was prepared using an amorphous silica (Q-10, Fuji Silysia) in the same manner as for CMK-3. Activated carbons were purchased from Wako (activated charcoal), denoted as AC(W) and Aldrich (SX Ultra, Norit), denoted as AC(N). Carbon blacks (VULCAN XC72 and BP2000) were supplied from Cabot.

Other supports are TiO₂ (P-25, Degussa), ZrO₂ (JRC-ZRO-2, Catalysis Society of Japan) and Al₂O₃ (JRC-ALO-2, Catalysis Society of Japan). Supported Ru catalysts (Ru metal loading 2 wt%) were prepared by a conventional impregnation method as follows: RuCl₃ aq. (0.202 mmol in 5 mL of water) was dropped into a mixture of a catalyst support (1.00 g) and water (20 mL), and the mixture was stirred for 16 h. After drying *in vacuo*, the solid was reduced in a fixed-bed flow reactor with H₂ (30 mL min⁻¹) at 673 K for 2 h. In the cases using oxide supports, the precursors were calcined with O₂ (30 mL min⁻¹) at 673 K before the H₂ reduction.

Transfer hydrogenation of cellulose was carried out in a stainless steel (SUS316) high-pressure reactor (OM Lab-Tech MMJ-100, 100 mL). Cellulose (Merck, Avicel) was milled using ZrO₂ balls at 60 rpm for 4 days. The milled cellulose (324 mg, 1.90 mmol glucose units, containing 4.8 wt% physisorbed water), supported Ru catalyst (50 mg), water (30 mL) and 2-propanol (10 mL) were charged in the reactor (glucose unit/Ru = 190), and then purged with 1 atm of N₂ or He. The mixture was heated to 463 K and maintained at this temperature for 18 h with stirring at 600 rpm. The analysis methods of products and the characterisation procedures of the catalysts are described in the ESI.

1 J. N. Chheda, G. W. Huber and J. A. Dumesic, *Angew. Chem. Int. Ed.*, 2007, **46**, 7164.

2 D. Klemm, B. Heublein, H.-P. Fink and A. Bohn, *Angew. Chem. Int. Ed.*, 2005, **44**, 3358.

3 P. L. Dhepe and A. Fukuoka, *ChemSusChem*, 2008, **1**, 969-975; R. Rinaldi and F. Schüth, *ChemSusChem*, 2009, **2**, 1096.

4 S. Deguchi, K. Tsujii and K. Horikoshi, *Chem. Commun.*, 2006, 3293.

5 A. Fukuoka and P. L. Dhepe, *Angew. Chem. Int. Ed.*, 2006, **45**, 5161.

6 a) C. Luo, S. Wang and H. Liu, *Angew. Chem. Int. Ed.*, 2007, **46**, 7636; b) W. Deng, X. Tan, W. Fang, Q. Zhang and Y. Wang, *Catal. Lett.*, 2009, **133**, 167; c) S. Van de Vyver, J. Geboers, M. Dusselier, H. Schepers, T. Vosch, L. Zhang, G. Van Tendeloo, P. A. Jacobs and B. F. Sels, *ChemSusChem*, 2010, **3**, 698; d) L. Ding, A. Wang, M. Zheng and T. Zhang, *ChemSusChem*, 2010, **3**, 818.

7 N. Ji, T. Zhang, M. Zheng, A. Wang, H. Wang, X. Wang and J. G. Chen, *Angew. Chem. Int. Ed.*, 2008, **47**, 8510; M. Zheng, A. Wang, N. Ji, J. Pang, X. Wang and T. Zhang, *ChemSusChem*, 2010, **3**, 63; Y. Zhang, A. Wang and T. Zhang, *Chem. Commun.*, 2010, **46**, 862.

8 V. Jollet, F. Chambon, F. Rataboul, A. Cabiacc, C. Pinel, E. Guillon and N. Essayem, *Green Chem.*, 2009, **11**, 2052.

9 H. Kobayashi, T. Komanoya, K. Hara and A. Fukuoka, *ChemSusChem*, 2010, **3**, 440.

10 W. L. Marshall and E. U. Franck, *J. Phys. Chem. Ref. Data*, 1981, **10**, 295.

11 The optimisation of the reaction conditions using Ru/AC(N) catalyst is shown in the ESI: effect of the concentration of 2-propanol (Table S1), screening of the hydrogen source (Table S2).

12 W. Deng, M. Liu, X. Tan, Q. Zhang and Y. Wang, *J. Catal.*, 2010, **271**, 22.

13 R. Ryoo, S. H. Joo and S. Jun, *J. Phys. Chem. B*, 1999, **103**, 7743; S. Jun, S. H. Joo, R. Ryoo, M. Kruk, M. Jaroniec, Z. Liu, T. Ohsuna and O. Terasaki, *J. Am. Chem. Soc.*, 2000, **122**, 10712.