



Title	Photoelectrochemical Reduction of Carbon Dioxide at Si(111) Electrode Modified by Viologen Molecular Layer with Metal Complex
Author(s)	Sun, Yu; Masuda, Takuya; Uosaki, Kohei
Citation	Chemistry Letters, 41(3), 328-330 https://doi.org/10.1246/cl.2012.328
Issue Date	2012-03
Doc URL	http://hdl.handle.net/2115/52105
Type	article (author version)
File Information	CL41-3_328-330.pdf



[Instructions for use](#)

Photoelectrochemical Reduction of Carbon Dioxide at Si(111) Electrode Modified by Viologen Molecular Layer with Metal Complex

Yu Sun,¹ Takuya Masuda,² and Kohei Uosaki^{*1,2,3}

¹Division of Chemistry, Graduate School of Science, Hokkaido University, Sapporo 060-0810

²Global Research Center for Environment and Energy based on Nanomaterials Science (GREEN), National Institute for Materials Science (NIMS), Tsukuba 305-0044

³International Center for Materials Nanoarchitectonics (MANA), National Institute for Materials Science (NIMS), Tsukuba 305-0044

(Received <Month> <Date>, <Year>; CL-<No>; E-mail: <insert corresponding e-mail address>)

Photoelectrochemical carbon dioxide reduction was carried out at a p-type Si(111) electrode modified with a viologen molecular layer and AuCl_4^{2-} or PdCl_4^{2-} . It was proved that the reduction reaction was mediated by viologen moiety and while CO_2 reduction was dominant at the Si(111) electrode modified with PdCl_4^{2-} in the potential region where viologen moiety was in the first reduced state, it became dominant at the electrode modified with AuCl_4^{2-} when viologen moiety became the second reduced state. FT-IR measurement confirmed the formation of formic acid/formate ion at the PdCl_4^{2-} /viologen-modified Si electrode.


Carbon dioxide fixation attracts much interest of many scientists and engineers not only because CO_2 is considered to be one of the main causes of global warming¹ but also because it is scientifically very challenging to convert CO_2 , one of the most stable molecules, to fuels and useful chemicals.² Electrochemical reduction of CO_2 is one of the most studied systems,²⁻⁴ but very large overpotential and low current efficiency prevent its practical use. Moreover, if electricity is generated by using fossil fuel, more CO_2 is produced. Photoelectrochemical and photocatalytic reduction of CO_2 using semiconductor is ideal as solar energy can be utilized to reduce CO_2 .² Unfortunately, however, most of the semiconductors, which have a suitable bandgap for solar energy conversion, are corrosive in aqueous solutions.⁵ Furthermore, most of the semiconductor surfaces are not catalytically active for multi-electron transfer reactions such as hydrogen evolution and CO_2 reduction, because they do not adsorb reaction intermediates with suitable strength.⁶⁻⁸ One of the methods to solve these problems is to modify the semiconductor surface with metal or metal ions, which act as catalyst. But this approach has one severe problem that surface states, which act as charge recombination centers, are often introduced at the metal-semiconductor interface as a result of the surface modification by metal.⁹

Several groups used organic molecular layers to separate catalytic metals and semiconductor surfaces so that the introduction of surface states, which is the result of direct contact between catalytic metals and semiconductor surface, can be avoided and demonstrated that efficiencies of photoelectrochemical reactions are significantly enhanced, although the position and amount of catalyst are not well controlled.^{10,11} Recently, we have demonstrated that very efficient photoelectrochemical hydrogen evolution reaction (HER) can be achieved at a Si(111) electrode modified with a highly ordered organic molecular layer with viologen moieties, which is directly bonded to Si surface via Si-C bond, as an

electron mediator and Pt complex, which is confined within the molecular layer as a catalyst.^{12,13}

In this paper, we have extended this approach to photoelectrochemical carbon dioxide reduction at p-type Si(111) electrode modified with viologen molecular layer and various metal complexes. AuCl_4^- and PdCl_4^{2-} are chosen as complexes as electrochemical CO_2 reduction is known to proceed efficiently at Au and Pd electrodes while H_2 generation is dominant at Pt electrode in CO_2 saturated solution.¹⁴

Surface modification was carried out as schematically shown in Scheme 1. Details of the procedure for the modification by organic layers and characterization of modified surfaces have been reported before.¹² Briefly, a freshly prepared hydrogen-terminated (H-) Si(111) surface¹⁵ was sequentially treated to yield a viologen monolayer-modified (V^{++} -) Si(111) substrate: (1) H-Si(111) surface was illuminated with 254 nm light for 2 h in deaerated 4-vinylbenzylchloride to yield a 4-ethylbenzylchloride-modified (EBC-) Si(111) surface, (2) the substrate was then kept in benzene solution saturated with 4, 4'-bipyridine and then in 1-bromobutane, both at 70°C for 12 h to obtain a V^{++} -Si(111) surface. The V^{++} -Si(111) was immersed in an aqueous solution containing 10 mM of NaAuCl_4 or K_2PdCl_4 for 20 min at room temperature to yield Au- and Pd- V^{++} -Si(111) surfaces, respectively.

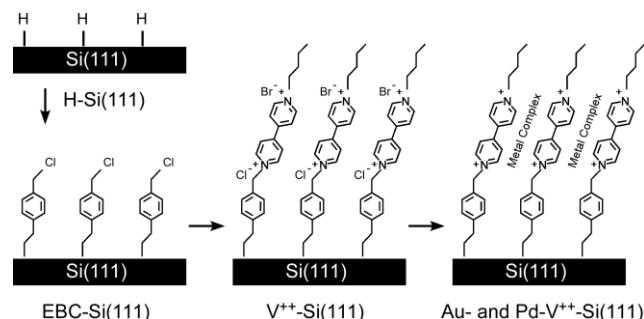

Scheme 1. Schematic illustration of the modification steps of hydrogen terminated (H-) Si(111) surface to obtain Au- and Pd- V^{++} -Si(111) surfaces. Metal Complex: AuCl_4^- and PdCl_4^{2-} . See the text for the detail.¹²

X-ray photoelectron spectra (XP spectra) obtained using a Rigaku model XPS-7000 with monochromatic $\text{Mg K}\alpha$ for the (A) Au- and (B) Pd- V^{++} -Si(111) surfaces in Au4f and Pd3d regions, respectively, confirm the incorporation of the metals.¹⁶

Figure 1 shows I-V curves of the (A) Au- and (B) Pd-V⁺⁺-Si(111) electrodes in Ar and CO₂ saturated 0.1 M Na₂SO₄ aqueous solutions. The pH of the Ar saturated 0.1 M Na₂SO₄ solution was adjusted to 4.4 by adding H₂SO₄, since the pH of 0.1 M Na₂SO₄ changed from 5.9 to 4.4 by CO₂ saturation. Relatively small current flowed at the n-Si(111) electrodes modified with viologen layer/metal complexes in dark both in Ar and CO₂ saturated solutions. However, currents in CO₂ saturated solution were clearly larger than those in Ar saturated solution at potentials more negative than ca. -0.5 V.

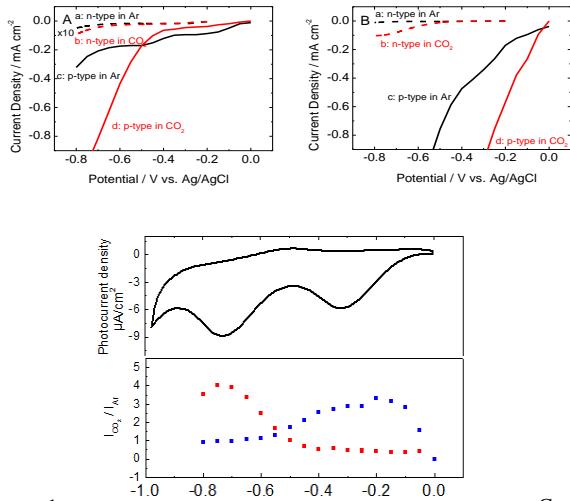


Figure 1. Current-voltage relations of (A) Au- and (B) Pd-V⁺⁺-Si(111) electrodes in 0.1 M Na₂SO₄ aqueous solutions saturated with Ar (black; a, c) and CO₂ (red; b, d) in dark (n-type, broken line; a, b) and under illumination (p-type, solid line; c, d) with a light intensity of 0.12 mW/cm². Scan rate: 1 mV/s. (C) Top panel: Cyclic voltammogram of p-type V⁺⁺-Si(111) electrodes in a 0.1 M Na₂SO₄ aqueous solution saturated with Ar under illumination with a light intensity of 0.12 mW/cm². Scan rate: 100 mV/s. Bottom panel: Ratio between currents at Au- (red) and Pd-V⁺⁺-Si(111) electrodes (blue) in CO₂ saturated solution and that in Ar saturated solution (I_{CO₂}/I_{AR}) as a function of potential.

Cathodic currents in both the Ar and CO₂ saturated solutions started to flow at much more positive potentials at the p-Si(111) electrodes modified with viologen layer/metal complexes under illumination¹⁷ than those at the modified n-Si(111) electrode in dark, although only negligibly small currents flowed in dark (< 5 μA at -0.8 V) as expected because electron is the minority carrier of p-type semiconductor. At the p-type Pd-V⁺⁺-Si(111) electrode, photocurrent started to flow at potential as positive as 0 V and increased significantly as potential became more negative both in the Ar and CO₂ saturated solutions. Photocurrent in the CO₂ saturated solution was larger than that in the Ar saturated solution in the potential region shown in Fig. 1 but both became almost the same as potential became more negative than ca. -0.6 V. On the other hand, although photocurrent started to flow also at around 0 V at the Au-V⁺⁺-p-Si(111) electrode in both solutions, it did not increase much even when potential was made more negative, particularly in the Ar saturated solution. Photocurrent in the CO₂ saturated solution significantly increased and became larger than that in the Ar saturated solution when potential became more negative than ca. -0.55 V.

These trends are more clearly seen in the bottom panel of Fig. 1(C), which shows potential dependencies of the ratio between photocurrents in the CO₂ (I_{CO₂}) and Ar saturated solutions (I_{AR}) at the Au-V⁺⁺- and Pd-V⁺⁺-Si(111) electrodes. At the Pd modified Si electrode, I_{CO₂} became larger than I_{AR} as soon as photocurrent started to flow at 0 V but I_{CO₂}/I_{AR} gradually decreased as potential became more negative than ca. -0.2 V and became 1 as potential became more negative than ca. -0.6 V as mentioned before. At the Au modified Si electrode, I_{CO₂} was smaller than I_{AR} in the relatively positive potential region but I_{CO₂}/I_{AR} increased significantly as potential became more negative than ca. -0.5 V and reached 4 at -0.7 V. The top panel of Fig. 1(C) is the Cyclic voltammogram (CV) of V⁺⁺-Si(111) electrode without metal complex under illumination obtained with very fast scan rate (50 mV/s). Reduction peaks of viologen moiety are clearly observed at -0.25 V and -0.7 V for the reduction of V⁺⁺ to V⁺ and of V⁺ to V⁻, respectively. Positions of these peaks were more positive than those observed at n-type V⁺⁺-Si(111) electrode in dark as expected.^{12(b)} Potential dependencies of photocurrent and I_{CO₂}/I_{AR} seem to be related to the reduced state of viologen moiety. While at the Pd-V⁺⁺-Si(111) electrode, large photocurrent flowed in both Ar and CO₂ saturated solution as soon as the reduction of V⁺⁺ to V⁺ started, at the Au-V⁺⁺-Si(111) electrode, only relatively small and almost no photocurrent were observed in Ar and CO₂ saturated solutions, respectively, in potential region where viologen moiety was in V⁺ and significant increase of photocurrent was observed in CO₂ saturated solution as soon as V⁺ was reduced to V⁻. This difference should be due to the difference in the energy to form adsorbed intermediate states on the metal catalysts.

As a qualitative analysis of the products of CO₂ reduction, in situ FT-IR measurements were performed at the Au- and Pd-V⁺⁺-Si(111) electrodes in 0.1 M Na₂SO₄ solution saturated with CO₂.¹⁸ Figure 2(A) shows IR spectra (s-polarization) obtained at the Pd-V⁺⁺-Si(111) in the CO₂ saturated 0.1 M Na₂SO₄ solution keeping the potential at -0.7 V for a given period of time under illumination with a spectrum measured in dark before illumination as a reference.

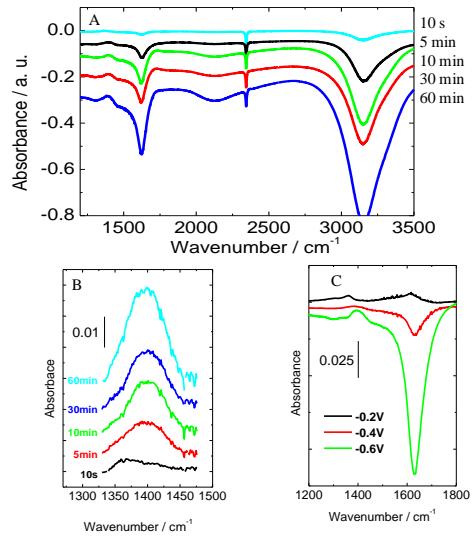


Figure 2. IR spectra at the Pd-V⁺⁺-Si(111) electrode in a CO₂ saturated 0.1 M Na₂SO₄ solution (A, B) with keeping the potential at -0.7 V for a given period of time under illumination in (A) 1250-3500 cm⁻¹ and (B)

1325-1475 cm⁻¹ regions with background correction, and (C) at various potentials in 1200-1800 cm⁻¹ region.

No significant difference was noticed between the p- and s-polarized spectra.²⁰ Negative going peaks due to the consumption in the thin layer were observed at around 1600, 2350, and 3,200 cm⁻¹, corresponding to bending of OH of water, CO stretching of dissolved CO₂, and OH stretching of water, respectively, showing that HER and CO₂ reduction proceeded. A small positive going peak due to the accumulation of reduction product was observed at around 1,410 cm⁻¹, which corresponds to symmetric stretch of carboxylate group. The growth of this peak with time is more clearly seen in Fig. 2 (B), which shows IR spectra in 1325-1475 cm⁻¹ region with correction of background due to strong negative going OH bending peak. This agrees with previous reports that the main product of electrochemical carbon dioxide reduction reaction at Pd electrode is formic acid/formate ion.²¹ Asymmetric stretching peak of carboxylate group, which should be present at around 1,510 cm⁻¹ is not visible because of strong negative going OH bending peak at this potential. IR spectra obtained various potentials shown in Fig. 2(C) indicate that at -0.2 V, the negative going OH bending peak is not visible and small positive going peaks due to symmetric and symmetric stretch of carboxylate group are observed. This is in good agreement with the result shown in Fig. 1(B) that dominant reaction at this potential is CO₂ reduction.

In situ FT-IR measurements obtained at the Au-V⁺⁺-Si(111) electrode in 0.1 M Na₂SO₄ solution saturated with CO₂ shows only negative going peaks due to the consumption in the thin layer at around 1600, 2350, and 3,200 cm⁻¹, corresponding to bending of OH of water, CO stretching of dissolved CO₂, and OH stretching of water, respectively, and no positive going peaks were observed. Thus, although it is confirmed that HER and CO₂ reduction proceeded at the Au-V⁺⁺-Si(111) electrode, no product was determined. According to previous reports, main product of CO₂ reduction at gold electrode is CO.¹⁴

In conclusion, photoelectrochemical carbon dioxide reduction was significantly enhanced by modifying Si(111) surfaces by the organic molecular layer with viologen moieties and AuCl₄²⁻ or PdCl₄²⁻. It was confirmed that viologen moiety plays an important role for mediating electron transfer from Si to metal catalysts. While CO₂ reduction was dominant at the Si(111) electrode modified with PdCl₄²⁻ in the potential region where viologen moiety was in the first reduced state, the second reduced state is required to reduce CO₂ at the electrode modified with AuCl₄²⁻. FTIR measurements confirmed the formation of formic acid/formate ion as a product of CO₂ reduction and selectivity of CO₂ reduction to HER is high at the positive potential at Pd-V⁺⁺-Si(111) electrode. The decrease of selectivity for CO₂ reduction at the Pd-V⁺⁺-Si(111) electrode as potential became negative should simply be due to the low surface concentration of CO₂ with respect H₂O (H⁺) for HER. More detailed analysis including gaseous products is under way.

Professors Katsuaki Shimazu and Toshikazu Kawaguchi are acknowledged for XPS measurements. The present work was partially supported by GCOE Program (Project No. B01: Catalysis as the Basis for Innovation in Materials Science), World Premier International Research Center (WPI) Initiative

on Materials Nanoarchitectonics, and MEXT Program for Development of Environmental Technology using Nanotechnology from Ministry of Education, Culture, Sports, Science and Technology, Japan. YS is supported by MEXT scholarship for foreign students.

References and Notes

- 1 J. O'M. Bockris, in *Energy Options*, Halsted, New York, **1980**.
- 2 M. M. Halmann, in *Chemical Fixation of Carbon Dioxide-Methods for Recycling CO₂ into Useful Products*, CRC, Florida, **1993**, Chap. 8, pp. 121-127.
- 3 M. Mikkelsen, M. Jorgensen, F. C. Kreds, *Energy Environ. Sci.* **2010**, *3*, 43.
- 4 Y. Hori, in *Modern Aspects of Electrochemistry*, ed. by C. G. Vayenas, R. White, M. Gamboa-aldeco, Springer, New York, **1999**, Vol. 42, Chap. 3, pp. 89-189.
- 5 A. Nozik, *Annu. Rev. Phys. Chem.* **1978**, *29*, 189.
- 6 J. O'M. Bockris, K. Uosaki, *J. Electrochem. Soc.* **1977**, *124*, 1348.
- 7 K. Uosaki, H. Kita, in *Modern Aspects of Electrochemistry*, ed. by R. E. Write, J. O'M. Bockris, B. E. Conway, Springer, New York, **1986**, Vol. 18, Chap. 3, pp. 1-60.
- 8 a) Y. Nakato, S. Tonomura, H. Tsubomura, *Ber. Bunsenges. Phys. Chem.* **1976**, *80*, 1289. b) W. Kautek, J. Gobrecht, H. Gerischer, *Ber. Bunsenges. Phys. Chem.* **1980**, *84*, 1034. c) A. Heller, *Acc. Chem. Res.* **1981**, *14*, 154. d) R. N. Dominey, N. S. Lewis, J. A. Bruce, D. C. Bookbinder, M. S. Wrighton, *J. Am. Chem. Soc.* **1982**, *104*, 467. e) F. R. E. Fan, R. G. Keli, A. J. Bard, *J. Am. Chem. Soc.* **1983**, *105*, 220. f) K. Uosaki, H. Kita, *Chem. Lett.* **1984**, *13*, 301. g) M. Szklarczyk, J. O'M. Bockris, *J. Phys. Chem.* **1984**, *88*, 5241.
- 9 a) Y. Nakato, K. Ueda, H. Yano, H. Tsubomura, *J. Phys. Chem.* **1988**, *92*, 2316. b) K. Uosaki, Y. Shigematsu, H. Kita, *Chem. Lett.* **1988**, *11*, 1815. c) K. Uosaki, Y. Shigematsu, S. Kaneko, H. Kita, *J. Phys. Chem.* **1989**, *93*, 6521.
- 10 a) D. C. Bookbinder, J. A. Bruce, R. N. Dominey, N. S. Lewis, M. S. Wrighton, *Proc. Natl. Acad. Sci. USA* **1980**, *77*, 6280. b) R. N. Dominey, N. S. Lewis, J. A. Bruce, D. C. Bookbinder, M. S. Wrighton, *J. Am. Chem. Soc.* **1982**, *104*, 467.
- 11 a) K. Nakato, S. Takabayashi, A. Imanishi, K. Murakoshi, Y. Nakato, *Sol. Energy Mat. Sol. C* **2004**, *83*, 323. b) S. Takabayashi, M. Ohashi, K. Mashima, Y. Liu, S. Yamazaki, Y. Nakato, *Langmuir* **2005**, *21*, 8832.
- 12 a) T. Masuda, K. Uosaki, *Chem. Lett.* **2004**, *33*, 788. b) T. Masuda, K. Shimazu, K. Uosaki, *J. Phys. Chem. C* **2008**, *112*, 10923.
- 13 T. Masuda, H. Fukumitsu, S. Takakusagi, W. J. Chun, T. Kondo, K. Asakura, K. Uosaki, *Adv. Mater.* **2012**, *24*, 268.
- 14 a) Y. Hori, H. Wakebe, T. Tsukamo, O. Koga, *Electrochimica Acta* **1994**, *39*, 1833. b) M. Azuma, K. Hashimoto, M. Hiramoto, *J. Electrochem. Soc.*, **1990**, *137*, 1772.
- 15 S. Ye, T. Ichihara, K. Uosaki, *Appl. Phys. Lett.* **1999**, *75*, 1562.
- 16 G. E. Muilenberg, in *Handbook of X-Ray Photoelectron Spectroscopy*, Perkin-Elmer, Minnesota, **1978**.
- 17 Illumination was provided by a 500 W xenon lamp (Ushio, UXL-500-D) through an IR cut filter (Toshiba, IRA-20), a UV cut filter (Sigma Koki) and an ND filter (Toshiba).
- 18 ATR FT-IR spectra were obtained in thin layer configuration¹⁹ using a Bio-Rad FTS-30 spectrometer equipped with a mercury cadmium telluride (HgCdTe) detector cooled with liquid nitrogen. A diode laser (13 mW cm⁻²) was used as a light source. All the spectra were measured by integrating 32 interferograms with a resolution of 2 cm⁻¹.
- 19 K. Uosaki, Y. Shigematsu, H. Kita, K. Kunimatsu, *J. Phys. Chem.*, **94**, *11*, 4623-4627 (1990).
- 20 It must be noted the non-zero contribution of surface species in s-polarized IR spectra at semiconductor electrode, although s-polarized IR spectra at metal electrode contains no information from the surface species.¹⁹
- 21 a) K. Ohkawa, K. Hashimoto, A. Fujishima, *J. Electroanal. Chem.* **1993**, *345*, 445. b) K. Ohkawa, Y. Noguchi, S. Nakayama, K. Hashimoto, A. Fujishima, *J. Electroanal. Chem.* **1994**, *369*,

Graphical Abstract

Textual Information

Description (if any)

Title

Photoelectrochemical Reduction of Carbon Dioxide at Si(111) Electrode Modified by Viologen Molecular Layer with Metal Complex

Authors' Names

Yu Sun, Takuya Masuda, and Kohei Uosaki

Graphical Information

