



Title	Odd-frequency Cooper pair around a magnetic impurity
Author(s)	Suzuki, Shu-Ichiro; Sato, Takumi; Asano, Yasuhiro
Citation	Physical Review B, 106(10), 104518 https://doi.org/10.1103/PhysRevB.106.104518
Issue Date	2022-09-29
Doc URL	http://hdl.handle.net/2115/87281
Rights	©[2022] American Physical Society
Type	article
File Information	PhysRevB.106.104518.pdf



[Instructions for use](#)

Odd-frequency Cooper pair around a magnetic impurity

Shu-Ichiro Suzuki ^{1,2}, Takumi Sato ³, and Yasuhiro Asano ³

¹Department of Applied Physics, Nagoya University, Nagoya 464-8603, Japan

²Faculty of Science and Technology, University of Twente, P.O. Box 217, 7500 AE Enschede, The Netherlands

³Department of Applied Physics, Hokkaido University, Sapporo 060-8628, Japan

 (Received 7 April 2022; revised 26 May 2022; accepted 15 September 2022; published 29 September 2022)

The Yu-Shiba-Rusinov (YSR) state appears as a bound state of a quasiparticle at a magnetic atom embedded in a superconductor. We discuss why the YSR state has energy below the superconducting gap and why the pair potential changes the sign at the magnetic atom. Although a magnetic atom in a superconductor has been considered as a pair breaker since the 1960s, we propose an alternative physical picture to explain these reasons. The analytical expression of the Green's function indicates that a magnetic atom converts a spin-singlet s -wave Cooper pair into odd-frequency Cooper pairs rather than breaking it and that the odd-frequency pairing correlations coexist with the YSR states below the gap. The relationships among the free-energy density, the amplitudes of pairing correlation functions, and the sign change of the pair potential at a magnetic impurity are discussed utilizing the self-consistent solution of the Eilenberger equation. We conclude that the sign change of the pair potential happens only when the amplitudes of odd-frequency pairing correlations are dominant at the magnetic impurity. In the presence of the local π -phase shift in the pair potential, odd-frequency pairs can decrease the free-energy density there because their response to a magnetic field is paramagnetic.

DOI: [10.1103/PhysRevB.106.104518](https://doi.org/10.1103/PhysRevB.106.104518)

I. INTRODUCTION

The Yu-Shiba-Rusinov (YSR) state [1–3] is a bound state around a magnetic impurity embedded in a superconductor and is considered to appear as a result of breaking a spin-singlet Cooper pair by the magnetic moment. Superconducting junctions with the YSR states have been attracting renewed attention as a possible platform for quantum computer architectures. Actually, it is known that a chain of magnetic nanoparticles on an s -wave superconductor accommodates Majorana fermions at its ends [4–6]. Controlling the superconducting subgap state is a necessary element of future quantum technology [7–9].

A spin-singlet Cooper pair is formed by two electrons that are time-reversal partners to each other. Thus a magnetic impurity (a defect breaking time-reversal symmetry) acts as a pair-breaker. Indeed, it is widely accepted that magnetic impurities drastically suppress the superconducting transition temperature T_c [10,11]. Although the formation of the YSR state was pointed out in the 1960s, there are three unsolved issues: (i) This conventional simple picture does not explain why magnetic impurity generates the YSR states *below the gap*. (ii) A strong magnetic impurity changes the sign of the pair potential around the impurity site [12–15]. As briefly mentioned in a review paper [16], there is no convincing explanation for the local π -phase shift even now. (iii) It has been unclear the relation between the appearance of the YSR states and the suppression of T_c . In this paper, we will show that the existence of odd-frequency Cooper pairs around the magnetic impurity provides a satisfactory explanation for these issues.

The odd-frequency Cooper pairing is a concept that was introduced by Berezinskii [17] to explain the superfluidity in ^3He . Although there has been much theoretical work on odd-frequency superconducting states in bulk systems since the 1990s [18–25], experimental evidence is still lacking. One of the authors showed that the spatially uniform odd-frequency superconducting order is impossible in single-band metals [26]. However, it turns out that the odd-frequency spin-triplet s -wave triplet state can be realized as an induced subdominant pairing correlation in a rather conventional system consisting of a spin-singlet s -wave superconductor and a ferromagnet [27]. Induced odd-frequency pairing correlations have been discussed in connection with a subgap quasiparticle appearing at a surface of unconventional superconductors [28–32], a vortex core [33,34], and an edge of a Majorana nanowire [35]. In superconductors having internal degrees of freedom (e.g., sublattices, multiorbital, and multiband), a quasiparticle on the Bogoliubov Fermi surface [36] accompanies an odd-frequency Cooper pair [37]. Although the odd-frequency pairing correlations around a magnetic impurity were pointed out by recent studies [38,39], physical phenomena unique to an odd-frequency Cooper pair have not been discussed yet. The most important property of odd-frequency Cooper pairs is that they exhibit a paramagnetic response to an external magnetic field [40–43]. When the amplitude of an odd-frequency pair is dominant at some place in a superconductor, the spatial gradient in the superconducting phase decreases the free energy there. Indeed, two of the authors showed that the magnetic response of a small unconventional superconductor can be paramagnetic at low temperature [42]. We summarize

the physical consequences of paramagnetic Cooper pairs in Appendix A.

In this paper, we calculate the Green's function around a magnetic impurity in a spin-singlet s -wave superconductor both analytically and numerically. The analytical expression of the anomalous Green's function shows that the magnetic impurity converts a spin-singlet s -wave Cooper pair into an odd-frequency Cooper pair. The direct comparison between the normal and the anomalous Green's functions explains well the coexistence of such an odd-frequency pair and a quasiparticle at the YSR states. Thus the formation of YSR states below the gap is a natural consequence of the appearance of an odd-frequency pair. As a result of the symmetry conversion of a Cooper pair, the amplitude of the spin-singlet s -wave pairing correlation decreases down to zero and changes sign with an increase of the amplitude of the magnetic moment. To explain why the pair potential changes sign around a magnetic impurity, we analyze the free-energy density and the pairing correlation function around the magnetic impurity by solving the Eilenberger equation [44,45] numerically. The results show that the free-energy density at a magnetic impurity can be larger than that in the normal state. Such an unusual local state is possible only in an inhomogeneous superconductor. Odd-frequency Cooper pairs increase the free-energy density because they are thermodynamically unstable under the spatially uniform pair potential. We also show that the free-energy density at the impurity is decreased by the π -phase shift in the pair potential when odd-frequency Cooper pairs stay more dominantly than even-frequency pairs. The paramagnetic response of odd-frequency pairs explains naturally the close relationships among the appearance of an odd-frequency Cooper pair, the local π -phase shift in the pair potential, and the instability of the superconducting state around the impurity. As an extension of the main conclusions, we also discuss the decrease of transition temperature T_c in the presence of a number of magnetic impurities.

This paper is organized as follows. In Sec. II, we summarize the pairing correlations around a magnetic impurity embedded in a superconductor in one dimension. In Sec. III, we display numerical results of the pair potential, the local density of states, the pairing correlations, and the free-energy density. We explain why the appearance of odd-frequency pairs decreases T_c in Sec. IV. The conclusion is given in Sec. V. Throughout this paper, we use the system of units $\hbar = k_B = c = 1$, where k_B is the Boltzmann constant and c is the speed of light.

II. COOPER PAIRS AROUND A MAGNETIC IMPURITY

Let us consider a spin-singlet s -wave superconductor in one dimension where a magnetic impurity is embedded at $x = 0$. The Bogoliubov-de Gennes (BdG) Hamiltonian of a superconductor is given by

$$\check{H}_{\text{BdG}}(x) = \begin{bmatrix} \xi_x & \Delta i \hat{\sigma}_2 e^{i\varphi} \\ \Delta (-i) \hat{\sigma}_2 e^{-i\varphi} & -\xi_x^* \end{bmatrix} + \check{V}(x), \quad (1)$$

$$\xi_x = -\frac{1}{2m} \frac{d^2}{dx^2} - \epsilon_F, \quad (2)$$

where Δ is the uniform pair potential in spin-singlet s -wave symmetry, ϵ_F is the Fermi energy, \check{V} represents the impurity potential, and $\hat{\sigma}_j$ for $j = 1-3$ is the Pauli matrix in spin space. The potential of a paramagnetic impurity at $x = 0$ is described by

$$\check{V}(x) = \begin{bmatrix} \mathbf{V} \cdot \hat{\boldsymbol{\sigma}} & 0 \\ 0 & -\mathbf{V} \cdot \hat{\boldsymbol{\sigma}}^* \end{bmatrix} \delta(x). \quad (3)$$

The Gor'kov equation reads

$$[i\omega_n - \check{H}_{\text{BdG}}(x)] \check{\mathcal{G}}(x - x') = \check{\mathcal{I}} \delta(x - x'), \quad (4)$$

where $\omega_n = (2n + 1)\pi T$ is the Matsubara frequency, with n and T being an integer number and a temperature, respectively. The Green's function has a structure

$$\check{\mathcal{G}}(x, x') = \begin{bmatrix} \hat{g}(x, x') & \hat{f}(x, x') \\ -\hat{f}^*(x, x') & -\hat{g}^*(x, x') \end{bmatrix}, \quad (5)$$

because of particle-hole symmetry in the BdG Hamiltonian. As shown in Appendix B, the Green's function in the presence of an impurity can be calculated exactly. The normal Green's function is shown in Eq. (B14) in Appendix B. The density of states are calculated from the normal Green's function in the retarded causality,

$$\begin{aligned} N(x, \epsilon) &= -\frac{1}{4\pi} \text{Im Tr} [\check{\mathcal{G}}_\epsilon^R(x, x)], \\ &= -\frac{1}{4\pi} \text{Im Tr} [\hat{g}_\epsilon^R(x, x) - (\hat{g}_\epsilon^R)^*(x, x)], \\ \check{\mathcal{G}}_\epsilon^R(x, x') &= \check{\mathcal{G}}(x, x')|_{i\omega_n \rightarrow \epsilon + i\delta}, \end{aligned} \quad (6)$$

where δ is a small positive real value. The retarded Green's function at $x = x'$ for $0 \leq \epsilon < \Delta$ is calculated as

$$\text{Tr} [\check{\mathcal{G}}_\epsilon^R(x, x)] = \frac{4\pi N_0 \epsilon}{\sqrt{\Delta^2 - \epsilon^2}} \left[1 - e^{-2|x|/\xi_0} |\boldsymbol{\gamma}|^2 \frac{2\Delta^2 + \{\Delta^2(1 - |\boldsymbol{\gamma}|^2) + \epsilon^2(1 + |\boldsymbol{\gamma}|^2)\} \cos 2k|x|}{\Delta^2(1 - |\boldsymbol{\gamma}|^2) - \epsilon^2(1 + |\boldsymbol{\gamma}|^2)} \right], \quad (7)$$

where N_0 is the density of states per spin at the Fermi level, and $\boldsymbol{\gamma} = \pi N_0 \mathbf{V}$. The first term representing the bulk superconducting gap does not contribute to the density of states for $0 < |\epsilon| < \Delta$. The second term represents a quasiparticle excitation at a magnetic impurity. It is easy to show that the denominator has poles at $\epsilon = \pm \epsilon_0$ with

$$\epsilon_0 = \Delta \frac{1 - |\boldsymbol{\gamma}|^2}{1 + |\boldsymbol{\gamma}|^2}, \quad (8)$$

TABLE I. Symmetry of the potential for random magnetic impurities in three theoretical models. The potential of a magnetic impurity in Eq. (3) breaks translational symmetry, inversion symmetry locally, spin-rotation symmetry, and time-reversal symmetry. Breaking local inversion symmetry enables the parity conversion of the pairing correlation between even-parity and odd-parity as indicated by (a). Breaking spin-rotation symmetry enables the spin conversion of the pairing correlation between spin-singlet and spin-triplet as indicated by (b). In the self-consistent Born approximation resulting in Eqs. (20) and (22), translational, local inversion, and spin-rotation symmetries are restored in the self-energy due to magnetic impurities. The renormalization factor changes sign in the absence of time-reversal symmetry, as indicated by (c). In the present theory resulting in Eq. (32), translational and local inversion symmetries are recovered by averaging Eq. (31). Since spin-rotation symmetry is broken as indicated by (d), the odd-frequency spin-triplet even-parity state can be considered as an intermediate state for scatterings.

	Translational	Local inversion	Spin-rotation	Time-reversal
A magnetic impurity	×	× ^(a)	× ^(b)	×
Born approximation	○	○	○	× ^(c)
Present theory	○	○	× ^(d)	×

which corresponds to an energy of the YSR state. The anomalous Green's function is also calculated as

$$\begin{aligned}
 \hat{f}(x, x') = & \frac{\pi N_0 \Delta}{\Omega} \left[-\cos k(|x - x'|) e^{-|x-x'|/\xi_0} + \frac{e^{-(|x|+|x'|)/\xi_0} |\boldsymbol{\gamma}|^2}{Z} \{2\omega_n^2(C_+ + C_-) - \Omega^2(1 - |\boldsymbol{\gamma}|^2)C_+\} \right] i\hat{\sigma}_2 e^{i\varphi} \\
 & + \frac{\pi N_0 \Delta e^{-(|x|+|x'|)/\xi_0}}{Z} 2i\omega_n |\boldsymbol{\gamma}|^2 S_- i\hat{\sigma}_2 e^{i\varphi} - \frac{\pi N_0 \Delta e^{-(|x|+|x'|)/\xi_0}}{Z} \Omega(1 - |\boldsymbol{\gamma}|^2) S_- \boldsymbol{\gamma} \cdot \hat{\boldsymbol{\sigma}} i\hat{\sigma}_2 e^{i\varphi} \\
 & + \frac{\pi N_0 \Delta e^{-(|x|+|x'|)/\xi_0}}{Z} i\omega_n \{(1 + |\boldsymbol{\gamma}|^2)C_+ + (1 - |\boldsymbol{\gamma}|^2)C_-\} \boldsymbol{\gamma} \cdot \hat{\boldsymbol{\sigma}} i\hat{\sigma}_2 e^{i\varphi}, \tag{9}
 \end{aligned}$$

with S_{\pm} and C_{\pm} in Eq. (B11), and Z in Eq. (B15). Similar results were obtained in the previous paper [38].

The first term stems from the unperturbed Green's function. The second term is the pairing correlation at the impurity. These two terms belong to an even-frequency spin-singlet even-parity s -wave symmetry class and are linked to the pair potential through the gap equation. In Table I, we summarize symmetries broken by a magnetic impurity. Equation (3) breaks translational symmetry, inversion symmetry in the vicinity of $x = 0$, spin-rotation symmetry, and time-reversal symmetry. As a consequence, a magnetic impurity generates various pairing correlations, as shown in Eq. (9). The absence of local inversion symmetry allows the generation of an odd-parity p -wave Cooper pair from an even-parity s -wave pair. Indeed, the third term in Eq. (9) is the pairing correlation belonging to the odd-frequency spin-singlet odd-parity symmetry class because it is an odd function of ω_n , proportional to $\hat{\sigma}_2$, and antisymmetric under the interchange of $x \leftrightarrow x'$. The breaking spin-rotation symmetry enables the generation of a spin-triplet Cooper pair from a spin-singlet pair. The last term in Eq. (9) represents the pairing correlation belonging to the odd-frequency spin-triplet even-parity symmetry class. It is easy to confirm that the last term is symmetric under the interchange of $x \leftrightarrow x'$. As a result of breaking spin-rotation symmetry and local inversion symmetry simultaneously, even-frequency spin-triplet odd-parity pairing correlation appears as indicated by the fourth term in Eq. (9). It is more natural to think that the magnetic impurity converts a spin-singlet s -wave Cooper pair into a Cooper pair belonging to another symmetry class rather than destroying it.

Comparing the normal and the anomalous Green's function enables us to understand the close relationship between odd-frequency pairs and quasiparticles in the YSR states. The

local density of states (LDOS) derived from the second term of Eq. (7) is calculated as

$$\begin{aligned}
 N_{\text{YSR}}(x, \epsilon) = & -N_0 \Delta \frac{|\boldsymbol{\gamma}|}{1 + |\boldsymbol{\gamma}|^2} \\
 & \times Y(x) \text{Im} \left[\frac{1}{\epsilon + i\delta - \epsilon_0} + \frac{1}{\epsilon + i\delta + \epsilon_0} \right] \tag{10}
 \end{aligned}$$

for $\epsilon \approx \pm\epsilon_0$, where the function

$$Y(x) = e^{-2|x|/\xi_0} (\cos^2 kx + |\boldsymbol{\gamma}|^2 \sin^2 kx) \tag{11}$$

represents the x dependence of the Green's function, and

$$\frac{1}{\epsilon + i\delta \pm \epsilon_0} = \frac{\mathcal{P}}{\epsilon \pm \epsilon_0} - i\pi \delta(\epsilon \pm \epsilon_0) \tag{12}$$

gives two peaks in the LDOS due to YSR states below the gap. The last term of Eq. (9) indicated by \hat{f}_{OTE} describes the odd-frequency spin-triplet even-parity pairing correlation and is calculated to be

$$\begin{aligned}
 \hat{f}_{\text{OTE}}(x, x) = & -\pi N_0 \Delta \frac{\boldsymbol{\gamma} \cdot \hat{\boldsymbol{\sigma}}}{1 + |\boldsymbol{\gamma}|^2} i\hat{\sigma}_2 e^{i\varphi} \\
 & \times Y(x) \left[\frac{1}{i\omega_n - \epsilon_0} + \frac{1}{i\omega_n + \epsilon_0} \right]. \tag{13}
 \end{aligned}$$

The two Green's functions in Eqs. (10) and (13) have the same x dependence and the same singularity in energy. Since the two Green's functions satisfy the Gor'kov equation, the singularity at $\epsilon = \pm\epsilon_0$ in the normal Green's function in Eq. (10) and that in the anomalous Green's function in Eq. (13) compensate each other. The former describes the peaks in the LDOS reflecting the existence of YSR states, and the latter represents the odd-frequency pairing correlation. Therefore, odd-frequency Cooper pairs and subgap quasiparticles at YSR

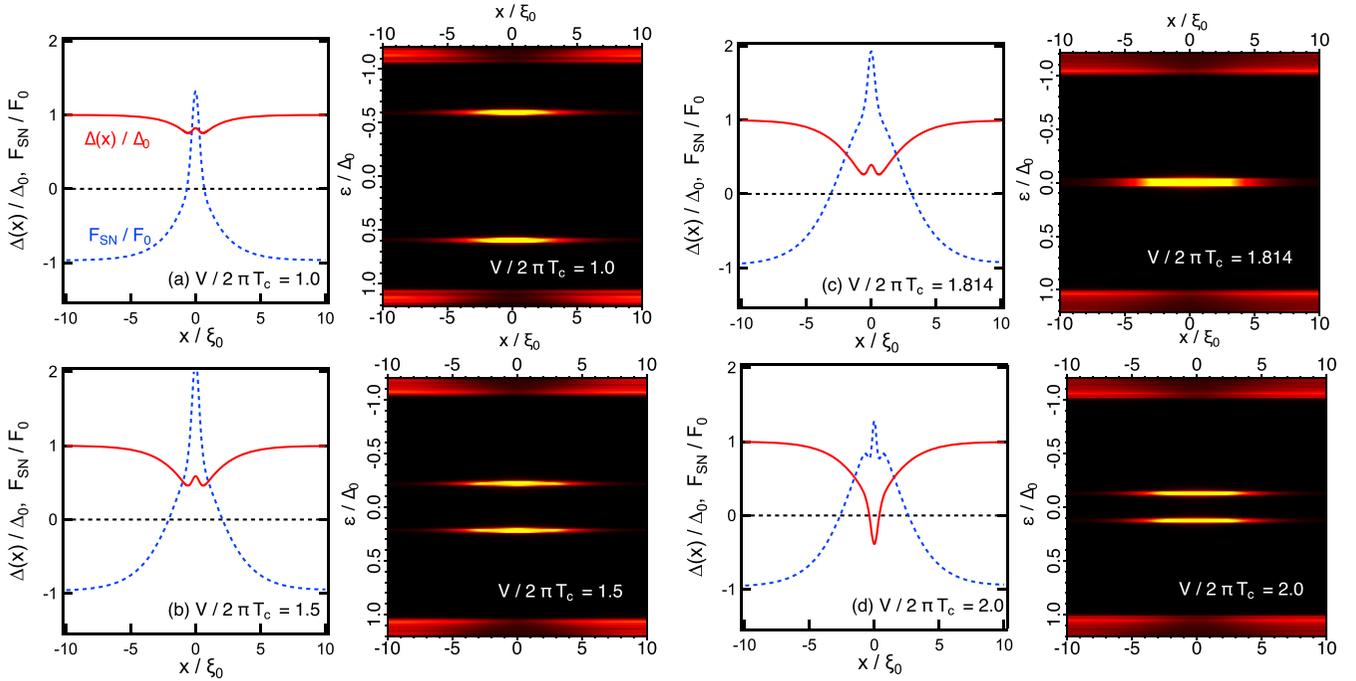


FIG. 1. The numerical results of the pair potential $\Delta(x)$ and the free-energy density F_{SN} , and the local density of states $N(x, \epsilon)$ are plotted for several choices of the amplitude of magnetic moment as $|V|/2\pi T_c = 1.0$ in (a), 1.5 in (b), 1.814 in (c), and 2.0 in (d). The pair potential shown with a solid line is normalized to Δ_0 , which is the amplitude of the pair potential in a uniform superconductor at $T = 0$. The free-energy density shown with a broken line is normalized to $F_0 = N_0 \Delta_0^2 / 2$. The local density of states is shown on the right panel, where we solve the Eilenberger equation for complex energies $\epsilon + i\delta$ with $\delta/2\pi T_c = 0.005$. The size of a magnetic impurity in Eq. (16) is set as $x_0/\xi_0 = 0.5$.

states coexist with each other. As far as we have studied, odd-frequency pairs are almost always associated with subgap quasiparticles. Thus the appearance of the YSR states below the gap is a direct consequence of the generation of the odd-frequency pairing correlations.

The pair potential and the pairing correlation functions are related to each other by the gap equation

$$\Delta(x) = T \sum_{\omega_n} \lambda \frac{1}{2} \text{Tr}[\hat{f}(x, x)(-i\delta_2)], \quad (14)$$

where λ is the strength of the short-range attractive interaction between two electrons. Tracing in spin space and putting $x' \rightarrow x$, the spin-singlet s -wave component is extracted from Eq. (9). As a result, only the first two terms in Eq. (9) contribute to the pair potential. The gap equation at $x = 0$,

$$\Delta(0) = \pi \lambda N_0 T \sum_{\omega_n} \frac{\Delta \Omega (1 - |\gamma|^2)}{Z}, \quad (15)$$

suggests that the pair potential at the impurity decreases with the increase of the magnetic moment. The suppression of Δ can be interpreted as a result of the pair conversion from a spin-singlet s -wave pair to an odd-frequency pair. Strictly speaking, an idealistic magnetic impurity characterized by the δ -function in Eq. (3) does not change the sign of the pair potential [3]. But a magnetic impurity with a finite size causes the sign change of the pair potential when its magnetic moment is larger than a critical value irrespective of the spatial dimension of a superconductor [12,13]. It has been unclear what causes the sign change of the pair potential [16]. As we discussed briefly in the Introduction, an odd-frequency

pair indicates the paramagnetic response to a magnetic field and favors the spatial gradient in the superconducting phase. Therefore, odd-frequency pairs around the magnetic impurity stabilize the local π -phase shift in the pair potential. In the next section, we will check the validity of this conclusion by numerical simulation.

III. SIGN CHANGE IN THE PAIR POTENTIAL

In Sec. II, we assume that the pair potential is uniform in real space. In this section, we check the validity of our conclusions in the presence of spatial variation in the pair potential. In particular, we focus on the effects of odd-frequency pairs on the sign change of the pair potential. We solve the Eilenberger equation in a superconductor in one dimension, where the potential of a magnetic impurity is described by

$$V(x) = V e^{-\left(\frac{x}{x_0}\right)^2}, \quad (16)$$

where x_0 represents the spatial range of the impurity potential. The details of the simulation are shown in Appendix C. We numerically calculate the pair potential in Eq. (C13) and the LDOS in Eq. (C14). In this section, we measure the length and the energy in units of the coherence length $\xi_0 = v_F/2\pi T_c$ and $2\pi T_c$, respectively. Here we summarize parameters used in numerical simulation. The length of the superconductor is fixed at $20\xi_0$, x_0 in Eq. (16) is $0.5\xi_0$, and the cutoff energy ω_c for the Matsubara frequency is $3 \times 2\pi T_c$.

Figure 1 shows the pair potential and LDOS around a magnetic impurity for several choices of the amplitude of magnetic moment $|V|$, where Δ_0 is the amplitude of the pair potential in the bulk at $T = 0$. The results at $|V|/2\pi T_c = 1.0$

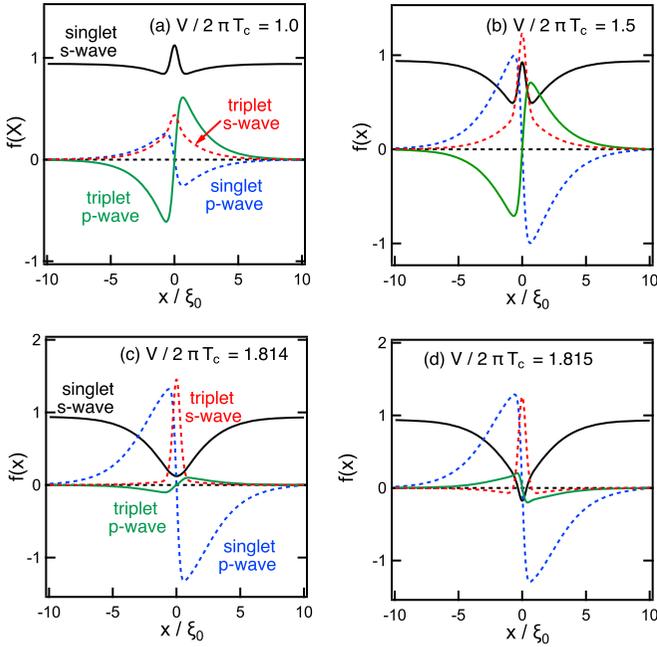


FIG. 2. The amplitude of the pairing correlations around the magnetic impurity for (a) $|V|/2\pi T_c = 1$, (b) 1.5, (c) 1.814, and (d) 1.815. The solid (broken) lines are the results of even-frequency (odd-frequency) components. The Matsubara frequency is fixed at $\omega_{n=0}/2\pi T_c = 0.1$.

in Fig. 1(a) show the slight suppression of the pair potential around a magnetic impurity. The LDOS in the right panel of (a) indicates the existence of the YSR states around the impurity. The energy of the bound state is about $\epsilon = \pm 0.6\Delta_0$, which is related to the minimum gap size around the impurity. For $|V|/2\pi T_c = 1.5$ in Fig. 1(b), a magnetic impurity suppresses the pair potential further. As a result, the two bound-state energies get closer to the Fermi level as shown in the right panel in (b). The minimum gap size is $0.45\Delta_0$ and the energy of a YSR state is $\pm 0.21\Delta_0$. Although the minimum gap size for $|V|/2\pi T_c = 1.814$ is $0.26\Delta_0$ in Fig. 1(c), the two YSR states exist at almost zero energy. When the magnetic moment increases up to $|V|/2\pi T_c = 2$, the pair potential at the impurity changes sign and the two bound-state energies cross, as shown in Fig. 1(d). The one-dimensional superconductor with a magnetic impurity is similar to the SFS junction. The cross of the Andreev bound-state energies at an SFS junction is responsible for the transition between the 0-state and the π -state [46].

In Fig. 2, we plot the amplitude of the pairing correlations around the magnetic impurity at $\omega_n/2\pi T_c = 0.1$, where we choose (a) $|V|/2\pi T_c = 1.0$, (b) 1.5, (c) 1.814, and (d) 1.815. In Fig. 2(a), the spin-singlet s -wave component is the most dominant and has a small peak at $x = 0$, which results in a tiny peak in the pair potential at $x = 0$ as shown in Fig. 1(a). The amplitude of the even-frequency spin-triplet p -wave component is the second most dominant. The odd-frequency spin-triplet s -wave and the odd-frequency spin-singlet p -wave components shown with broken lines are subdominant everywhere in a superconductor at $|V|/2\pi T_c = 1.0$. The appearance of an odd-frequency pair and the spatial variation

in the pair potential are related to each other [47]. In this case, the local odd-frequency pairing correlation generates the tiny peak at $x = 0$ in the pair potential in Fig. 1(a). In addition to this, odd-frequency pairs make the superconducting state unstable locally. We calculate the free-energy density in Eq. (C16) and plot the results with a broken line in Fig. 1(a). The free-energy density is almost equal to $-F_0$ far from the impurity, where $F_0 = N_0\Delta_0^2/2$ is the condensation energy of the uniform superconducting state measured from the energy of the normal state. The negative free energy means that the superconducting state is more stable than the normal state. Although the odd-frequency pairing correlations are subdominant as shown in Fig. 2(a), the free-energy density becomes positive at $x = 0$ in Fig. 1(a). The positive free energy at some place does not mean the absence of the pair potential there immediately. Such a locally destroyed superconductivity cannot be a self-consistent solution of the Eilenberger equation. To achieve zero pair potential at the impurity, the spin-singlet s -wave correlation must rapidly become zero in real space. This costs the kinetic energy of the superconducting condensate. The nonzero pair potentials under the positive free-energy density are only locally possible in inhomogeneous superconductors. The total free energy of such an inhomogeneous superconducting state is lower than that in the normal state.

Under a spatially uniform pair potential, odd-frequency Cooper pairs are thermodynamically unstable because of their paramagnetic property. The results of the free-energy density in Fig. 1 show that the superconducting state is locally unstable due to the presence of odd-frequency pairs. When we increase the magnetic moment to $|V|/2\pi T_c = 1.5$, the spin-singlet s -wave correlation decreases its amplitude slightly, as shown in Fig. 2(b). In contrast, the two odd-frequency pairing correlations grow as shown with broken lines. As a result, the free-energy density around $x = 0$ in Fig. 1(b) increases and becomes larger than that in (a). In Fig. 2(c), we increase the magnetic moment to $|V|/2\pi T_c = 1.814$. The spin-singlet s -wave correlation is suppressed drastically at $x = 0$ and the two odd-frequency pairing correlations become dominant locally around the impurity, as shown with two broken lines. In Fig. 2(d), we increase the magnetic moment only slightly to $|V|/2\pi T_c = 1.815$. The spin-singlet s -wave component changes sign around $x = 0$, which leads to the local sign change of the pair potential. The profiles of the two odd-frequency components, on the other hand, are insensitive to the slight increase of $|V|$.

In Fig. 3, we compare the pair potential in (a) and the free-energy density in (b) at the two values of $|V|/2\pi T_c = 1.814$ and 1.815. The abrupt sign change of the pair potential in Fig. 3(a) happens as a result of the finite-size effect. The local sign change in the pair potential causes the drastic decrease of the free-energy density as shown in Fig. 3(b). The free energy for $|x| < 0.8\xi_0$ in the presence of the sign change is smaller than that in the absence of the sign change. As displayed in both Figs. 2(c) and 2(d), odd-frequency pairs are dominant in such places. As odd-frequency pairs are paramagnetic, the sign change of the pair potential is one of the possible solutions to decrease the free-energy density. We conclude that odd-frequency pairs generated by a magnetic impurity cause the local π -phase shift in the pair potential near the impurity.

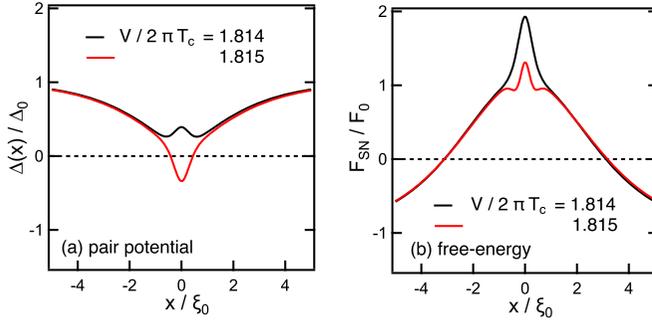


FIG. 3. The pair potential (a) and the free-energy density (b) are plotted for $|V|/2\pi T_c = 1.814$ and 1.815 . At $|V|/2\pi T_c = 1.815$, the pair potential at $x = 0$ changes sign, as shown in (a). As a result of the sign change, the free energy at $|V|/2\pi T_c = 1.815$ can be smaller than that at $|V|/2\pi T_c = 1.814$.

Finally, we show that the overall sign change in the spin-triplet p -wave component [Figs. 2(c) and 2(d)] does not affect the free-energy density. The pairing correlations are calculated from the parameters a_ν for $\nu = 0-3$ as shown in Eqs. (C9)–(C14). Thus the overall sign change of the pairing correlation is derived from that of a_ν (i.e., $a_\nu \rightarrow -a_\nu$). The induced pairing correlations contribute to the free-energy density through the second term in Eq. (C16). The function \mathcal{N}_0 shown in Eq. (C14) consists of the products of a_ν and its particle-hole conjugation \underline{a}_ν . Thus the overall sign change of the spin-triplet p -wave component does not affect the free-energy density because $a_\nu \underline{a}_\nu$ remains unchanged under a_ν to $-a_\nu$.

IV. SUPPRESSION OF T_c

It has been widely accepted since the 1960s that the transition temperature decreases with the increase of the magnetic impurity concentration [10,11]. We first summarize the outline of these historical papers. The transition temperature is determined by solving the linearized gap equation,

$$\Delta = gN_0 2\pi T \sum_{\omega_n > 0} F, \quad (17)$$

where F is the linearized anomalous Green's function, and it is $F = F_0 = \Delta/|\omega_n|$ in the clean limit. The anomalous Green's function is renormalized by the self-energy due to impurity scatterings. For nonmagnetic impurities, the anomalous Green's function is calculated as

$$F = F_{\text{nm}} = \frac{\tilde{\Delta}}{\tilde{\omega}_n}, \quad (18)$$

$$\tilde{\Delta} = \Delta \left[1 + \frac{1}{2\tau_n |\omega_n|} \right], \quad \tilde{\omega}_n = \omega_n \left[1 + \frac{1}{2\tau_n |\omega_n|} \right], \quad (19)$$

where τ_n is the lifetime of an electron due to scatterings by nonmagnetic impurities. The relation $F_{\text{nm}} = F_0$ holds true because the renormalization factor in the numerator of F_{nm} cancels that in the denominator. As a result, the transition temperature does not change in the presence of nonmagnetic impurities. For magnetic impurities, however, we find within

the self-consistent Born approximation that

$$F = F_m = \frac{\tilde{\Delta}}{\tilde{\omega}_n} = \frac{\Delta}{|\omega_n| + 1/\tau_m}, \quad (20)$$

where τ_m is the lifetime of an electron due to scatterings by magnetic impurities. In Table I, we summarize symmetries broken by the self-energy due to magnetic impurities. Thus translational symmetry, local inversion symmetry, and spin-rotation symmetry are restored after averaging. The renormalization factor of ω_n and that of Δ can be different from each other because the magnetic moments of impurities break time-reversal symmetry,

$$\hat{\sigma}_2 \mathbf{V} \cdot \hat{\sigma}^* \hat{\sigma}_2 = -\mathbf{V} \cdot \hat{\sigma}. \quad (21)$$

The negative sign on the right-hand side is the source of $1/\tau_m$ in Eq. (20) that explains the suppression of T_c . Indeed, the transition temperature is estimated as

$$\ln \left(\frac{T_c}{T_0} \right) \approx \psi \left(\frac{1}{2} \right) - \psi \left(\frac{1}{2} + \frac{\xi_0 T_0}{\ell_m T_c} \right), \quad (22)$$

$$\begin{aligned} & \psi \left(\frac{1}{2} \right) - \psi \left(\frac{1}{2} + \frac{x}{2} \right) \\ &= \sum_{n=0}^{\infty} \frac{2}{2n+1+x} - \sum_{n=0}^{\infty} \frac{2}{2n+1}, \end{aligned} \quad (23)$$

where T_0 is the transition temperature in the clean limit, $\ell_m = v_F \tau_m$ is the mean-free path of an electron due to scatterings by magnetic impurities, and $\psi(x)$ is the digamma function. As shown with a broken line in Fig. 4, T_c decreases rapidly with the increase of ξ_0/ℓ_m . We note that neither spin-triplet pairing correlations nor odd-frequency pairing correlations are considered on the way to Eq. (22).

Secondly, we discuss how odd-frequency pairs affect the transition temperature. To do this, we derive the linearized Eilenberger equations, which are displayed in Eqs. (C17) and (C18). The gap equation in the linearized regime is given in Eq. (C19). We consider a pair of the classical trajectories: one is along $\hat{\mathbf{k}}$ and the other is along $-\hat{\mathbf{k}}$. As a result, we obtain the following equations, which relate the four pairing correlations belonging to different symmetry classes:

$$v_F \hat{\mathbf{k}} \cdot \nabla S_- + 2\omega_n S_+ - 2i\mathbf{T}_+ \cdot \mathbf{V} - 2\text{sgn}(\omega_n) \Delta = 0, \quad (24)$$

$$v_F \hat{\mathbf{k}} \cdot \nabla \mathbf{T}_- + 2\omega_n \mathbf{T}_+ - 2iS_+ \mathbf{V} = \mathbf{0}, \quad (25)$$

$$v_F \hat{\mathbf{k}} \cdot \nabla S_+ + 2\omega_n S_- - 2i\mathbf{T}_- \cdot \mathbf{V} = \mathbf{0}, \quad (26)$$

$$v_F \hat{\mathbf{k}} \cdot \nabla \mathbf{T}_+ + 2\omega_n \mathbf{T}_- - 2iS_- \mathbf{V} = \mathbf{0}, \quad (27)$$

$$S_{\pm}(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) = a_0(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \pm a_0(\mathbf{r}, -\hat{\mathbf{k}}, \omega_n), \quad (28)$$

$$\mathbf{T}_{\pm}(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) = \mathbf{a}(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \pm \mathbf{a}(\mathbf{r}, -\hat{\mathbf{k}}, \omega_n). \quad (29)$$

Riccati's parameter S_+ (S_-) represents the spin-singlet even-parity (odd-parity) pairing correlation, and \mathbf{T}_+ (\mathbf{T}_-) represents the spin-triplet even-parity (odd-parity) pairing correlation. Equation (24) describes the relation among the three spin-singlet even-parity pairing correlations and the pair potential. The spatial gradient of the odd-parity correlation S_- generates the even-parity component, which is a result of

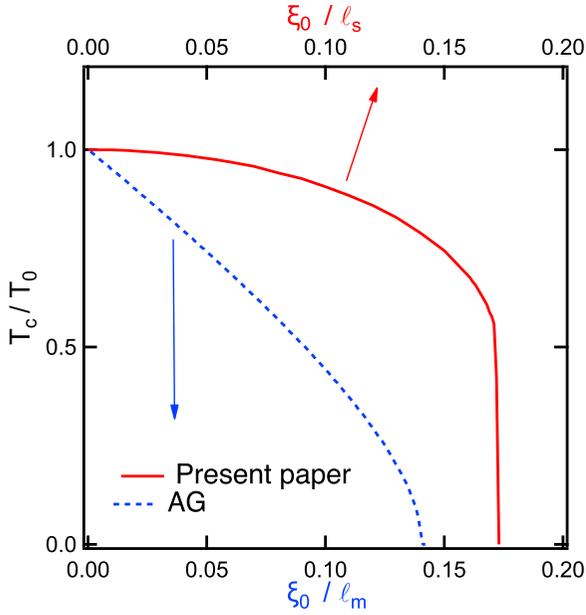


FIG. 4. The theoretical results of the transition temperature are plotted as a function of the inverse of the mean-free path. The broken line is the result calculated from the impurity self-energy within the self-consistent Born approximation, where we use Eq. (20). The solid line is the result of this paper, where we use Eq. (32). It is impossible to compare T_c in the two results because the horizontal lines are defined in different ways. In Eq. (20), $\ell_m = v_F \tau_m$ is the mean-free path of an electron on the Fermi level. In Eq. (32), on the other hand, $\ell_s = \tau_s v_F$ can be interpreted as the mean free path of a spin-singlet Cooper pair.

breaking local inversion symmetry. For simplicity, we neglect the effects of breaking local inversion symmetry and delete the gradient terms in real space in Eqs. (24)–(27). In this approximation, we implicitly consider the homogeneous correlation functions after averaging over the position of magnetic impurities. The correlation functions under the approximation recover both translational symmetry and local inversion symmetry.

In the absence of gradient terms in real space, $S_- = T_- = 0$ is a solution of Eqs. (26) and (27). The odd-frequency correlation T_+ contributes to the spin-singlet pairing correlation as a result of breaking spin-rotation symmetry by magnetic impurities. In what follows, we analyze the two remaining equations, Eqs. (24) and (25), in the absence of gradient terms. Equation (25) implies that the magnetic moment generates the odd-frequency spin-triplet pairing correlation T_+ from the spin-singlet even-parity correlation S_+ in the absence of spin-rotation symmetry. The Matsubara frequency ω_n in the second term enables the conversion from the odd-frequency correlation T_+ to the even-frequency correlation S_+ . As a result of the conversion, the free-energy density at a magnetic impurity increases above zero, as shown in Fig. 1. The free energy averaged over a whole superconductor increases and the transition temperature decreases with the increase of the magnetic impurity concentration. The superconducting state disappears when the averaged free energy becomes zero. By eliminating the odd-frequency pairing correlation T_+ at Eqs. (24) and (25), we reach an equation only for the

spin-singlet even-parity component,

$$\omega_n^2 S_+ + \mathbf{V} \cdot \mathbf{V} S_+ = \Delta |\omega_n|. \quad (30)$$

We assume the properties of a random potential,

$$\overline{\mathbf{V}(\mathbf{r})} = 0, \quad \overline{\mathbf{V}(\mathbf{r})\mathbf{V}(\mathbf{r})} = \frac{1}{\tau_s^2}, \quad (31)$$

under ensemble-averaging, where $1/\tau_s$ can be interpreted as the *lifetime of a spin-singlet Cooper pair* in the presence of magnetic impurities. This can be confirmed by changing $i\omega_n \rightarrow -\partial_\tau \rightarrow -i\partial_t$ in Eq. (30). We find that τ_s gives the characteristic timescale of the equation. We finally reach a solution of

$$S_+ = \frac{\Delta |\omega_n|}{\omega_n^2 + 1/\tau_s^2}. \quad (32)$$

The scatterings by magnetic impurities remove the singularity at $\omega_n = 0$ at the denominator. This explains the decrease of T_c when we substitute $F = S_+$ into Eq. (17). In Fig. 4, we show T_c calculated by using Eq. (32) with a solid line, where the horizontal axis is ξ_0/ℓ_s , with $\ell_s = \tau_s v_F$ meaning the mean-free path of a spin-singlet s -wave Cooper pair under magnetic impurities. The calculated results show that T_c decreases with the increase of scatterings by magnetic impurities. This phenomenon can be understood from two different viewpoints because magnetic impurities simultaneously generate odd-frequency Cooper pairs and subgap quasiparticles. The viewpoint from a Cooper pair shows that the odd-frequency pair increases the free energy locally. The viewpoint from a quasiparticle suggests that the occupation of the YSR states below the Fermi level reduces the condensation energy. We conclude that these two facts make the superconducting state unstable and decrease T_c .

V. CONCLUSION

We have studied the properties of a superconducting state around a magnetic impurity embedded in a conventional superconductor. The analytical results of the anomalous Green's function show that the magnetic impurity converts a spin-singlet s -wave Cooper pair into odd-frequency Cooper pairs. Comparing the normal and the anomalous Green's function explains the coexistence of odd-frequency Cooper pairs and quasiparticles at the Yu-Shiba-Rusinov (YSR) states. We conclude that the formation of the YSR states below the gap is a direct consequence of the appearance of an odd-frequency Cooper pair.

The numerical results of the free-energy density show that the superconducting states around a magnetic impurity are thermodynamically unstable because of the paramagnetic property of odd-frequency Cooper pairs. This fact explains naturally the remaining open issues listed in the Introduction. The sign of the pair potential changes around an impurity with a sufficiently large magnetic moment because odd-frequency pairs are dominant around such a strong magnetic impurity. On the basis of the obtained results, we also proposed an alternative scenario to explain the suppression of the transition temperature in the presence of many magnetic impurities.

ACKNOWLEDGMENTS

The authors are grateful to A. A. Golubov, Y. Tanaka, Ya. V. Fominov, and S. Hoshino for useful discussion. This work was supported by JSPS KAKENHI (No. JP20H01857) and JSPS Core-to-Core Program (No. JPJSCCA20170002). S.-I.S. is supported by a Grant-in-Aid for JSPS Fellows (JSPS KAKENHI Grant No. JP19J02005) and by Overseas Research Fellowships by JSPS. S.-I.S. acknowledges the hospitality at the University of Twente. T.S. is supported in part by the establishment of university fellowships towards the creation of science technology innovation from the Ministry of Education, Culture, Sports, Science, and Technology (MEXT) of Japan.

APPENDIX A: PARAMAGNETIC COOPER PAIRS

The superconducting condensate can be described phenomenologically by the macroscopic wave function

$$\psi(\mathbf{r}) = \sqrt{n_S(\mathbf{r})} e^{i\theta(\mathbf{r})}, \quad (\text{A1})$$

where n_S is the density of Cooper pairs and θ is the phase of the condensate. The flux quantization is derived from the single-valuedness of this wave function. The Josephson effect is explained as the tunnel effect between two superconductors characterized by such wave functions. The energy of the condensate can be calculated in terms of the macroscopic wave function,

$$E = \int d\mathbf{r} \frac{\hbar^2}{2m} \left\{ \left(\nabla + i \frac{e}{\hbar c} \mathbf{A} \right) \psi^\dagger(\mathbf{r}) \right\} \left\{ \left(\nabla - i \frac{e}{\hbar c} \mathbf{A} \right) \psi(\mathbf{r}) \right\}, \quad (\text{A2})$$

$$= \int d\mathbf{r} \frac{\hbar^2}{2m} \left\{ \frac{(\nabla n_S)^2}{4n_S} + n_S \left(\nabla \theta - \frac{e}{\hbar c} \mathbf{A} \right)^2 \right\}. \quad (\text{A3})$$

The first term in Eq. (A3) represents the kinetic energy of the condensate, and the second term means the elastic energy of the superconducting phase. Since $n_S > 0$, both the spatial gradient of the density and the spatial gradient of the phase increase the energy of the condensate, which describes the rigidity of the superconducting state. Therefore, both the pair density and the phase are uniform at the ground state in the absence of a magnetic field. The electric current can be described by

$$\mathbf{j} = \frac{e\hbar}{2im} \left[\psi^\dagger(\mathbf{r}) \left(\nabla - i \frac{e}{\hbar c} \mathbf{A} \right) \psi(\mathbf{r}) - \left(\nabla + i \frac{e}{\hbar c} \mathbf{A} \right) \psi^\dagger(\mathbf{r}) \psi(\mathbf{r}) \right] \\ = \frac{e\hbar n_S}{m} \nabla \theta - \frac{n_S e^2}{mc} \mathbf{A}. \quad (\text{A4})$$

Together with the Maxwell equation $\nabla \times \mathbf{H} = \frac{4\pi}{c} \mathbf{j}$, we obtain the equation for a magnetic field in a superconductor,

$$\nabla^2 \mathbf{H} - \frac{4\pi n_S e^2}{m c^2} \mathbf{H} = \mathbf{0}. \quad (\text{A5})$$

London's length $\lambda_L = \sqrt{m c^2 / 4\pi n_S e^2}$ characterizes the spatial variation of a magnetic field. Equation (A5) represents the Meissner screening effect of a magnetic field. The dumping of a magnetic field into a superconductor is described by the

negative sign at the second term on the last line in Eq. (A4). The argument above is valid when the pair density n_S is positive everywhere in a superconductor.

Let us assume that the pair density is negative locally at a finite area around $\mathbf{r} = \mathbf{r}_0$, and let us discuss the physical consequence of $n_S(\mathbf{r}_0) < 0$. The second term in Eq. (A3) suggests that a large gradient of the phase and the penetration of a magnetic field are necessary to decrease the energy of the condensate. Namely, the condensate with the “negative pair density” is paramagnetic. Equation (A5) with negative n_S suggests also that a magnetic field can penetrate into such a paramagnetic superconductor [40,41]. Such a local area around \mathbf{r}_0 may no longer be superconductive because the phase θ fluctuates easily from a constant value. Thus the pair density n_S must be positive to realize the stable homogeneous superconducting ground state both electromagnetically and thermodynamically. However, the “pair density” can be negative locally in the presence of an odd-frequency pair.

The surface of a superconductor breaks inversion symmetry locally. As a result of breaking inversion symmetry, odd-parity (even-parity) pairing correlations appear at the surface of an even-parity (odd-parity) superconductor. Such induced pairing correlations belong to an odd-frequency symmetry class because the surface does not change the spin of a Cooper pair. In what follows, we demonstrate that the pair density can be negative at such a surface by using an analytical solution of the Eilenberger equation,

$$\hbar v_F \hat{\mathbf{k}} \cdot \nabla \hat{g} + [H, \hat{g}] = \mathbf{0}, \quad (\text{A6})$$

$$H = \begin{bmatrix} \omega_n & \Delta(\mathbf{r}, \hat{\mathbf{k}}) \\ -s_s \Delta(\mathbf{r}, \hat{\mathbf{k}}) & -\omega_n \end{bmatrix}, \quad \hat{g}(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \\ = \begin{bmatrix} g(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) & f(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \\ -s_s f(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) & -g(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \end{bmatrix}. \quad (\text{A7})$$

Here we have reduced to 2×2 particle-hole space by extracting one spin sector of the Bogoliubov–de Gennes (BdG) Hamiltonian. The pair potential obeys the symmetry relation

$$\Delta(\mathbf{r}, -\hat{\mathbf{k}}) = \begin{cases} \Delta(\mathbf{r}, \hat{\mathbf{k}}) & \text{singlet } s_s = -1, \\ -\Delta(\mathbf{r}, \hat{\mathbf{k}}) & \text{triplet } s_s = 1, \end{cases} \quad (\text{A8})$$

which is derived from the Fermi-Dirac statistics of electrons. The Eilenberger equation can be decomposed into three equations [47],

$$v_F \hat{\mathbf{k}} \cdot \nabla g = 2\Delta f_S, \quad v_F \hat{\mathbf{k}} \cdot \nabla f_B = -2\omega_n f_S, \\ v_F \hat{\mathbf{k}} \cdot \nabla f_S = 2(\Delta g - \omega_n f_B), \quad (\text{A9})$$

with

$$f_B = \frac{1}{2}(f - s_s f), \quad f_S = \frac{1}{2}(f + s_s f). \quad (\text{A10})$$

The quasiclassical Green's functions satisfy the normalization condition

$$g^2 - s_s f f = g^2 + f_B^2 - f_S^2 = 1. \quad (\text{A11})$$

In a homogeneous superconductor, we obtain the solution as

$$g = \frac{\omega_n}{\Omega}, \quad f_B = \frac{\Delta(\hat{\mathbf{k}})}{\Omega}, \quad f_S = 0, \quad \Omega = \sqrt{\omega_n^2 + \Delta^2(\hat{\mathbf{k}})}. \quad (\text{A12})$$

Thus f_B is interpreted as a bulk component of pairing correlation, which contributes to the pair potential through the gap equation

$$\Delta(\mathbf{r}, \hat{\mathbf{k}}) = T \sum_{\omega_n} \int \frac{d\hat{\mathbf{k}}'}{S_d} \lambda(\hat{\mathbf{k}}, \hat{\mathbf{k}}') f(\mathbf{r}, \hat{\mathbf{k}}', \omega_n), \quad (\text{A13})$$

where λ represents an attractive interaction between two electrons. The second equation in Eqs. (A9) represents the symmetry relationship between f_B and f_S . Since $\hat{\mathbf{k}}$ is an odd-parity function and ω_n is an odd in Matsubara frequency, f_S belongs to the opposite parity and opposite frequency symmetry class to f_B . Therefore, f_S is considered as an induced pairing component due to the spatial gradient of f_B . Although the anomalous Green's function f in Eq. (A13) consists of both f_B and f_S , only the bulk component f_B contributes to the pair potential. Since f_S is an odd function of ω_n , the summation of f_S over ω_n vanishes. The Meissner kernel for the quasiclassical Green's function is described as [48]

$$j_\mu = -\frac{2ne^2}{mc} \mathcal{Q}_{\mu,\nu} A_\nu, \quad (\text{A14})$$

$$\begin{aligned} \mathcal{Q}_{\mu,\nu} &= d\pi T \sum_{\omega_n} \int \frac{d\hat{\mathbf{k}}}{S_d} \hat{k}_\mu \hat{k}_\nu \partial_{\omega_n} g(\mathbf{r}, \hat{\mathbf{k}}, \omega_n) \\ &= d\pi T \sum_{\omega_n > 0} \int \frac{d\hat{\mathbf{k}}}{S_d} \hat{k}_\mu \hat{k}_\nu (f_B^2 - f_S^2) \partial_{\omega_n} \log \frac{1+g}{1-g}. \end{aligned} \quad (\text{A15})$$

The last expression suggests that the odd-frequency pairing correlation decreases $\mathcal{Q}_{\mu,\nu}$. By putting the results in Eq. (A12) for a spin-singlet s -wave superconductor into \mathcal{Q} , it is possible to recover the results of [49]

$$\mathcal{Q}_{\mu,\nu} = \pi T \sum_{\omega_n} \frac{\Delta^2}{(\omega_n^2 + \Delta^2)^{3/2}} \delta_{\mu,\nu}. \quad (\text{A16})$$

The product of $n \mathcal{Q}_{\mu,\mu}$ is often referred to as pair density.

As an example of inhomogeneous superconducting states, we consider the condensate near the surface of a two-dimensional p -wave superconductor. The pair potential is described as

$$\begin{aligned} \Delta(x) &= \Delta \cos \theta \tanh\left(\frac{x}{\xi_0}\right), \quad \hat{k}_x = \cos \theta, \\ \hat{k}_y &= \sin \theta, \quad \xi_0 = \frac{v_F}{\Delta \cos \theta}, \end{aligned} \quad (\text{A17})$$

where we assume that a surface is at $x = 0$ and a p -wave superconductor occupies $x > 0$, the superconducting state is uniform in the y direction, and ξ_0 is the coherence length. The

solution of Eq. (A9) can be obtained as [50]

$$\begin{aligned} g(x, \theta, \omega_n) &= \frac{\omega_n}{\Omega_\theta} + \frac{\Delta^2 \cos^2 \theta}{2\omega_n \Omega_\theta} \cosh^{-2}\left(\frac{x}{\xi_0}\right), \\ f_B(x, \theta, \omega_n) &= \frac{\Delta \cos \theta}{\Omega_\theta} \tanh\left(\frac{x}{\xi_0}\right), \\ f_S(x, \theta, \omega_n) &= -\frac{\Delta^2 \cos^2 \theta}{2\omega_n \Omega_\theta} \cosh^{-2}\left(\frac{x}{\xi_0}\right), \\ \Omega_\theta &= \sqrt{\omega_n^2 + \Delta^2 \cos^2 \theta}. \end{aligned} \quad (\text{A18})$$

The bulk component $f_B(x, \theta + \pi, \omega_n) = -f_B(x, \theta, \omega_n)$ is odd-parity, whereas the surface component f_S is even-parity because of $\cos^2(\theta + \pi) = \cos^2 \theta$. The gap equation in Eq. (A13) is described as

$$\begin{aligned} \Delta(x) &= T \sum_{\omega_n} \int_0^{2\pi} \frac{d\theta'}{2\pi} (2\lambda \cos \theta \cos \theta') \\ &\quad \times [f_B(x, \theta', \omega_n) + f_S(x, \theta', \omega_n)], \end{aligned} \quad (\text{A20})$$

$$= \Delta \cos \theta \tanh\left(\frac{x}{\xi_0}\right) \lambda T \sum_{\omega_n} \frac{1}{\sqrt{\omega_n^2 + \Delta^2}}. \quad (\text{A21})$$

On the way to the second line, we approximately neglect the θ dependence of Ω_θ and that of ξ_0 in f_B . The amplitude of f_S increases with the decrease of ω_n at its denominator and can be larger than the amplitude of f_B for $\omega_n \ll \Delta$. The resulting response kernel,

$$\begin{aligned} \mathcal{Q}_{\mu,\nu} &\approx \delta_{\mu,\nu} \pi T \sum_{\omega_n} \int_0^{2\pi} \frac{d\theta}{2\pi} \frac{\Delta^2 \cos^2 \theta}{(\omega_n^2 + \Delta^2 \cos^2 \theta)^{3/2}} \\ &\quad \times \left[1 - \frac{\Delta^2 \cos^2 \theta}{2\omega_n^2} \cosh^{-2}\left(\frac{x}{\xi_0}\right) \right], \end{aligned} \quad (\text{A22})$$

can be negative for a low temperature $T \ll T_c$ near the surface $0 < x < \xi_0$. The paramagnetic response at the surface of an unconventional superconductor was pointed out for a d -wave superconductor [51,52]. To make clear the details of the paramagnetic effect theoretically, analysis beyond the linear response is necessary. In Refs. [42,53], the pair potential and a magnetic field are determined self-consistently with each other in a small unconventional superconductor. A small p -wave superconducting disk shows a paramagnetic response to a magnetic field at low temperature. Even-frequency pairs stabilize p -wave superconductivity in the bulk, and odd-frequency pairs exhibit the paramagnetic response at the surface.

Finally, we briefly explain the coexistence of an odd-frequency pair and a quasiparticle at the Andreev bound state at a surface. After applying $i\omega_n \rightarrow \epsilon + i\delta$, the local density of states for $|\epsilon| < \Delta$ calculated from the second term of the normal Green's function becomes

$$\begin{aligned} \frac{N(x, \epsilon)}{N_0} &= \text{Re} \int \frac{d\theta}{2\pi} i \frac{\Delta^2 \cos^2 \theta}{2(\epsilon + i\delta) \sqrt{\Delta^2 \cos^2 \theta - \epsilon^2}} \\ &\quad \times \cosh^{-2}\left(\frac{x}{\xi_0}\right) \rightarrow \delta(\epsilon) \frac{\Delta}{\pi} \cosh^{-2}\left(\frac{x}{\xi_0}\right). \end{aligned} \quad (\text{A23})$$

The peak of the local density of states at zero energy reflects the existence of a quasiparticle at the surface Andreev bound state.

APPENDIX B: LIPPMANN-SCHWINGER EQUATION

The Lippmann-Schwinger equation relates the Green's function in the presence of perturbations \check{V} to the Green's function in the absence of perturbation as

$$\check{G}(\mathbf{r}, \mathbf{r}') = \check{G}^{(0)}(\mathbf{r}, \mathbf{r}') + \int d\mathbf{r}_1 \check{G}^{(0)}(\mathbf{r}, \mathbf{r}_1) \check{V}(\mathbf{r}_1) \check{G}(\mathbf{r}_1, \mathbf{r}'). \quad (\text{B1})$$

When we consider an impurity potential $\check{V}(\mathbf{r}) = \check{V}\delta(\mathbf{r})$, the equation becomes

$$\check{G}(\mathbf{r}, \mathbf{r}') = \check{G}^{(0)}(\mathbf{r}, \mathbf{r}') + \check{G}^{(0)}(\mathbf{r}, 0) \check{V} \check{G}(0, \mathbf{r}'). \quad (\text{B2})$$

By putting $\mathbf{r} = 0$ into the equation, the equation

$$\check{G}(0, \mathbf{r}') = \check{G}^{(0)}(0, \mathbf{r}') + \check{G}^{(0)}(0, 0) \check{V} \check{G}(0, \mathbf{r}') \quad (\text{B3})$$

has a closed form. Substituting the solution

$$\check{G}(0, \mathbf{r}') = [1 - \check{G}^{(0)}(0, 0) \check{V}]^{-1} \check{G}^{(0)}(0, \mathbf{r}') \quad (\text{B4})$$

into Eq. (B2), we obtain

$$\check{G}(\mathbf{r}, \mathbf{r}') = \check{G}^{(0)}(\mathbf{r}, \mathbf{r}') + \check{G}^{(0)}(\mathbf{r}, 0) \check{V} \times [1 - \check{G}^{(0)}(0, 0) \check{V}]^{-1} \check{G}^{(0)}(0, \mathbf{r}'). \quad (\text{B5})$$

In this paper, we consider a spin-singlet s -wave superconductor in one dimension as described by Eq. (1). The unperturbed Green's function in the Matsubara representation is given by

$$\check{G}^{(0)}(x, x') = -\frac{\pi N_0}{\Omega} \check{U}^\dagger \begin{bmatrix} i\omega_n C_0 - \Omega S_0 & \Delta C_0 \\ \Delta C_0 & i\omega_n C_0 + \Omega S_0 \end{bmatrix} \times e^{-|x-x'|/\xi_0} \check{U}, \quad (\text{B6})$$

with

$$\Omega = \sqrt{\omega_n^2 + \Delta^2}, \quad k_\pm = k \left(1 \pm i \frac{\Omega}{2\epsilon_F} \right), \quad \check{U} = \begin{bmatrix} 1 & 0 \\ 0 & i\hat{\sigma}_2 e^{i\varphi} \end{bmatrix}, \quad (\text{B7})$$

$$C_0 = \cos(k|x-x'|), \quad S_0 = \sin(k|x-x'|), \quad \xi_0 = \frac{2\epsilon_F}{\Omega k_F}, \quad (\text{B8})$$

where $\hat{\sigma}_j$ for $j = 1-3$ is the Pauli matrix in spin space, and k denotes the Fermi wave number.

The potential of a nonmagnetic impurity is described by

$$\check{V} = \begin{bmatrix} V_0 \hat{\sigma}_0 & 0 \\ 0 & -V_0 \hat{\sigma}_0 \end{bmatrix} = V_0 \hat{\tau}_3, \quad (\text{B9})$$

where $\hat{\tau}_j$ for $j = 1-3$ is the Pauli matrix in particle-hole space. The Green's function in the presence of a nonmagnetic impurity is calculated as

$$\check{G}(x, x') = \check{G}^{(0)}(x, x') - \frac{\pi N_0}{\Omega} e^{-(|x|+|x'|)/\xi_0} \frac{\gamma_0}{(1 + \gamma_0^2)} \times \check{U}^\dagger \begin{bmatrix} i\omega(S_+ - \gamma_0 C_+) + \Omega(C_+ + \gamma_0 S_+) & \Delta(S_+ - \gamma_0 C_+) \\ \Delta(S_+ - \gamma_0 C_+) & i\omega(S_+ - \gamma_0 C_+) - \Omega(C_+ + \gamma_0 S_+) \end{bmatrix} \check{U}, \quad (\text{B10})$$

$$C_\pm = \cos\{k(|x| \pm |x'|)\}, \quad S_\pm = \sin\{k(|x| \pm |x'|)\}, \quad \gamma_0 = \pi N_0 V_0. \quad (\text{B11})$$

The anomalous Green's function results in

$$\hat{f}(x, x') = -\frac{\pi N_0 \Delta}{\Omega} i\hat{\sigma}_2 \left[C_0 e^{-|x-x'|/\xi_0} + \frac{\gamma_0}{1 + \gamma_0^2} (S_+ - \gamma_0 C_+) e^{-(|x|+|x'|)/\xi_0} \right]. \quad (\text{B12})$$

The anomalous Green's function $\hat{f}(x, x')$ consists only of a spin-singlet even-parity Cooper pair because it remains unchanged under $x \leftrightarrow x'$. The normal Green's function becomes

$$\text{Tr}[\check{G}_\epsilon^R(x, x)] = \frac{-4\pi i N_0 \epsilon}{\sqrt{\epsilon^2 - \Delta^2}} \left[1 + \frac{\gamma_0}{1 + \gamma_0^2} (\sin 2k|x| - \gamma_0 \cos 2k|x|) e^{-2|x|/\xi_0} \right], \quad (\text{B13})$$

which is always a real value for $\epsilon < \Delta$.

In the presence of a magnetic impurity, the normal Green's function is calculated to be

$$\hat{g}(x, x') = \frac{\pi N_0}{\Omega} \left[-e^{-|x-x'|/\xi_0} (i\omega_n C_0 - \Omega S_0) - \frac{e^{-(|x|+|x'|)/\xi_0}}{Z} |\boldsymbol{\gamma}|^2 [2i\omega_n \Delta^2 C_- + \{\Delta^2(1 - |\boldsymbol{\gamma}|^2) - \omega_n^2(1 + |\boldsymbol{\gamma}|^2)\} (i\omega_n C_+ - \Omega S_+)] + \frac{e^{-(|x|+|x'|)/\xi_0}}{Z} \boldsymbol{\gamma} \cdot \hat{\boldsymbol{\sigma}} \Omega \{\Delta^2(1 - |\boldsymbol{\gamma}|^2) C_- + i\omega_n (i\omega_n C_+ - \Omega S_+) (1 + |\boldsymbol{\gamma}|^2)\} \right], \quad (\text{B14})$$

$$Z = \Delta^2(1 - |\boldsymbol{\gamma}|^2)^2 + \omega_n^2(1 + |\boldsymbol{\gamma}|^2)^2, \quad \boldsymbol{\gamma} = \pi N_0 V. \quad (\text{B15})$$

where S_\pm and C_\pm are given in Eq. (B11). The anomalous Green's function is displayed in Eq. (9).

APPENDIX C: EILENBERGER EQUATION

To study the pairing correlations around a magnetic impurity, we solve the Eilenberger equation numerically. The Matsubara Green function can be decomposed into the Riccati parameters as

$$\check{G}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = \begin{pmatrix} \hat{G} & \hat{F} \\ \hat{F} & -\hat{G} \end{pmatrix} = \begin{pmatrix} \hat{N} & \hat{0} \\ \hat{0} & \hat{N} \end{pmatrix} \begin{pmatrix} \text{sgn}(\omega_n)(1 - \hat{a}\hat{a}) & 2\hat{a} \\ 2\hat{a} & -\text{sgn}(\omega_n)(1 - \hat{a}\hat{a}) \end{pmatrix}, \quad (\text{C1})$$

$$\hat{a} = \hat{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n), \quad \hat{a} = \hat{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n), \quad (\text{C2})$$

$$\hat{N} = (1 + \hat{a}\hat{a})^{-1}, \quad \hat{N} = (1 + \hat{a}\hat{a})^{-1}. \quad (\text{C3})$$

The Riccati parameters can be decomposed into four components as

$$\hat{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = a_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) + \mathbf{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) \cdot \hat{\sigma}, \quad (\text{C4})$$

where a_0 is the spin-singlet component, and a_j for $j = 1-3$ are three spin-triplet components. They obey the symmetry relations

$$a_0(\mathbf{r}, -\hat{\mathbf{k}}, -i\omega_n) = a_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n), \quad \mathbf{a}(\mathbf{r}, -\hat{\mathbf{k}}, -i\omega_n) = -\mathbf{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n). \quad (\text{C5})$$

The spin-singlet component a_0 is either the even-parity even-frequency symmetry or the odd-parity odd-frequency one. The three spin-triplet components \mathbf{a} are either the odd-parity even-frequency symmetry or the even-parity odd-frequency one. The Riccati parameter \hat{a} in Eq. (C2) obeys the Eilenberger equation,

$$i\hbar v_F \hat{\mathbf{k}} \cdot \nabla \hat{a} + 2i\omega_n \hat{a} + \mathbf{V}(\mathbf{r}) \cdot \hat{\sigma} \hat{a} + \hat{a} \mathbf{V}(\mathbf{r}) \cdot \hat{\sigma} - i \text{sgn}(\omega_n) \Delta(\mathbf{r}) + i \text{sgn}(\omega_n) \hat{a} \Delta(\mathbf{r}) \hat{a} = 0, \quad (\text{C6})$$

$$i\hbar v_F \hat{\mathbf{k}} \cdot \nabla \hat{a} - 2i\omega_n \hat{a} - \mathbf{V}(\mathbf{r}) \cdot \hat{\sigma} \hat{a} - \hat{a} \mathbf{V}(\mathbf{r}) \cdot \hat{\sigma} + i \text{sgn}(\omega_n) \Delta(\mathbf{r}) - i \text{sgn}(\omega_n) \hat{a} \Delta(\mathbf{r}) \hat{a} = 0. \quad (\text{C7})$$

The equation

$$\underline{X}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = \hat{\sigma}_2 \underline{X}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) \hat{\sigma}_2 = \hat{\sigma}_2 X^*(\mathbf{r}, -\hat{\mathbf{k}}, i\omega_n) \hat{\sigma}_2 \quad (\text{C8})$$

defines the relation among X , \underline{X} , and \underline{X} .

The anomalous Green's function is represented by

$$\hat{F}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = 2\hat{N}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) \hat{a}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = \mathcal{F}_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) + \mathcal{F}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) \cdot \hat{\sigma}, \quad (\text{C9})$$

$$\mathcal{F}_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = \frac{2}{Z_N} [a_0 + (a_0^2 - \mathbf{a}^2) \underline{a}_0]_{(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n)}, \quad (\text{C10})$$

$$\mathcal{F}(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) = \frac{2}{Z_N} [\mathbf{a} + (a_0^2 - \mathbf{a}^2) \underline{\mathbf{a}}]_{(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n)}, \quad (\text{C11})$$

$$Z_N = 1 + (a_0^2 - \mathbf{a} \cdot \mathbf{a})(\underline{a}_0^2 - \underline{\mathbf{a}} \cdot \underline{\mathbf{a}}) + 2(a_0 \underline{a}_0 - \mathbf{a} \cdot \underline{\mathbf{a}}). \quad (\text{C12})$$

The pair potential for spin-singlet s -wave symmetry is calculated self-consistently by using the gap equation,

$$\Delta(\mathbf{r}) = \pi N_0 g \int \frac{d\hat{\mathbf{k}}}{S_d} T \sum_{\omega_n} \mathcal{F}_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n), \quad (\text{C13})$$

where s_d is the solid angle in d -dimension and g is the coupling constant. The Riccati parameters in the real energy representation $i\omega_n \rightarrow \epsilon + i\delta$ enable us to calculate the local density of states

$$N(\mathbf{r}, \epsilon) = N_0 \text{Re} \int \frac{d\hat{\mathbf{k}}}{S_d} [2\mathcal{N}_0(\mathbf{r}, \hat{\mathbf{k}}, \epsilon) - 1], \quad \mathcal{N}_0 = \frac{1}{Z_N} (1 + a_0 \underline{a}_0 - \mathbf{a} \cdot \underline{\mathbf{a}}), \quad (\text{C14})$$

where \mathcal{N}_0 is the spin-singlet component of \hat{N} in Eq. (C3). The condensation energy of the superconducting states can be represented as [54]

$$F_S - F_N = \int d\mathbf{r} f_{\text{SN}}(\mathbf{r}), \quad (\text{C15})$$

$$f_{\text{SN}}(\mathbf{r}) = \pi N_0 \int \frac{d\hat{\mathbf{k}}}{S_d} \left[T \sum_{\omega_n} \Delta^*(\mathbf{r}) \mathcal{F}_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) + 8T \sum_{\omega_n > 0} \int_{\omega_n}^{\infty} d\omega \text{Re} [\mathcal{N}_0(\mathbf{r}, \hat{\mathbf{k}}, i\omega) - 1] \right]. \quad (\text{C16})$$

The first term is derived from the constant term in the mean-field Hamiltonian. Although the second term is calculated from the normal Green's function, a Cooper pair affects the condensation energy through the normalization of the Green's function (i.e., $\hat{G}^2 + \hat{F}\hat{F} = \hat{1}$).

To discuss the suppression of T_c due to odd-frequency Cooper pairs, we analyze the linearized Eilenberger equation. By deleting the last term in Eq. (C6), we obtain

$$(v_F \hat{\mathbf{k}} \cdot \nabla + 2\omega_n) a_0 - 2i\mathbf{a} \cdot \mathbf{V}(\mathbf{r}) - \text{sgn}(\omega_n) \Delta(\mathbf{r}) = 0, \quad (\text{C17})$$

$$(v_F \hat{\mathbf{k}} \cdot \nabla + 2\omega_n) \mathbf{a} - 2ia_0 \mathbf{V}(\mathbf{r}) = 0. \quad (\text{C18})$$

The first (second) equation corresponds to the spin-singlet (spin-triplet) part of Eq. (C6). The gap equation in the linear regime is given by

$$\Delta(\mathbf{r}) = \pi g N_0 T \sum_{\omega_n} \int \frac{d\hat{\mathbf{k}}}{S_d} 2a_0(\mathbf{r}, \hat{\mathbf{k}}, \omega_n). \quad (\text{C19})$$

In numerical simulation in this paper, we calculate the Ricatti parameters $a(x, \pm, i\omega_n)$, where $+$ ($-$) indicates the positive (negative) momentum point on the Fermi surface in one dimension. The angle average on the Fermi surface is represented as

$$\int \frac{d\hat{\mathbf{k}}}{S_d} X(\mathbf{r}, \hat{\mathbf{k}}, i\omega_n) \rightarrow \frac{1}{2} \sum_{s=\pm} X(x, s, i\omega_n). \quad (\text{C20})$$

-
- [1] L. Yu, Bound state in superconductors with paramagnetic impurities, *Acta. Phys. Sin* **21**, 75 (1965).
- [2] H. Shiba, Classical spins in superconductors, *Prog. Theor. Phys.* **40**, 435 (1968).
- [3] A. I. Rusinov, Superconductivity near a paramagnetic impurity, *JETP Lett.* **9**, 85 (1969).
- [4] T.-P. Choy, J. M. Edge, A. R. Akhmerov, and C. W. J. Beenakker, Majorana fermions emerging from magnetic nanoparticles on a superconductor without spin-orbit coupling, *Phys. Rev. B* **84**, 195442 (2011).
- [5] J. Klinovaja, P. Stano, A. Yazdani, and D. Loss, Topological Superconductivity and Majorana Fermions in RKKY Systems, *Phys. Rev. Lett.* **111**, 186805 (2013).
- [6] S. Nadj-Perge, I. K. Drozdov, J. Li, H. Chen, S. Jeon, J. Seo, A. H. MacDonald, B. A. Bernevig, and A. Yazdani, Observation of majorana fermions in ferromagnetic atomic chains on a superconductor, *Science* **346**, 602 (2014).
- [7] G. C. Ménard, S. Guissart, C. Brun, S. Pons, V. S. Stolyarov, F. Debontridder, M. V. Leclerc, E. Janod, L. Cario, D. Roditchev, P. Simon, and T. Cren, Coherent long-range magnetic bound states in a superconductor, *Nat. Phys.* **11**, 1013 (2015).
- [8] Z. Schertübl, G. Fülöp, C. P. Moca, J. Gramich, A. Baumgartner, P. Makk, T. Elalaily, C. Schönenberger, J. Nygård, G. Zaránd, and S. Csonka, Large spatial extension of the zero-energy yu–shiba–rusinov state in a magnetic field, *Nat. Commun.* **11**, 1834 (2020).
- [9] H. Ebisu, K. Yada, H. Kasai, and Y. Tanaka, Odd-frequency pairing in topological superconductivity in a one-dimensional magnetic chain, *Phys. Rev. B* **91**, 054518 (2015).
- [10] A. A. Abrikosov and L. P. Gor'kov, Contribution to the theory of superconducting alloys with paramagnetic impurities, *Sov. Phys. JETP* **12**, 1243 (1961).
- [11] K. Maki, in *Superconductivity*, edited by R. D. Parks (Marcel Dekker, New York, 1969) Vol. 2, p. 1035
- [12] M. I. Salkola, A. V. Balatsky, and J. R. Schrieffer, Spectral properties of quasiparticle excitations induced by magnetic moments in superconductors, *Phys. Rev. B* **55**, 12648 (1997).
- [13] M. E. Flatté and J. M. Byers, Local Electronic Structure of a Single Magnetic Impurity in a Superconductor, *Phys. Rev. Lett.* **78**, 3761 (1997).
- [14] T. Meng, J. Klinovaja, S. Hoffman, P. Simon, and D. Loss, Superconducting gap renormalization around two magnetic impurities: From Shiba to Andreev bound states, *Phys. Rev. B* **92**, 064503 (2015).
- [15] K. Björnson, A. V. Balatsky, and A. M. Black-Schaffer, Superconducting order parameter π -phase shift in magnetic impurity wires, *Phys. Rev. B* **95**, 104521 (2017).
- [16] A. V. Balatsky, I. Vekhter, and J.-X. Zhu, Impurity-induced states in conventional and unconventional superconductors, *Rev. Mod. Phys.* **78**, 373 (2006).
- [17] V. L. Berezinskii, New model of the anisotropic phase of superfluid He^3 , *JETP Lett.* **20**, 287 (1974).
- [18] T. R. Kirkpatrick and D. Belitz, Disorder-Induced Triplet Superconductivity, *Phys. Rev. Lett.* **66**, 1533 (1991).
- [19] D. Belitz and T. R. Kirkpatrick, Even-parity spin-triplet superconductivity in disordered electronic systems, *Phys. Rev. B* **46**, 8393 (1992).
- [20] A. Balatsky and E. Abrahams, New class of singlet superconductors which break the time reversal and parity, *Phys. Rev. B* **45**, 13125 (1992).
- [21] E. Abrahams, A. Balatsky, J. R. Schrieffer, and P. B. Allen, Interactions for odd- ω -gap singlet superconductors, *Phys. Rev. B* **47**, 513 (1993).
- [22] P. Coleman, E. Miranda, and A. Tsvelik, Possible realization of odd-frequency pairing in heavy fermion compounds, *Phys. Rev. Lett.* **70**, 2960 (1993).
- [23] E. Abrahams, A. Balatsky, D. J. Scalapino, and J. R. Schrieffer, Properties of odd-gap superconductors, *Phys. Rev. B* **52**, 1271 (1995).
- [24] O. Zachar, S. A. Kivelson, and V. J. Emery, Exact Results for a 1D Kondo Lattice from Bosonization, *Phys. Rev. Lett.* **77**, 1342 (1996).

- [25] M. Vojta and E. Dagotto, Indications of unconventional superconductivity in doped and undoped triangular antiferromagnets, *Phys. Rev. B* **59**, R713(R) (1999).
- [26] Y. V. Fominov, Y. Tanaka, Y. Asano, and M. Eschrig, Odd-frequency superconducting states with different types of Meissner response: Problem of coexistence, *Phys. Rev. B* **91**, 144514 (2015).
- [27] F. S. Bergeret, A. F. Volkov, and K. B. Efetov, Long-Range Proximity Effects in Superconductor-Ferromagnet Structures, *Phys. Rev. Lett.* **86**, 4096 (2001).
- [28] L. J. Buchholtz and G. Zwicknagl, Identification of p -wave superconductors, *Phys. Rev. B* **23**, 5788 (1981).
- [29] J. Hara and K. Nagai, A polar state in a slab as a soluble model of p -wave fermi superfluid in finite geometry, *Prog. Theor. Phys.* **76**, 1237 (1986).
- [30] C.-R. Hu, Midgap Surface States as a Novel Signature for $d_{xa}^2 - x_b^2$ -wave Superconductivity, *Phys. Rev. Lett.* **72**, 1526 (1994).
- [31] Y. Tanaka and S. Kashiwaya, Theory of Tunneling Spectroscopy of d -wave Superconductors, *Phys. Rev. Lett.* **74**, 3451 (1995).
- [32] Y. Tanaka, M. Sato, and N. Nagaosa, Symmetry and topology in superconductors odd-frequency pairing and edge states, *J. Phys. Soc. Jpn.* **81**, 011013 (2012).
- [33] T. Yokoyama, Y. Tanaka, and A. A. Golubov, Theory of pairing symmetry inside the Abrikosov vortex core, *Phys. Rev. B* **78**, 012508 (2008).
- [34] Y. Tanuma, N. Hayashi, Y. Tanaka, and A. A. Golubov, Model for Vortex-core Tunneling Spectroscopy of Chiral p -wave Superconductors via Odd-frequency Pairing States, *Phys. Rev. Lett.* **102**, 117003 (2009).
- [35] Y. Asano and Y. Tanaka, Majorana fermions and odd-frequency cooper pairs in a normal-metal nanowire proximity-coupled to a topological superconductor, *Phys. Rev. B* **87**, 104513 (2013).
- [36] D. F. Agterberg, P. M. R. Brydon, and C. Timm, Bogoliubov Fermi Surfaces in Superconductors with Broken Time-Reversal Symmetry, *Phys. Rev. Lett.* **118**, 127001 (2017).
- [37] D. Kim, S. Kobayashi, and Y. Asano, Quasiparticle on bogoliubov fermi surface and odd-frequency cooper pair, *J. Phys. Soc. Jpn.* **90**, 104708 (2021).
- [38] D. Kuzmanovski, R. S. Souto, and A. V. Balatsky, Odd-frequency superconductivity near a magnetic impurity in a conventional superconductor, *Phys. Rev. B* **101**, 094505 (2020).
- [39] V. Perrin, F. L. N. Santos, G. C. Ménard, C. Brun, T. Cren, M. Civelli, and P. Simon, Unveiling Odd-Frequency Pairing around a Magnetic Impurity in a Superconductor, *Phys. Rev. Lett.* **125**, 117003 (2020).
- [40] Y. Tanaka, Y. Asano, A. A. Golubov, and S. Kashiwaya, Anomalous features of the proximity effect in triplet superconductors, *Phys. Rev. B* **72**, 140503(R) (2005).
- [41] Y. Asano, A. A. Golubov, Y. V. Fominov, and Y. Tanaka, Unconventional Surface Impedance of a Normal-Metal Film Covering a Spin-Triplet Superconductor Due to Odd-Frequency Cooper Pairs, *Phys. Rev. Lett.* **107**, 087001 (2011).
- [42] S.-I. Suzuki and Y. Asano, Paramagnetic instability of small topological superconductors, *Phys. Rev. B* **89**, 184508 (2014).
- [43] Y. Asano and A. Sasaki, Odd-frequency Cooper pairs in two-band superconductors and their magnetic response, *Phys. Rev. B* **92**, 224508 (2015).
- [44] G. Eilenberger, Transformation of gorkov's equation for type ii superconductors into transport-like equations, *Z. Phys. A* **214**, 195 (1968).
- [45] A. I. Larkin and Y. N. Ovchinnikov, Quasiclassical method in the theory of superconductivity, *Sov. Phys. JETP* **28**, 1200 (1969).
- [46] M. Rouco, I. V. Tokatly, and F. S. Bergeret, Spectral properties and quantum phase transitions in superconducting junctions with a ferromagnetic link, *Phys. Rev. B* **99**, 094514 (2019).
- [47] Y. Asano, Y. V. Fominov, and Y. Tanaka, Consequences of bulk odd-frequency superconducting states for the classification of cooper pairs, *Phys. Rev. B* **90**, 094512 (2014).
- [48] S. Higashitani, Odd-frequency pairing effect on the superfluid density and the Pauli spin susceptibility in spatially nonuniform spin-singlet superconductors, *Phys. Rev. B* **89**, 184505 (2014).
- [49] A. A. Abrikosov, L. P. Gor'kov, and I. E. Dzyaloshinski, *Methods of Quantum Field Theory in Statistical Physics* (Dover, New York, 1975).
- [50] N. Schopohl, Transformation of the eilenberger equations of superconductivity to a scalar riccati equation, [arXiv:cond-mat/9804064](https://arxiv.org/abs/cond-mat/9804064).
- [51] S. Higashitani, Mechanism of paramagnetic meissner effect in high-temperature superconductors, *J. Phys. Soc. Jpn.* **66**, 2556 (1997).
- [52] H. Walter, W. Prusseit, R. Semerad, H. Kinder, W. Assmann, H. Huber, H. Burkhardt, D. Rainer, and J. A. Sauls, Low-temperature Anomaly in the Penetration Depth of $\text{YBa}_2\text{Cu}_3\text{O}_7$ Films: Evidence for Andreev Bound States at Surfaces, *Phys. Rev. Lett.* **80**, 3598 (1998).
- [53] S.-I. Suzuki and Y. Asano, Effects of surface roughness on the paramagnetic response of small unconventional superconductors, *Phys. Rev. B* **91**, 214510 (2015).
- [54] G. Eilenberger, General approximation method for the free energy functional of superconducting alloys, *Z. Phys.* **190**, 142 (1966).