



HOKKAIDO UNIVERSITY

Title	MEASUREMENT OF ACIDITY AND BASICITY OF SILICA-ALUMINA AND ACIDITY OF ZINC SULFIDE BY CALORIMETRIC TITRATION
Author(s)	TANABE, Kozo; YAMAGUCHI, Tsutomu
Citation	JOURNAL OF THE RESEARCH INSTITUTE FOR CATALYSIS HOKKAIDO UNIVERSITY, 14(1), 93-100
Issue Date	1966-04
Doc URL	https://hdl.handle.net/2115/24809
Type	departmental bulletin paper
File Information	14(1)_P93-100.pdf



MEASUREMENT OF ACIDITY AND BASICITY OF SILICA-ALUMINA AND ACIDITY OF ZINC SULFIDE BY CALORIMETRIC TITRATION

By

Kozo TANABE^{*)} and Tsutomu YAMAGUCHI^{*)}

(Received February 9, 1966)

Abstract

Surface acidities of silica-alumina and zinc sulfide and the basicity of silica-alumina were measured by a calorimetric titration, using *n*-butylamine or trichloroacetic acid as a titrating base or acid respectively. It was found that silica-alumina showed acidity of *ca.* 0.8 mmol/g and basicity of *ca.* 0.6 mmol/g. Zinc sulfide showed *ca.* 1.3 mmol/g acidity. The observed acidities of both silica-alumina and zinc sulfide were found greater than those measured by an indicator method, suggesting the existence of weak acid sites which could not be measured by the latter method. Heat of the reaction of silica-alumina with *n*-butylamine was obtained as 13.8 ± 0.4 kcal/mol.

Introduction

We have previously measured the surface acidity and basicity of many solids such as metal oxides, sulfates, sulfides etc. by titrating with *n*-butylamine or benzoic acid, using acid-base indicators¹⁾. In the present work, calorimetric titration method was employed for the determination of both acidity and basicity of solids and the observed values were compared with those measured by the method using indicators. The calorimetric determination of surface acidity was first conducted by TRAMBOUZE *et al.*²⁾ and developed recently by TOPCHIEVA *et al.*³⁾ In their works, ethylacetate and dioxane which react with Lewis acid alone were used as titrating bases, while we employed *n*-butylamine to measure the sum of Brönsted and Lewis acidity. Trichloroacetic acid was also employed in order to measure the basicity of silica-alumina which could not be measured by the indicator method as we have reported previously¹⁾.

Experimental

Materials and Reagents

Silica-alumina was prepared by precipitation from sodium silicate solution

^{*)} The Research Institute for Catalysis, Hokkaido Univ., Sapporo, Japan.

and aluminum nitrate solution followed by heating the precipitate in air at 500°C⁴). The acidity was found to be 0.55 mmol/g by means of the indicator method with methyl red ($pK_a = +4.8$) or dimethyl yellow ($pK_a = +3.3$) and *n*-butylamine as a titrating reagent. Zinc sulfide was a guaranteed reagent of Kanto Chemical Co. Its acidity by the indicator method was the same as that reported in our previous paper¹³.

Benzene, trichloroacetic acid (both guaranteed reagents of Kanto Chemical Co.) and *n*-butylamine (guaranteed reagent of Tokyo Chemical Industry) were used without further purification. The concentration of trichloroacetic acid in benzene was determined by titrating with *n*-butylamine, using bromthymol blue as an indicator.

Measurement of Acidity and Basicity

100 ml of benzene and 3~5 g of solid materials were put into a 500 ml Dewar vessel equipped with a Beckmann thermometer, a glass stirrer and a microburette. For thermal insulation, the vessel was covered with a thick cork. The contents of the vessel were stirred and the slight rise in temperature due to the mechanical heat generation was read every two minutes as shown by crosses (line M) in Fig. 1. Then 0.5 ml or 1 ml of *n*-butylamine was added

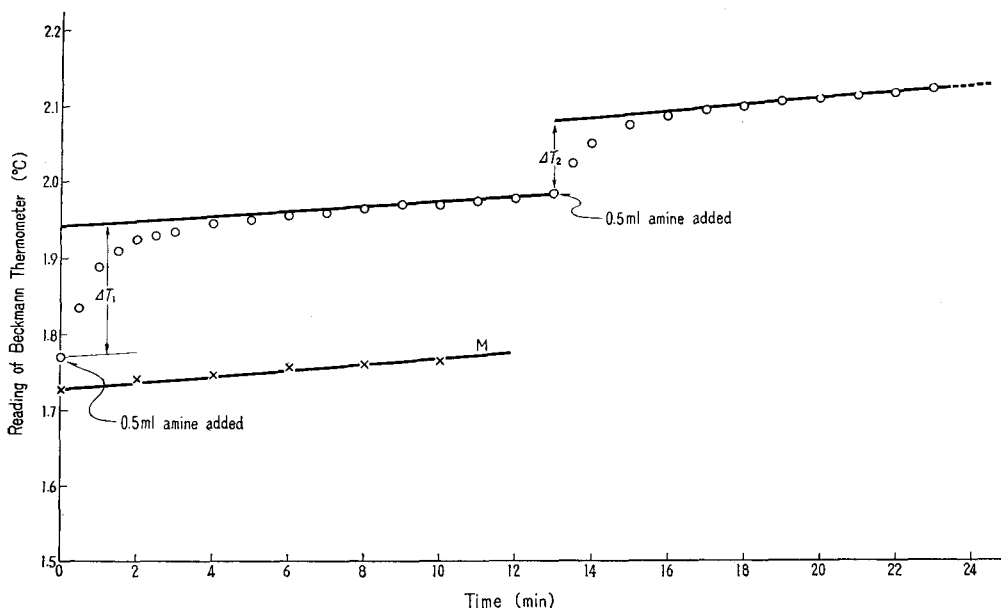


Fig. 1. Temperature rise due to the heat of reaction of silica-alumina (3.9 g) with 1.01 N *n*-butylamine (0.5 ml). Line M shows temperature rise where no amine is added.

Measurement of Acidity and Basicity of Silica-alumina and Acidity of Zinc Sulfide

from a microburette and the temperature rise due to the heat of the acid-base reaction was read every 30 or 60 seconds as shown by circles in Fig. 1. After the rate of temperature increase reduced to the constant value due to stirring, as indicated by a temperature-time relation parallel with line M, another 0.5 or 1 ml amine was added and the temperature rise was recorded similarly. This procedure was repeated until no further temperature increase due to the reaction could be brought about by further addition of amine. The temperature increase due to the heat of acid-base reaction is given by the differences ΔT_i of parallel lines before and after each addition of amine.

The integrated increase in temperature, $\Delta T_n = \sum \Delta T_i$, was plotted against the titre volume of amine as shown in Figs. 3 and 4. At the end point of the titration, the curves become flat, indicating $\Delta T_n = \Delta T_{n+1}$. The acidity is obtained from the total amount of amine which can be read at the end point.

The basicity was measured similarly by using trichloroacetic acid instead of *n*-butylamine as a titrating reagent. Since the heat of dissolution of trichloroacetic acid is not negligible (see a dotted line*) of Fig. 5), rather large correction for this effect and the mechanical one had to be made to obtain the plots of Fig. 6.

The Heat of Reaction of Silica-alumina with Amine

The heat of the reaction ($-\Delta H$) was calculated from Eq. (1) using total temperature increase, ΔT_t , sample weight W , acidity A and heat capacity Q .

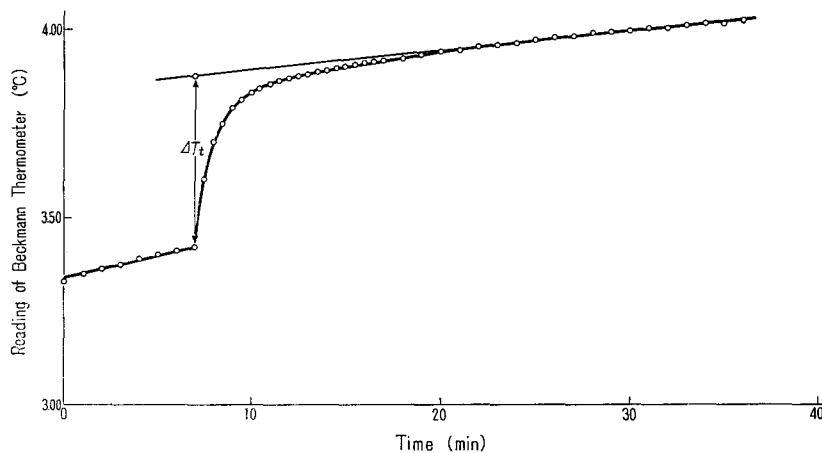


Fig. 2. Temperature rise due to the heat of reaction of silica-alumina (3.45 g) with 1.00 N *n*-butylamine (5 ml).

*) which also contains a small temperature increase due to mechanical heat.

Kozo TANABE and Tsutomu YAMAGUCHI

$$-\Delta H = \frac{Q \times \Delta T t}{A \times W} \text{ (kcal/mol)} \quad (1)$$

$\Delta T t$ was obtained by reading the temperature increase brought about by the addition of excess amine for neutralizing solid acid as shown in Fig. 2. The heat capacity in the same system was calculated to be 49 ± 1 cal/deg using the equation.

$$Q = \frac{I \times V \times t}{4.18 \times \Delta T q}, \quad (2)$$

where the value of the temperature increase $\Delta T q$ was 0.928°C when an electric power ($V=3.0\text{V}$, $I=190\text{mA}$) was supplied for 5 min. to NICHROM wire as heater.

The heat of reaction of silica-alumina with *n*-butylamine was thus found to be 13.8 ± 0.4 kcal/mol.

Results and Discussion

Acidities of Silica-alumina and Zinc Sulfide

Amine titration curves for silica-alumina and zinc sulfide are shown in Figs. 3 and 4. The titres of 1.01 N *n*-butylamine required for neutralizing 3.9 g of silica-alumina and 3.76 g of zinc sulfide are 3 and 5 ml, respectively. Thus, the acidity is calculated to be 0.78 mmol/g for silica-alumina and 1.3 mmol/g

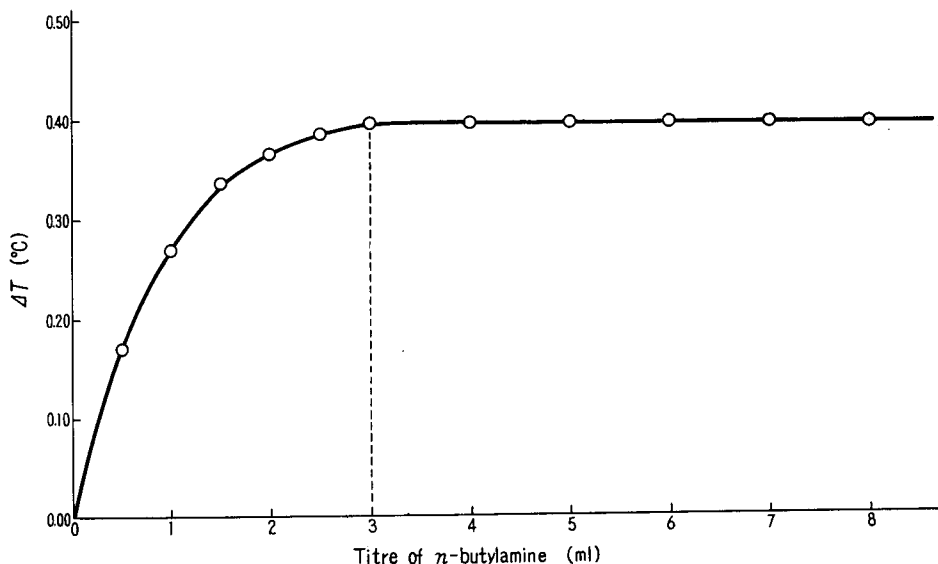


Fig. 3. Titration curve. $\text{SiO}_2 \cdot \text{Al}_2\text{O}_3$; 3.9 g, *n*-butylamine; 1.01 N

Measurement of Acidity and Basicity of Silica-alumina and Acidity of Zinc Sulfide

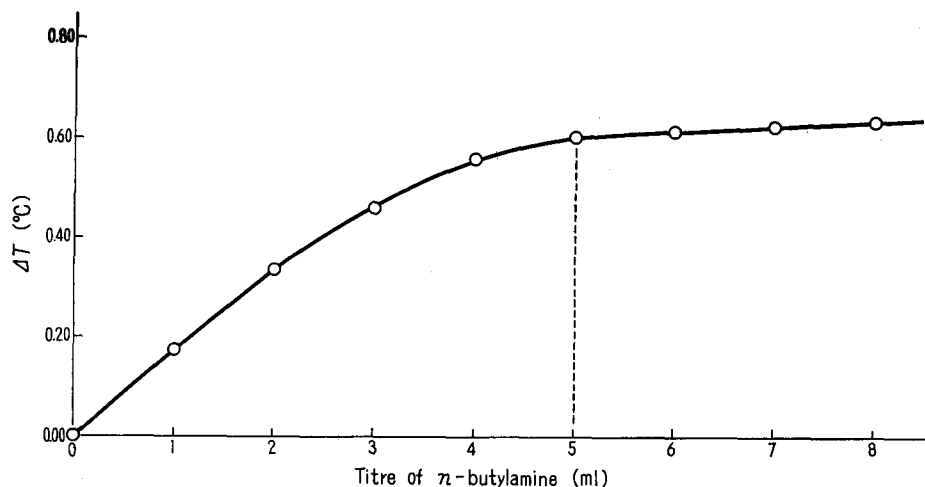


Fig. 4. Titration curve. ZnS; 3.76 g, *n*-butylamine; 1.01 N.

for zinc sulfide. These values are higher than those measured by the indicator method, as illustrated in Table 1. This indicates that the acid sites exist whose acid strength is less than $pK_a = +4.8$ for silica-alumina and $pK_a = +6.8$ for

TABLE 1. Acidity of $\text{SiO}_2 \cdot \text{Al}_2\text{O}_3$ and ZnS.

Solid Acids	Calorimetric Titration Method mmol/g	Indicator Method (mmol/g)			
		NR ^{*)}	MR ^{*)}	PNA ^{*)}	DY ^{*)}
$\text{SiO}_2 \cdot \text{Al}_2\text{O}_3$	0.78	—	0.55	0.55	—
ZnS	1.3	0.773 ^{**)}	0.36 ^{**)}	0.092 ^{**)}	0 ^{**)}

^{*)} NR; neutral red ($pK_a = +6.8$), MR; methyl red ($pK_a = +4.8$), PNA; phenylazo- α -naphthylamine ($pK_a = +4.0$), dimethyl yellow ($pK_a = +3.3$).

^{**)} See ref. 1.

zinc sulfide and that they can be measured by the calorimetric titration method, using a comparatively strong base, *n*-butylamine.

It is also seen in Figs. 3 and 4 that the rate of temperature rise becomes gradually smaller as the total amount of amine titre is increased. This seems to indicate that there exists an energetic heterogeneity of acid sites, as pointed out by TOPCHIEVA *et al.*³⁾ The slow reaction of amine with acid sites having smaller acid strength and the slower diffusion of amine molecule into micro-pores of solid catalysts may result in the slower rate of temperature rise.

Kozo TANABE and Tsutomu YAMAGUCHI

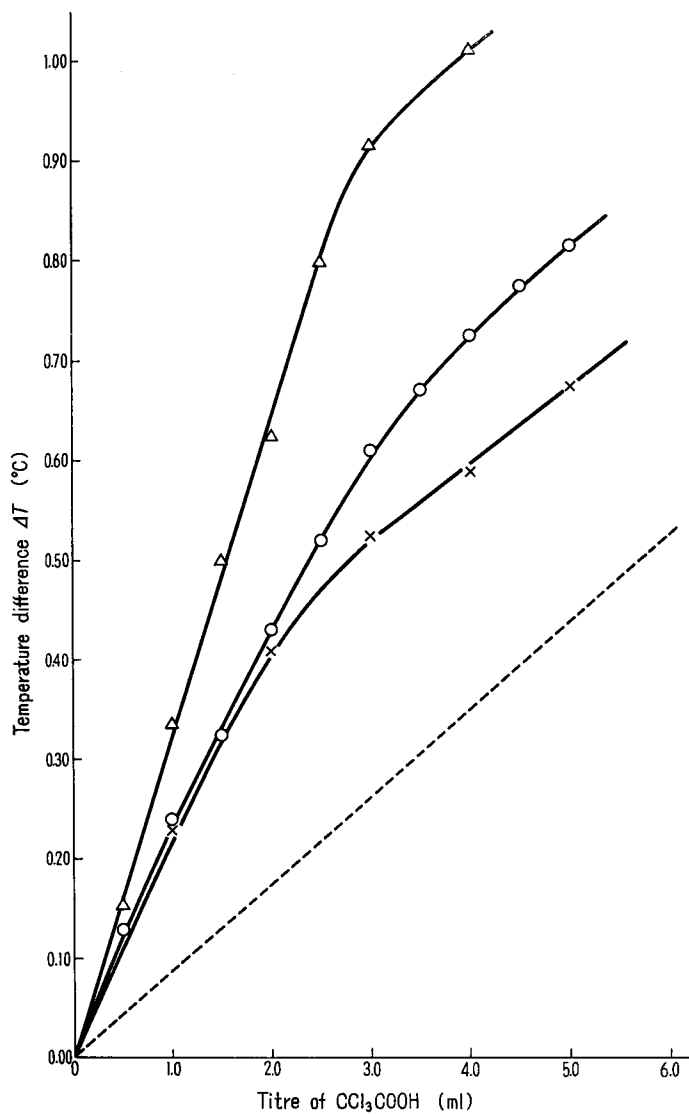


Fig. 5. Titration curves. $\text{SiO}_2 \cdot \text{Al}_2\text{O}_3$: \triangle ; 4.08 g, \circ ; 4.15 g, \times ; 4.22 g. Trichloroacetic acid; 0.810 N. Dotted line shows temperature rise due to the heat of dissolution plus mechanical heat.

Measurement of Acidity and Basicity of Silica-alumina and Acidity of Zinc Sulfide

Basicity of Silica-alumina

Titration curves for basicity measurement of silica-alumina are given in Fig. 6. Taking 3 ml as the amount of trichloroacetic acid required for neutralizing basic sites of silica-alumina, the basicity is calculated to be 0.58~0.60 mmol/g.*) Since trichloroacetic acid is a fairly strong acid, comparatively weak basic sites must be also included in the observed basicity. Nevertheless,

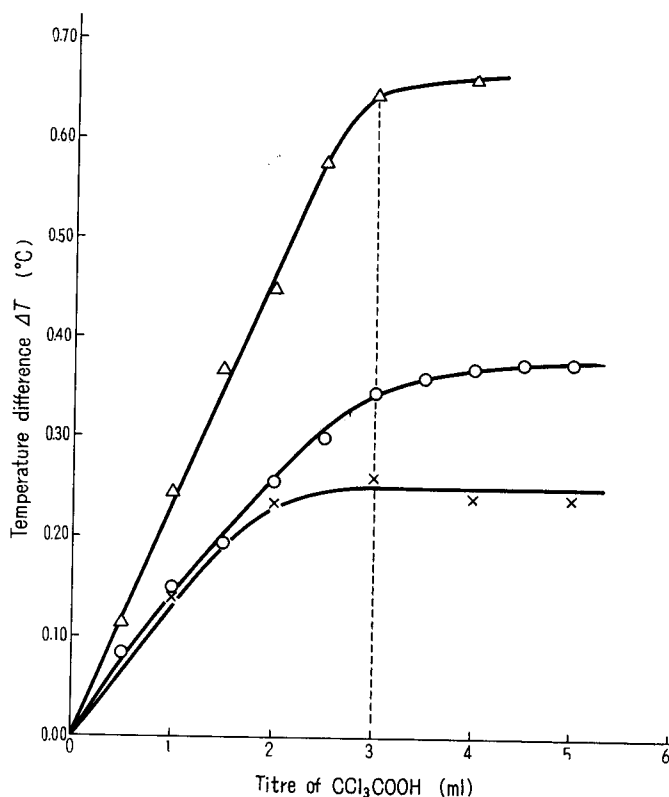


Fig. 6. Corrected titration curve for basicity determination.
 SiO₂·Al₂O₃: △; 4.08 g, ○; 4.15 g, ×; 4.22 g.
 CHCl₃COOH; 0.810 N.

the fact that basic sites as well as acid sites do exist on silica-alumina is of great importance in a view-point of acid-base bifunctional catalysis. It was already reported by BROUWER⁵⁾ that double-bond isomerization of olefins on

*) An attempt to measure basicity by titrating with benzoic acid using bromthymol blue as an indicator failed in the case of silica-alumina, since the adsorbed indicator did not show its basic color (see ref. 1).

Kozo TANABE and Tsutomu YAMAGUCHI

solid acids such as silica-alumina largely occurs by way of a concerted reaction, under the assumption of a bifunctional nature of acid and base. Recently, PINES⁶⁾ also proposed a concerted mechanism for the dehydration of alcohol catalyzed by alumina and SCHWAB⁷⁾ gave evidence for the existence of basic points on the catalyst, although a question remains as to his method of boron fluoride adsorption.⁸⁾

Acknowledgment

We are indebted to Dr. M. ENYO for his kind help in conducting a part of the present investigation and to Dr. M. KATAYAMA for his helpful discussion.

References

- 1) K. TANABE and T. YAMAGUCHI, *This Journal*, **11**, 179 (1964).
- 2) Y. TRAMBOUZE, *Compt. rend.*, **233**, 648 (1951); Y. TRAMBOUZE, L. DE MOURGUES and M. PERRIN, *J. Chim. Phys.* **51**, 723 (1954); *Compt. rend.*, **236**, 1023 (1953).
- 3) K. V. TOPCHIEVA, I. F. MOSKOVSKAJA and N. A. DOBROKHOTOVA, *Kinetics and Catalysis (USSR)*, **5**, 910 (1964); K. V. TOPCHIEVA and I. F. MOSKOVSKAJA, *Dokl. Acad. Nauk (USSR)*, **123**, 891 (1958); K. V. TOPCHIEVA, I. F. MOSKOVSKAJA, L. G. BODROVA and E. I. KRUPIENJA, *J. Moscow Univ.*, 2nd series-Chemistry, **2**, 225 (1959).
- 4) N. HARA, S. ASANO and M. IKEBE, *J. Chem. Soc. Japan. Ind. Chem. Sect.*, **56**, 176 (1935).
- 5) D. M. BROUWER, *J. Catalysis*, **1**, 22 (1962).
- 6) K. WATANABE, C. N. PILLAI and H. PINES, *J. Am. Chem. Soc.*, **84**, 3934 (1962).
- 7) G. M. SCHWAB, "Proceedings of 3rd International Congress on Catalysis," Amsterdam, I-20 (1964).
- 8) See a discussion made by Dr. HAIR in ref. 7.