



HOKKAIDO UNIVERSITY

Title	Hydrogen and Helium Desorptions from B4C Overlaid Graphite and Isotropic Graphite
Author(s)	Yamauchi, Yuji; Hino, Tomoaki; Yamashina, Toshiro
Citation	北海道大學工學部研究報告, 174, 25-30
Issue Date	1995-07-28
Doc URL	https://hdl.handle.net/2115/42449
Type	departmental bulletin paper
File Information	174_25-30.pdf



Hydrogen and helium desorptions from B₄C overlaid graphite and isotropic graphite

Yuji YAMAUCHI¹, Tomoaki HINO^{1,2} and Toshiro YAMASHINA¹

(Received March 31, 1995)

Abstract

The desorption behavior for hydrogens and heliums trapped in B₄C overlaid graphite and isotropic graphite were examined by using a technique of thermal desorption spectroscopy. For the B₄C overlaid graphite, the trapped helium desorbed at relatively low temperature, ~300 °C, which was much lower than that of the hydrogen (~800 °C). For the graphite, the similar behavior was observed. The present data are useful to understand the uptake of the helium or the fuel hydrogen in a burning plasma.

1. Introduction

As the plasma facing material in fusion devices, B₄C coated graphite called B₄C overlaid graphite and boron film coatings on the graphite wall have been employed to improve recycling characteristics⁽¹⁻³⁾, to trap or getter the oxygen impurity^(4,5) and to reduce the chemical sputterings of the graphite⁽⁶⁾. Since the hydrogen trapped in the boron desorbs at relatively low temperature, ~350 °C, and the impact desorption cross section is larger than that of the carbon, the hydrogen concentration of the boron can be kept small by the baking and/or the helium discharge cleanings.

In JT-60U, a large number of the B₄C overlaid graphite tiles have been used in the divertor⁽⁷⁾, in addition to the boronization pretreatment before the main discharge shots. When the heat flux to the B₄C tiles in the divertor was enhanced by shifting the poloidal position of the divertor trace, it was observed that the level of helium ions injected as helium neutral beams was largely reduced⁽⁷⁾. It is presumed that the evaporated borons and/or the carbons getter or trap the heliums. However, the data concerning a helium trapping of boron material has not been systematically obtained yet. It thus is important to examine the helium trapping behavior of boron or carbon material.

In the present study, first the B₄C overlaid graphite was exposed to hydrogen ion beam until the hydrogen concentration saturated. Then, this material was exposed⁽⁸⁾ to helium

¹Department of Nuclear Engineering, Hokkaido University, Kita-13, Nishi-8, Kita-ku, Sapporo, 060 Japan

²National Institute for Fusion Science, Furo-cho, Chikusa-ku, Nagoya, 464-01 Japan

ion beam and the desorption spectra for both hydrogens and heliums are taken by using a technique of thermal desorption spectroscopy, TDS. The obtained spectra showed that the peak temperature of helium desorption was significantly lower than that of the hydrogen. Similar results were obtained also for the isotropic graphite. The present data may be helpful to understand the uptake behavior of the helium for the B₄C overlaid graphite or the isotropic graphite.

2. Experiments

The B₄C overlaid graphite and the isotropic graphite, PD-330S, made by Hitachi Chemical Inc., were irradiated at RT by hydrogen ions with an energy of 1.5 keV in the ECR ion source⁽⁶⁾. The fluence of hydrogen ions was large enough for the hydrogen concentration to be saturated, e.g. $\sim 5 \times 10^{18}$ H/cm². Then, these materials were irradiated by the helium ions with a fluence up to 3×10^{19} He/cm² and an energy of 4.5 keV in the same apparatus. After the irradiation due to the helium ions, the trapped amounts of both the hydrogen and the helium were measured by a TDS technique. For this purpose, the irradiated samples were resistively heated with a ramp rate of 50 °C/min and the desorption amounts were quantitatively measured by a quadruple mass spectrometer, QMS, in the same apparatus.


Figures 1(a), (b) and (c) show the desorption spectra of the isotropic graphite for different values of the helium fluence. As the increase of the helium fluence, the trapped amount of helium increased and the peak temperature (~ 200 °C) was very much lower than that of the hydrogen (~ 800 °C). The selective pumping of the graphite for the helium becomes possible when the temperature is lower than approximately 500 °C.

Figures 2(a), (b) and (c) show the desorption spectra of the B₄C overlaid graphite for different values of the helium fluence. Compared with the case of the graphite, the desorption peak of the helium was relatively broad but the helium desorption took place at the temperature lower than that of the hydrogen. Again the selective pumping of the B₄C overlaid graphite becomes possible when the temperature is lower than approximately 300 °C.

Figures 3 and 4 show the total desorption amounts of H₂ and He for the graphite and the B₄C overlaid graphite, respectively. Although the hydrogen amount retained decreased with an increase of the helium fluence, the helium amount trapped increased with the helium fluence. The capability of the B₄C overlaid graphite for the helium trapping is roughly the same as the graphite.


3. Discussions

The present data suggest that the helium can be trapped both by the boron or the carbon if the wall temperature is lower than approximately 500 °C. When the B₄C overlaid graphite receives a large heat flux, both the boron and the carbon can evaporate and then the selective

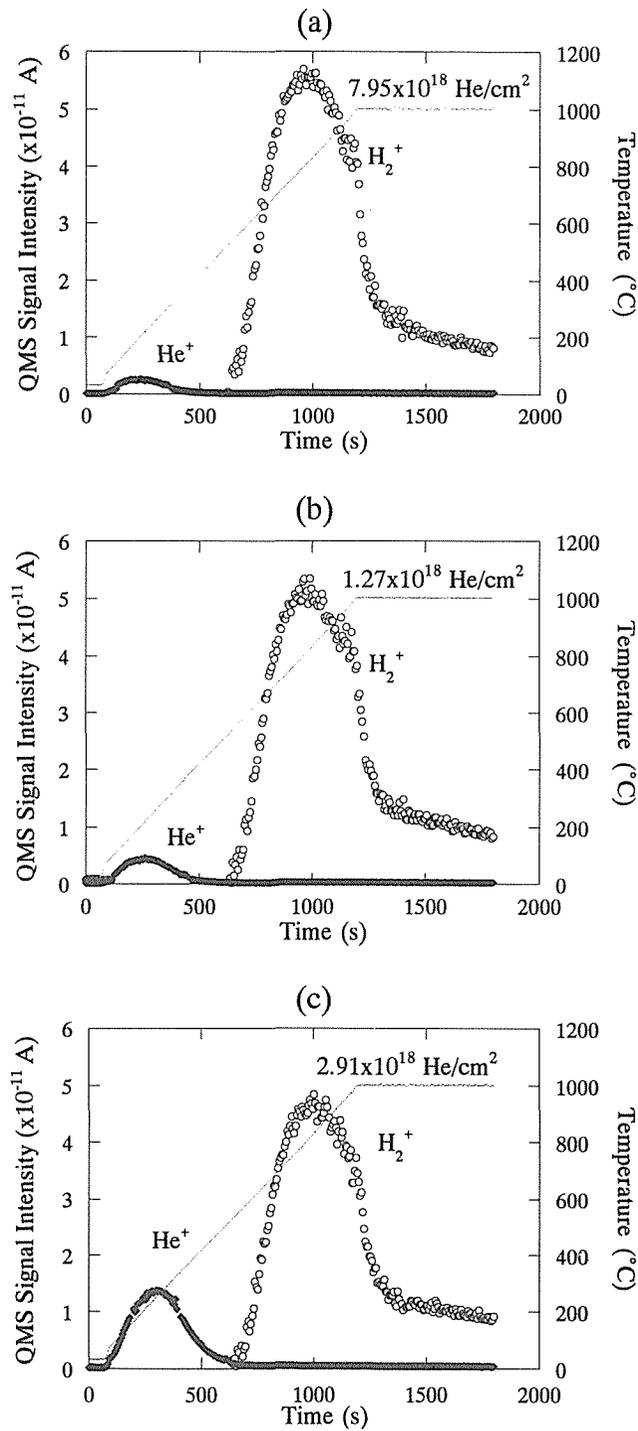

Figures 1 (a),(b)and(c)

H₂ and He desorption spectra of isotropic graphite after He ion irradiations with He fluences of 7.95×10^{17} He/cm²(a), 1.27×10^{18} He/cm²(b) and 2.91×10^{18} He/cm²(c).

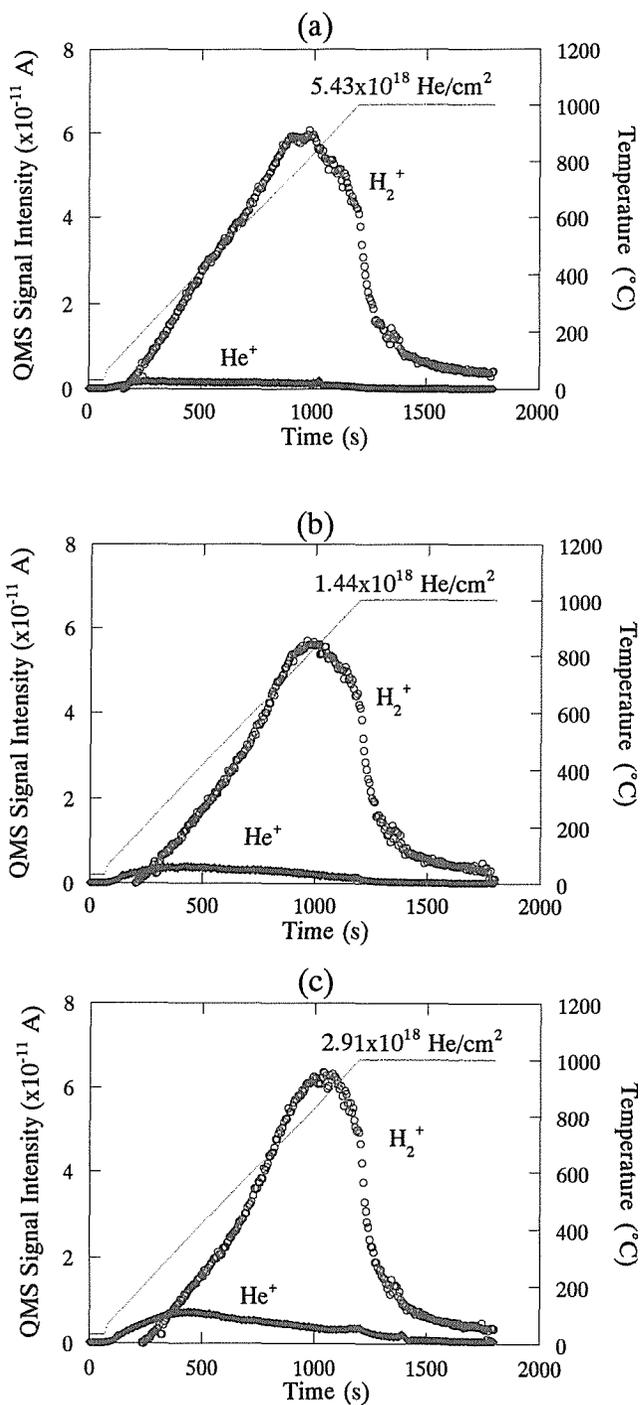

Figures 2 (a),(b)and(c)

H_2 and He desorption spectra of B_4C overlaid graphite after He ion irradiations with He fluences of $5.43 \times 10^{17} \text{ He/cm}^2$ (a), $1.44 \times 10^{18} \text{ He/cm}^2$ (b) and $2.91 \times 10^{18} \text{ He/cm}^2$ (c).

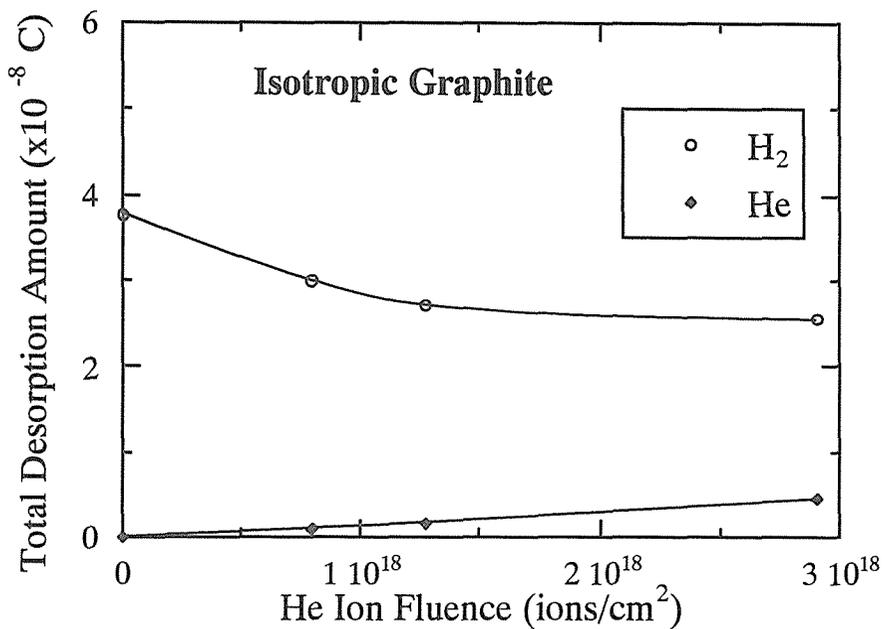


Figure 3

He fluence dependences of total trapped amounts of H₂ and He for isotropic graphite.

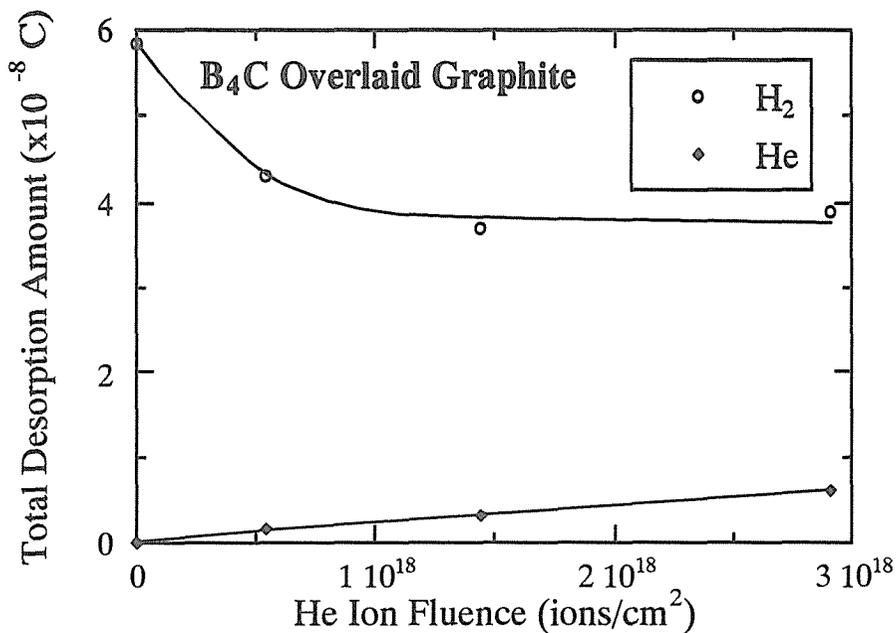


Figure 4

He fluence dependences of total trapped amounts of H₂ and He for B₄C overlaid graphite.

pumping for the helium may take place if the wall temperature is not so high. The strong uptake of the helium due to the evaporation of the B₄C overlaid graphite may be able to be explained by this reason. In addition, the present data may be helpful to understand the helium uptake in a burning plasma.

References

- (1) G. L. Jackson et al., J. Nucl. Mater. 196-198(1992) 236.
- (2) M. Saidoh et al., Jpn. J. Appl. Phys. Pt1, 32(1993) 3276.
- (3) T. Hino et al., J. Nucl. Mater. 210(1994) 226.
- (4) J. Winter, J. Nucl. Mater. 176&177(1990) 14.
- (5) T. Hino and T. Yamashina, J. Fusion Energy 13(1994) 69.
- (6) T. Hino et al., J. Nucl. Mater. 211(1994) 30.
- (7) T. Ando, M. Saidoh et al., To be presented in Japan-US Workshop P234 on High Heat Flux Components and Plasma Surface Interactions for Next Fusion Devices, Jan.31-Feb.3, 1995.
- (8) Y. Yamauchi, T. Hino et al, To be published in J. Nucl. Mater. (1995).