



Title	Unique [core+two] structure and optical property of a dodeca-ligated undecagold cluster : critical contribution of the exo gold atoms to the electronic structure
Author(s)	Shichibu, Yukatsu; Kamei, Yutaro; Konishi, Katsuaki
Citation	Chemical Communications, 48(61), 7559-7561 https://doi.org/10.1039/c2cc30251a
Issue Date	2012-08-07
Doc URL	https://hdl.handle.net/2115/52107
Rights	Chem. Commun., 2012, 48, 7559-7561 - Reproduced by permission of The Royal Society of Chemistry (RSC)
Type	journal article
File Information	CC48-61_7559-7561.pdf



Cite this: DOI: 10.1039/c2cc30251a

www.rsc.org/chemcomm

COMMUNICATION

Unique [core+two] structure and optical property of dodeca-ligated undecagold cluster: Critical contribution of the exo gold atoms to the electronic structure†

Yukatsu Shichibu, Yutaro Kamei, and Katsuaki Konishi*

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

A novel dodeca-ligated undecagold cluster having a nonagold core plus two exo-attached gold atoms was synthesized. Unlike the conventional icosahedron-based “core-only” isomer, the [9+2] cluster showed an intense visible absorption band. Theoretical calculation showed the involvement of the exo gold atoms in the generation of the unique electronic structure.

For several decades, there has been considerable interest in the unique structures and properties of geometrically defined gold clusters.^{1,2} The crystal structures of many phosphine-protected clusters have been determined;^{1,3–6} they reveal the metallic moieties generally prefer to form a “core” consisting of fused polyhedra. Herein we report the unusual [core+two] structure of a novel diphosphine-coordinated cluster cation $[\text{Au}_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{PPh}_2)_6]^{3+}$ (**1**), whose Au_{11} moiety consists of a toroidal Au_9 core and two appended gold atoms. The optical profile of **1** was rather different from those of conventional “core-only” clusters, and was characterised by the intense isolated absorption band in the visible region. We also conducted theoretical calculation studies⁷ to demonstrate the critical role of the exo-attached gold atoms in the generation of the unique electronic structure.

The dodeca-ligated Au_{11} cluster cation (**1**) was synthesized from the gold complex $\text{Au}_2(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{PPh}_2)\text{Cl}_2$.⁸ When the gold salt was reduced by NaBH_4 in ethanol at 0 °C, the colourless solution gradually became greenish over time. The addition of NaSbF_6 after 1 h precipitated the cluster product as the hexafluoroantimonate salt, which was further purified by recrystallisation. The electrospray ionization mass spectrum of the cluster species thus obtained shows a set of signals around $m/z \approx 1519$, which was unambiguously assigned to the trivalent cluster cation

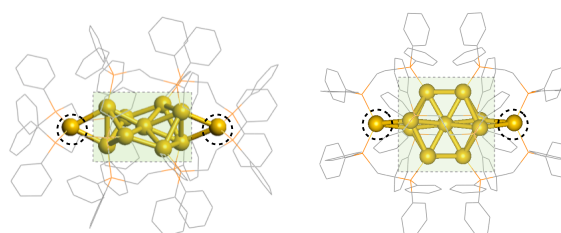


Fig. 1 Side (left) and top (right) views of the crystal structure of $[\text{Au}_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{PPh}_2)_6]^{3+}$ (**1**) representing the [9+2] structure consisting of a Au_9 core and two gold atoms at the exo positions. The core units and the exo gold atoms are indicated by the shaded rectangles and the dotted circles, respectively.

$[\text{Au}_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{PPh}_2)_6]^{3+}$ by comparison with a simulated isotopic distribution pattern (see, ESI†). Single-crystal X-ray analysis of **1**·(SbF_6)₃ revealed a unique cluster structure composed of a Au_9 core plus two gold atoms at the exo positions (Fig. 1). The exo atoms form triangles by sharing an edge of the Au_9 core. The Au_9 core unit is apparently similar to previously known examples of butterfly-shaped clusters, although it has a slightly wider range of Au–Au bond distances (2.6294(8)–2.9709(8) Å) than $[\text{Au}_9(\text{PPh}_3)_8]^{3+}$ (2.6745(9)–2.8804(12) Å)^{3b} and $[\text{Au}_9(\text{P}(p\text{-C}_6\text{H}_4\text{OCH}_3)_3)_8]^{3+}$ (2.689(2)–2.899(4) Å).^{3a} This may reflect some distortion caused by the bridging of the exo gold atoms. The exo gold atoms have Au–Au bond distances of 2.7769(9) and 2.8240(8) Å, which lie in the range of the bond distances in the central butterfly unit. Each of the exo gold atoms of **1** is bonded to the two phosphine ligands and is situated at the tetrahedral centre, whereas the eight peripheral gold atoms of the Au_9 core accommodate single phosphine ligands. The structure found in the solid state appeared essentially retained in solution. The ³¹P NMR spectrum of **1**·(SbF_6)₃ in CD_2Cl_2 showed three signals with an intensity ratio of 1:1:1 (Figure S2, ESI†), which were in agreement with the crystal structure.

1·(SbF_6)₃ in dichloromethane was deep green in colour. Accordingly, the electronic absorption spectrum revealed a distinct band in the red region (663 nm) together with small humps in the blue to UV region (460 and 390 nm) (Fig. 2a). The intense low-energy absorption at 663 nm ($\epsilon_{\text{max}} = 8.9 \times 10^4 \text{ L} \cdot \text{cm}^{-1} \cdot \text{mol}^{-1}$) was apparently observed as a single isolated

Faculty of Environmental Earth Science, Hokkaido University, North 10 West 5, Sapporo 060-0810, Japan. Fax: +81 11 7064538; Tel: +81 11 7064538; E-mail: konishi@ees.hokudai.ac.jp

† Electronic Supplementary Information (ESI) available: Experimental procedures, characterization and crystallographic data, and details of DFT calculations. CCDC 862706. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c2cc30251a

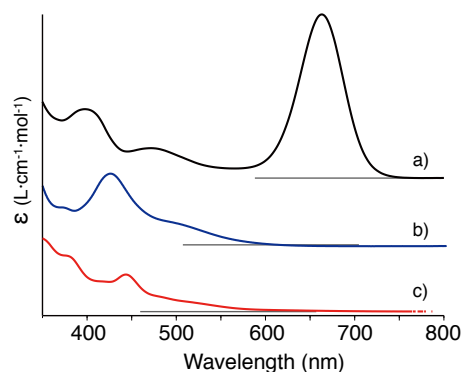


Fig. 2 Visible absorption spectra of a) $[\text{Au}_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_2\text{PPh}_2)_6]^{3+}$ (**1**), b) $[\text{Au}_{11}(\text{Ph}_2\text{P}(\text{CH}_2)_3\text{PPh}_2)_5]^{3+}$ (**2**) and c) $[\text{Au}_9(\text{PPh}_3)_8]^{3+}$.

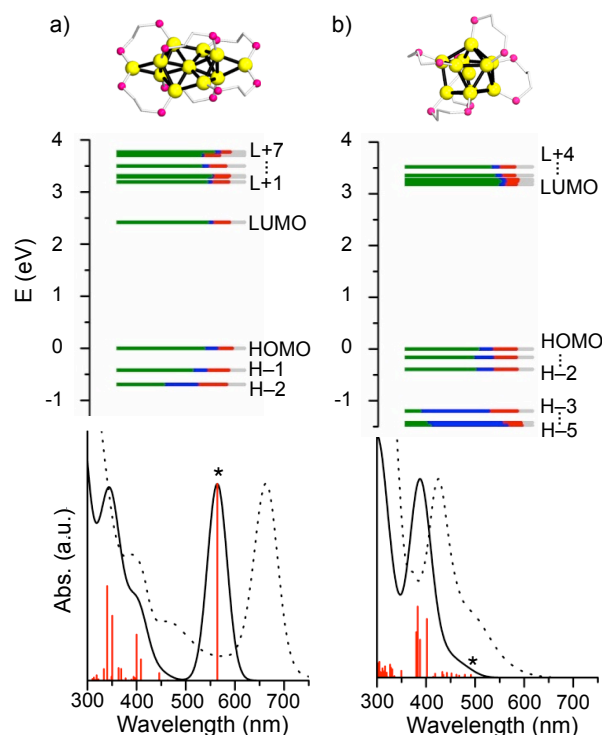


Fig. 3 Geometrical structures (top, Au and P atoms highlighted in yellow and magenta, respectively), Kohn–Sham (KS) orbital energy level diagrams (middle), and theoretical absorption spectra (bottom, solid lines) of a) $[\text{Au}_{11}(\text{H}_2\text{P}(\text{CH}_2)_2\text{PH}_2)_6]^{3+}$ (**1'**) and b) $[\text{Au}_{11}(\text{H}_2\text{P}(\text{CH}_2)_3\text{PH}_2)_5]^{3+}$ (**2'**). Each KS orbital is relative to the HOMO energy and is drawn to indicate the relative contributions (line length with color labels) of the atomic orbitals of Au (6sp) in green, Au (5d) in blue, P (3p) in red, and miscellaneous in gray. H–X and L+Y represent HOMO–X and LUMO+Y, respectively. Experimental absorption profiles of **1** and **2** (dotted lines) are shown for comparison. The asterisks indicate the HOMO–LUMO transitions.

cluster $[\text{Au}_{11}(\text{H}_2\text{P}(\text{CH}_2)_3\text{PH}_2)_5]^{3+}$ (**2'**) differed remarkably. The HOMO and the LUMO were not so energetically isolated from their neighboring orbitals (Fig. 3b (middle)). The LUMO to LUMO+4 were, though not degenerate, very close to each other. The TDDFT results reveal that the oscillator strength of the HOMO $\rightarrow$ LUMO transition (2.52 eV, 491 nm) was small and close to those of several transitions with similar energies (see, ESI†). Transitions with significant oscillator strengths were found at higher energies (e.g., 3.24 eV, 383 nm), thereby giving rise to the tail-plus-humps profile (Fig. 3b (bottom, solid line)). This trend was reasonably well reproduced in the experimentally observed spectrum (Fig. 2b and Fig. 3b (bottom, dotted line)).

As described above, the HOMO–LUMO transition is primarily responsible for the appearance of low-energy intense absorption band of **1**. Fig. 4 depicts the HOMO and

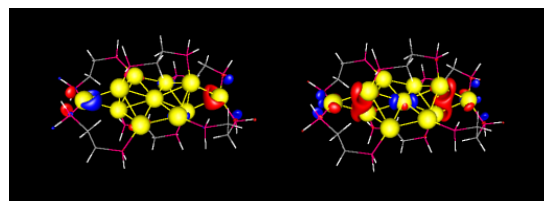


Fig. 4 LUMO (left) and HOMO (right) of $[\text{Au}_{11}(\text{H}_2\text{P}(\text{CH}_2)_2\text{PH}_2)_6]^{3+}$ (**1'**).

the LUMO of **1'**. Both orbitals are located near the triangular Au₃ units situated at both edges of the Au₁₁ entity. The LUMO is found near the exo gold atoms, whereas the HOMO is located on the shared edges of the Au₉ core and Au₃ triangles. Thus, the intense visible absorption band of **1** is mainly due to the core-to-exo intermetal transition.

In conclusion, we have determined the single-crystal structure and the optical property of a novel Au₁₁ cluster (**1**), providing experimental evidence that the attachment of extra metal atom(s) to the gold core moiety results in the generation of the unique electronic structure. Theoretical studies clearly indicate that the characteristic visible absorption is due to the HOMO–LUMO transition associated with the exo gold atoms attached to the metallic core. In contrast to conventional “core-only” clusters, which are generally brown in colour, the [core+two] clusters exhibit unique colours and thus may be potential chromogenic modules. It should be possible to tune their optical properties (colour) by varying the exo metal atoms. Developing a method for the addition reaction of non-gold atoms to core-only gold clusters for the rational design of “alloyed” [core+two] clusters is worthy of further investigation.

This work was partially supported by the MEXT, Grant-in-Aid for Scientific Research on Innovative Areas “Emergence in Chemistry” (20111009) and Japan Science and Technology Agency (JST), Core Research for Evolutional Science and Technology (CREST) and Advanced Low Carbon Technology Research and Development Program (ALCA). We also thank Dr. K. Yoza (Bruker AXS) for crystallography.

Notes and references

- † Crystallographic data for **1**-(SbF₆)₃·5EtOH: C₁₆₆H₁₇₄Au₁₁F₁₈O₅P₁₂Sb₃, *M* = 5494.57, monoclinic, *a* = 18.066(2) Å, *b* = 27.709(4) Å, *c* = 38.450(5) Å, *α* = 90.00°, *β* = 102.908(2)°, *γ* = 90.00°, *V* = 18762(4) Å³, *T* = 90 K, space group *C2/c*, *Z* = 4, 49426 reflections measured, 19177 independent reflections (*R*_{int} = 0.0629). The final *R*_i value was 0.0571 (*I* > 2σ(*I*)). The final *wR*(*F*²) values were 0.1491 (*I* > 2σ(*I*)). The final *R*_i value was 0.0996 (all data). The final *wR*(*F*²) value was 0.1794 (all data).
- (a) *Modern Supramolecular Gold Chemistry*, ed. A. Laguna, Wiley-VCH, Weinheim, 2008; (b) K. P. Hall and D. M. P. Mingos, *Prog. Inorg. Chem.*, 1984, **32**, 237; (c) D. M. P. Mingos, T. Sree and Z. Y. Lin, *Chem. Rev.*, 1990, **90**, 383; (d) R. Jin, *Nanoscale*, 2010, **2**, 343.
 - (a) P. D. Jadzinsky, G. Calero, C. J. Ackerson, D. A. Bushnell and R. D. Kornberg, *Science*, 2007, **318**, 430; (b) M. W. Heaven, A. Dass, P. S. White, K. M. Holt and R. W. Murray, *J. Am. Chem. Soc.*, 2008, **130**, 3754; (c) M. Zhu, C. M. Aikens, F. J. Hollander, G. C. Schatz and R. Jin, *J. Am. Chem. Soc.*, 2008, **130**, 5883; (d) H. Qian, W. T. Eckenhoff, Y. Zhu, T. Pintauer and R. Jin, *J. Am. Chem. Soc.*, 2010, **132**, 8280.
 - (a) C. E. Briant, K. P. Hall and D. M. P. Mingos, *J. Chem. Soc., Chem. Commun.*, 1984, 290; (b) F. Wen, U. Englert, B. Guttrath and U. Simon, *Eur. J. Inorg. Chem.*, 2008, 106; (c) M. Schulz-Dobrick and M. Jansen, *Eur. J. Inorg. Chem.*, 2006, 4498.
 - (a) V. G. Albano, P. L. Bellon, M. Manassero and M. Sansoni, *J. Chem. Soc., Chem. Commun.*, 1970, 1210; (b) F. A. Vollenbroek, J. J. Bour and J. W. A. Van der Velden, *Rec. Trav. Chim. Pays-Bas*, 1980, **99**, 137; (c) J. M. M. Smits, J. J. Bour, F. A. Vollenbroek and P. T. Beurskens, *J. Crystallogr. Spectrosc. Res.* 1983, **13**, 355; (d) R. C. B. Copley and D. M. P. Mingos, *J. Chem. Soc., Dalton Trans.*, 1996, 479; (e) K. Nunokawa, S. Onaka, T. Yamaguchi, T. Ito, S. Watase and M. Nakamoto, *Bull. Chem. Soc. Jpn.*, 2003, **76**, 1601.
 - (a) C. E. Briant, B. R. C. Theobald, J. W. White, L. K. Bell and D. M. P. Mingos, *J. Chem. Soc., Chem. Commun.*, 1981, 201; (b) Y. Shichibu, Y. Negishi, T. Watanabe, N. K. Chaki, H. Kawaguchi and


- T. Tsukuda, *J. Phys. Chem. C*, 2007, **111**, 7845; (c) Y. Shichibu and K. Konishi, *Small*, 2010, **6**, 1216.
- (a) J. W. A. van der velden, J. J. Bour, W. P. Bosman and J. H. Noordik, *J. Chem. Soc., Chem. Commun.*, 1981, 1218; (b) J. W. A. van der Velden, J. J. Bour, J. J. Steggerda, P. T. Beurskens, M. Roseboom and J. H. Noordik, *Inorg. Chem.*, 1982, **21**, 4321; (c) A. Laguna, M. Laguna, M. C. Gimeno and P. G. Jones, *Organometallics*, 1992, **11**, 2759; (d) B. K. Teo, X. B. Shi and H. Zhang, *J. Am. Chem. Soc.*, 1992, **114**, 2743; (e) G. M. T. Cheetham, M. M. Harding, J. L. Haggitt, D. M. P. Mingos and H. R. Powell, *J. Chem. Soc., Chem. Commun.*, 1993, 1000; (f) Y. Kamei, Y. Shichibu and K. Konishi, *Angew. Chem. Int. Ed.*, 2011, **50**, 7442.
- For recent DFT studies on gold clusters, see: (a) K. Nobusada and T. Iwasa, *J. Phys. Chem. C*, 2007, **111**, 14279; (b) M. Walter, J. Akola, O. Lopez-Acevedo, P. D. Jadzinsky, G. Calero, C. J. Ackerson, R. L. Whetten, H. Grönbeck and H. Häkkinen, *Proc. Natl. Acad. Sci. U.S.A.*, 2008, **105**, 9157; (c) Y. Pei, Y. Gao, N. Shao and X. C. Zeng, *J. Am. Chem. Soc.*, 2009, **131**, 13619; (d) D. E. Jiang, K. Nobusada, W. Luo and R. L. Whetten, *ACS Nano*, 2009, **3**, 2351; (e) ref. 2c.
- (a) P. A. Bates and J. M. Waters, *Inorg. Chim. Acta*, 1985, **98**, 125; (b) M. C. Brandys, M. C. Jennings and R. J. Puddephatt, *J. Chem. Soc., Dalton Trans.*, 2000, 4601.
- Butterfly and crown geometries are known for toroidal Au₉ clusters. These two isomers in solution are reported in equilibrium with each other to show similar electronic spectral characteristics (ref. 1b).
- TURBOMOLE V6.3 2011, a development of University of Karlsruhe and Forschungszentrum Karlsruhe GmbH, 1989-2007, TURBOMOLE GmbH, since 2007; available from <http://www.turbomole.com>.
- (a) W. Jahn, *J. Struct. Biol.*, 1999, **127**, 106; (b) M. F. Bertino, Z.-M. Sun, R. Zhang and L.-S. Wang, *J. Phys. Chem. B*, 2006, **110**, 21416; (c) Y. Yanagimoto, Y. Negishi, H. Fujihara and T. Tsukuda, *J. Phys. Chem. B*, 2006, **110**, 11511.

Cite this: DOI: 10.1039/c2cc30251a

www.rsc.org/chemcomm

COMMUNICATION

Table of contents entry

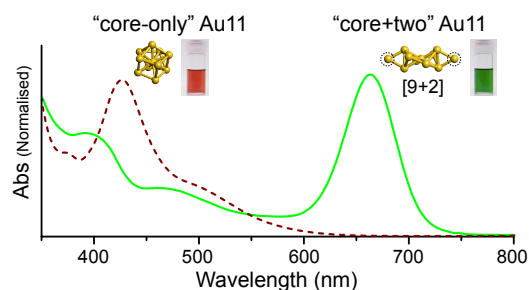

5

A novel Au₁₁ cluster having a “core+two” ([Au₉+2Au]) geometric structure showed an evidently different absorption spectrum from that of the “core-only” isomer.
10 The role of the exo gold atoms was investigated theoretically.