



Title	Self-Healing Behaviors of Tough Polyampholyte Hydrogels
Author(s)	Ihsan, Abu Bin; Sun, Tao Lin; Kurokawa, Takayuki et al.
Citation	Macromolecules, 49(11), 4245-4252 https://doi.org/10.1021/acs.macromol.6b00437
Issue Date	2016-06-14
Doc URL	https://hdl.handle.net/2115/65545
Rights	This document is the Accepted Manuscript version of a Published Work that appeared in final form in Macromolecules, copyright ©2016 American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see http://pubs.acs.org/doi/pdf/10.1021/acs.macromol.6b00437
Type	journal article
File Information	S I-journal.pdf, Supporting Table and Figures



Supporting Information

Self-healing Behaviors of Tough Polyampholyte Hydrogels

Abu Bin Ihsan^{1§}, Tao Lin Sun^{1,2,§}, Takayuki Kurokawa^{1, 2}, Sadia Nazneen Karobi³, Tasuku Nakajima^{1,2}, Takayuki Nonoyama^{1,2}, Chanchal Kumar Roy¹, Feng Luo¹, Jian Ping Gong^{1,2*}

¹Faculty of Advanced Life Science, Hokkaido University, Sapporo 060-0810, Japan

²Global Station for Soft Matter, Global Institution for Collaborative Research and Education (GI-CoRE), Hokkaido University, Sapporo 060-0810, Japan

³Graduate School of Life Science, Hokkaido University, Sapporo 060-0810, Japan

§: Authors equally contributed.

*: Author to whom correspondence should be addressed.

Tel & FAX: +81-(0)11-706-2774, E-mail: gong@mail.sci.hokudai.ac.jp.

Supporting movies

Movie S1. Fast healing behavior. The fresh surfaces were brought together by pressing them slightly at room temperature and then immediately bended. It was surprisingly observed that the two pieces were self-healed immediately after joining. Sample used: PA-0.1.

Movie S2. High strength of the healed sample. After healed in water at 25 °C for 24 h, a dramatic level of self-healing was observed and the scars disappeared completely. The mended samples were able to sustain large deformations of more than 1000% and to recover their shape and size when stress was released. Sample used: PA-0.1

Supporting Table and Figures

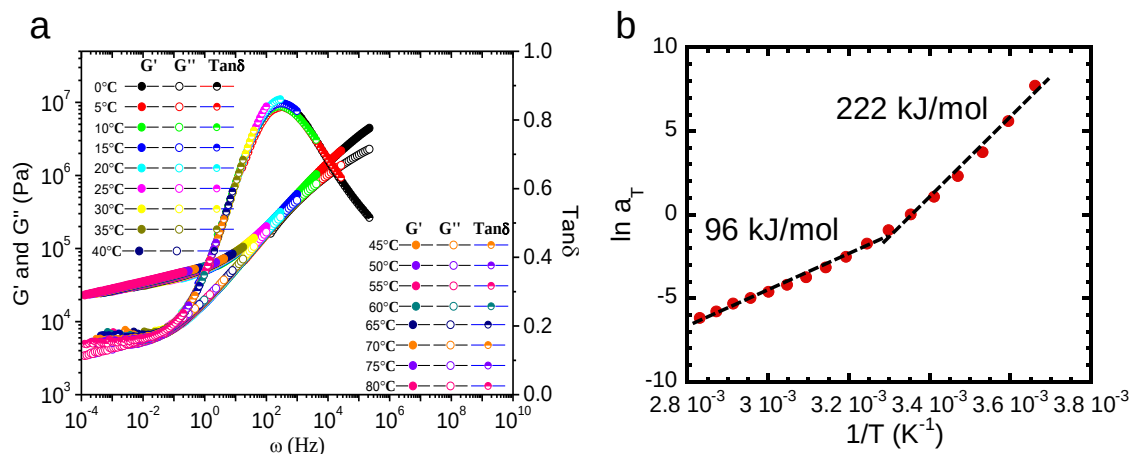


Figure S1: (a) A constructed master curve for frequency dependence of storage modulus (G'), loss modulus (G'') and $\tan\delta$ of PA-0.1. **(b)** Arrhenius plot depicting the temperature dependence of the shift factors for the sample.

By following the principle of time-temperature superposition, a master curve of storage modulus (G'), loss modulus (G'') and $\tan\delta$ over a wide frequency range for the equilibrated gel PA-0.1, was constructed at a reference temperature of 25°C, as presented in **Figure S1**. The apparent activation energy E_a is obtained from the Arrhenius equation, $a_T = Ae^{E_a/k_BT}$, where a_T is the shift factor, R is the ideal gas constant, and A is a constant. The temperature dependence of the shift factor a_T shows that the activation energy of the gel varies over a wide range, 96–222 kJ/mol.

Separation of transient bonds and permanent bonds

The transient, weak bonds and permanent, non-dynamic bonds (strong bonds, chemical and topological crosslinking) contribute to the nominal stress σ_N and they can be expressed by UCM element (viscous element) and the Gent element (elastic element), respectively,

$$\sigma_N(\lambda) = \sigma_{N,v}(\lambda) + \sigma_{N,e}(\lambda) \quad (1)$$

where

$$\sigma_{N,v}(\lambda) = \left(\frac{2G_v D_e}{1 - 2D_e} (1 - \exp(-\frac{(1 - 2D_e)}{D_e}(\lambda - 1))) + \frac{G_v D_e}{1 + D_e} (1 - \exp(-\frac{(1 + D_e)}{D_e}(\lambda - 1))) \right) \lambda^{-1} \quad (2)$$

for the viscoelastic stress, and

$$\sigma_{N,e}(\lambda) = \left(\frac{G_e}{\lambda^2 + 2\lambda^{-1} - 3} (\lambda^2 - \lambda^{-1}) \right) \lambda^{-1} \quad (3)$$

for the entropic elastic stress. Here, λ is the elongation ratio, G_v is the initial shear modulus of the viscoelastic part, stemming from the contribution of weak inter-chain bonds that rupture during deformation. D_e is the Deborah number (the product of the relaxation time of the viscous component and the strain rate). G_e is the shear modulus at small strain from the elastic part, stemming from the contributions of strong inter-chain bonds, the topological inter-chain entanglement, and the chemical cross-linking that do not flow during the deformation. J_m is the maximum allowable value of the first strain invariant representing the theoretical finite extensibility of the network chains. **Eq. 1** is determined by four parameters G_e , λ_m , G_v , and D_e . Since the Young's modulus $E = 3(G_e + G_v)$, we can fit the tensile stress-strain data with the model using 3 independent parameters and the Young's modulus E estimated from the tensile behaviour. The fitted G_e and G_v for the samples PA-C_{MBAA} are shown in **Figure 5** and the fitted parameters D_e and J_m are summarized in **Figure S2**. An increase in C_{MBAA} dramatically constrains the finite extensibility J_m . D_e keeps a constant, independent of C_{MBAA}.

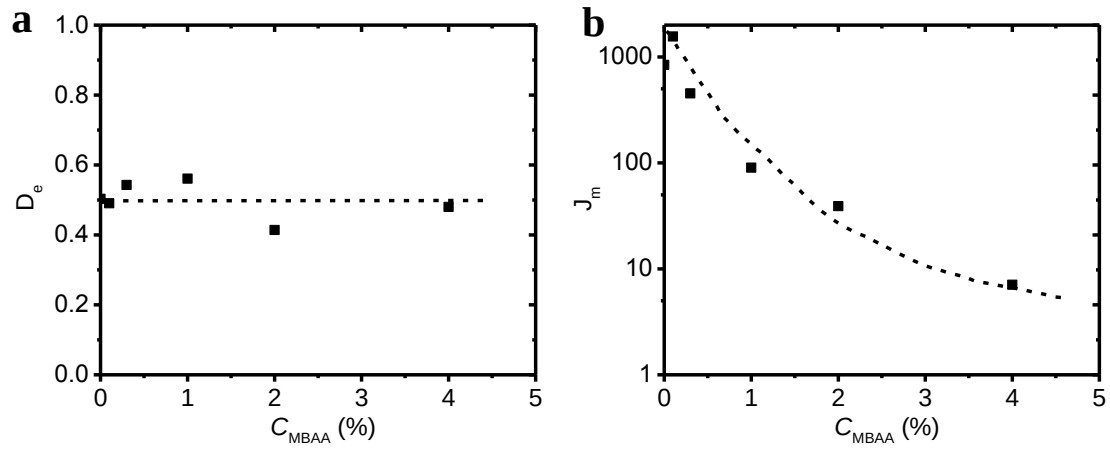


Figure S2. Chemical cross-linker density C_{MBAA} dependences of Deborah number (a) and theoretical first strain invariant value J_m (b) of PA- C_{MBAA} samples. The result was estimated from the tensile stress-strain curves performed at a stretching strain rate 0.011s^{-1} .

Table S1 Fitted parameters of polyampholyte gels PA-0.1 and PA*-0.

Sample	G_e (MPa)	G_v (MPa)	D_e	J_m	G_v/G_e
PA*-0 (25°C)	0.15	0.46	0.21	417.2	3.1
PA*-0 (55°C)	0.006	0.019	0.21	2125.8	3.2
PA-0.1 (4°C)	0.105	0.82	0.13	216.5	7.8
PA-0.1 (37°C)	0.0017	0.019	0.46	149.8	11.4
PA-0.1 (50°C)	0.0019	0.01	0.47	136.5	5.4