



Title	Modulation and Characterization of the Double Network Hydrogel Surface-Bulk Transition
Author(s)	Frauenlob, Martin; King, Daniel R.; Guo, Honglei et al.
Citation	Macromolecules, 52(17), 6704-6713 https://doi.org/10.1021/acs.macromol.9b01399
Issue Date	2019-09-10
Doc URL	https://hdl.handle.net/2115/79235
Rights	This document is the Accepted Manuscript version of a Published Work that appeared in final form in Macromolecules, copyright © American Chemical Society after peer review and technical editing by the publisher. To access the final edited and published work see https://doi.org/10.1021/acs.macromol.9b01399 .
Type	journal article
File Information	Macromolecules_52-17_6704-6713.pdf



Modulation and characterization of the double network hydrogel surface-bulk transition

Martin Frauenlob¹, Daniel R. King^{2,3}, Honglei Guo^{2,3}, Seiichiro Ishihara^{2,3}, Masumi Tsuda^{3,4,5}, Takayuki Kurokawa^{2,3}, Hisashi Haga^{2,3}, Shinya Tanaka^{3,4,5} and Jian Ping Gong^{2,3,5,*}

¹Graduate School of Life Science, Hokkaido University, N21W11, Kita-ku, Sapporo, Hokkaido 001-0021, Japan

²Faculty of Advanced Life Science, Hokkaido University, N21W11, Kita-ku, Sapporo, Hokkaido 001-0021, Japan

³Global Institution for Collaborative Research and Education (GI-CoRE), Hokkaido University, Hokkaido 001-0021, Japan


⁴Department of Cancer Pathology, Faculty of Medicine, Hokkaido University, N15W7, Kita-ku, Sapporo 060-8638, Japan

⁵Institute for Chemical Reaction Design and Discovery (WPI-ICReDD), Hokkaido University, N21W10, Kita-ku, Sapporo 001-0021 Japan

*Corresponding author

Name / E-mail address / ORCID iD

Martin Frauenlob	martinfrauenlob@sci.hokudai.ac.jp	0000-0001-7460-9378
Daniel R. King	dking@sci.hokudai.ac.jp	0000-0002-1377-5556
Honglei Guo	hlguo@sci.hokudai.ac.jp	0000-0002-1610-8521
Seiichiro Ishihara	sishihara@sci.hokudai.ac.jp	
Masumi Tsuda	tsudam@med.hokudai.ac.jp	
Takayuki Kurokawa	kurokawa@sci.hokudai.ac.jp	0000-0001-6834-684X
Hisashi Haga	haga@sci.hokudai.ac.jp	
Shinya Tanaka	tanaka@med.hokudai.ac.jp	
Jian Ping Gong	gong@sci.hokudai.ac.jp	0000-0003-2228-2750

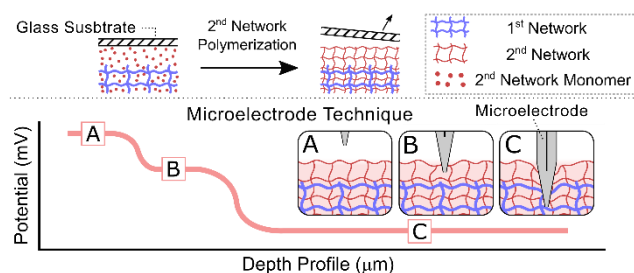

Abstract

The hydrogel chemical structure at the gel-solution interface is important towards practical use, especially in tough double network (DN) hydrogels that have promising applications as structural biomaterials. In this work, we regulate the surface chemical structure of DN hydrogels and the surface-bulk transition by the molding substrate used for the synthesis of the 2nd network. To characterize the surface and bulk structure, we combined ATR-FTIR and a newly developed microelectrode technique that probes the electric potential distribution within a hydrogel. We found that the polymerization on a repulsive substrate leads to the formation of a thin layer of 2nd network on the surface of DN hydrogels, which makes the surface different from the bulk. By controlling the 2nd network polymerization conditions and molding substrate, the surface-bulk transition region can be regulated, so that either only the 2nd network or both networks are present at the DN hydrogel surface. Through these findings we gained a new insight on the structure formation at the DN hydrogel surface, and this leads to easy regulation of the hydrogel surface structure and properties.

Introduction

The double network (DN) concept gave rise to hydrogels with rubber-like strength and toughness and inspired the development of novel hydrogel materials for potential applications in industrial^{1–3} and medical fields^{4–6}. DN hydrogels have structural similarities to living soft matter, and they therefore have received attention for use as cell scaffolds^{7,8}, implants^{9,10} and anti-adhesive membranes^{11,12}. For such applications in wet environments, understanding and controlling the surface physicochemical properties of DN hydrogels is crucial.

A typical DN hydrogel owes its high strength and toughness to the contrasting architecture of the two interpenetrating networks: a rigid and brittle 1st network, acting as sacrificial bonds, and a soft and stretchable 2nd network as its interpenetrating counterpart, synthesized in a two-step polymerization approach^{13–16}. To obtain the contrasting architecture, a DN hydrogel is usually made from a densely crosslinked polyelectrolyte as the 1st network and a sparsely crosslinked neutral polymer as the 2nd network. Driven by the high osmotic pressure of the counter-ions, the polyelectrolyte network substantially swells in the aqueous precursor solution of the 2nd network, reaching a rigid and brittle state, while the 2nd network, formed in the presence of the first network, can hardly swell due to the constrain of the already highly swollen first network, reaching a soft and stretchable state. Hydrogels made from polyanions such as poly(acrylic acid), poly(sodium p-styrene sulfonate), poly(2-acrylamido-2-methyl-propane sulfonic acid) (PAMPS) and PAMPS – sodium salt, have shown many unique properties, including low sliding friction on glass substrates in water, the adsorption of proteins and platelets, known as biofouling, and cell attachment^{17–19}. However, after introduction of the 2nd neutral network in such polyelectrolyte hydrogels to create a DN hydrogel, these properties change remarkably, so that cells hardly attach to the DN hydrogel^{20–22}. Yet, evidence suggests that DN hydrogels from PAMPS and poly(dimethylacrylamide) have therapeutic potential by inducing in vivo articular cartilage regeneration^{23,24}, in which the surface physicochemical properties of the DN hydrogels should play an important role in the initial cell adhesion^{25,26} or morphology^{27,28}. Understanding and regulating cell-hydrogel interactions are among the most challenging problems in

bioengineering, and are affected by hydrogel characteristics including charge density²⁹, water content³⁰, hydrophilicity³¹ and mechanical properties³².

In the case of DN hydrogels, it could be argued that cells do not adhere, but do so on the corresponding single network (SN) polyelectrolyte hydrogel, because the concentration of the electrically neutral 2nd network, is already high enough to weaken the surface charge sufficiently^{33–35}. Another reason might relate to the two-step synthesis approach and the interactions between the substrate material and the 1st network hydrogel³⁶. We consider that the surface of the DN hydrogels are sensitive to the two-step polymerization approach and the interaction between the 1st network and the wall of the molding substrate used to synthesize the 2nd network. In the case of a polyelectrolyte hydrogel, at the hydrogel-solution interface, an electric double layer is formed based on the balance of attraction of mobile counter-ions and repulsion of mobile co-ions to the immobile ions of the polyelectrolyte network. As a result, there is an electric potential difference between the polyelectrolyte hydrogel and the solution^{37,38}. The intensity of the electric potential of the hydrogel in relation to the solution depends on the ionic strength of the solution and the immobile charge density of the hydrogel³⁹. Such electric double layer is the origin of repulsion between two like-charged polyelectrolyte hydrogels. When two like-charged surfaces are forced to approach each other, an osmotic repulsion is generated between them to avoid an overlap of the electric double layers of the two surfaces and a liquid film is formed at the interface⁴⁰. Due to the existence of the liquid film as lubricant, two like-charged polyelectrolyte hydrogels show low sliding friction under water^{41,42}.


The above results suggest that the surface of a DN hydrogel could be regulated by the molding substrate used for synthesizing the 2nd network. When a polyanion is used as the 1st network and a negatively charged substrate is used as mold, a thin hydrogel layer of the 2nd network should be formed on the surface of the DN hydrogel. In contrast, if a hydrophobic mold is used, to which the 1st network is adhesive, no thin hydrogel layer of the 2nd network will be formed on the DN gel surface. In this work, we synthesized DN hydrogels from PAMPS as the 1st network and polyacrylamide (PAAm) as the 2nd network in a modified two-step synthesis approach. To regulate the surface-bulk transition we used

substrates of low (silicone coated polyethylene, Si-PET) and high (borosilicate glass substrate) surface energy in the 2nd network polymerization step (Scheme 1A). On the low surface energy substrate, we predict the adhesion of the 1st network to the substrate through hydrophobic interactions resulting in a DN hydrogel (DN/Si-PET) with 1st and 2nd network present at the surface. On the borosilicate glass mold that also carries negative charges on its surface, however, we assume that a PAAm layer forms (DN/Glass) because of the electrostatic repulsion between the PAMPS and the glass. As the thickness of the liquid layer at the repulsive interface is determined by the balance of the ionic osmotic pressure and the normal pressure applied, we tried to regulate the surface layer thickness through applying normal compression to the glass and PAMPS hydrogel in the 2nd network polymerization (DN/Glass-C, Figure S5A).

It is challenging to analyze the heterogeneous DN hydrogel structure, especially if it differs between the surface and the bulk. First, in swollen state, the water molecules and hydrogen bonds absorb a large bandwidth of electromagnetic waves, rendering spectroscopy techniques ineffective⁴³. Second, common electric potential characterization methods such as ζ -potential measurements, used to determine hydrogel charges, are not capable of analyzing a structure-related charge difference between the surface and bulk of the hydrogel⁴⁴. To overcome these difficulties, we adopted a recently developed method that provides a new perspective on the charge distributions in hydrogels, called the microelectrode technique (Scheme 1B)⁴⁵. By inserting a microelectrode into the hydrogel and recording the electric signal in accordance to the electrode penetration velocity, an electric potential-depth profile of the hydrogel is generated, which reveals the charge density distribution inside of the hydrogel. Here in this study we deployed attenuated total reflectance Fourier-transform infrared spectroscopy (ATR FT-IR) and the microelectrode technique to characterize the surface and bulk structure of the DN hydrogels. ATR FT-IR provides surface structure information while the microelectrode technique is a highly sensitive method giving a depth profile with a low spatial resolution of the microelectrode diameter (~200 nm). Using these two complementary methods, we

can characterize the surface layer structure and the surface-bulk transition of the hydrogels (Scheme 1C).

Ultimately, we identified that modulating the 2nd network polymerization condition regulates the surface-bulk transition and allows us to switch-on or switch-off the cell adhesive properties on DN hydrogels. By modifying the two-step DN hydrogel synthesis approach we provide an easily accessible opportunity to design tough hydrogels with functional surface charge transitions, which are useful in cell scaffolding and in vivo applications.

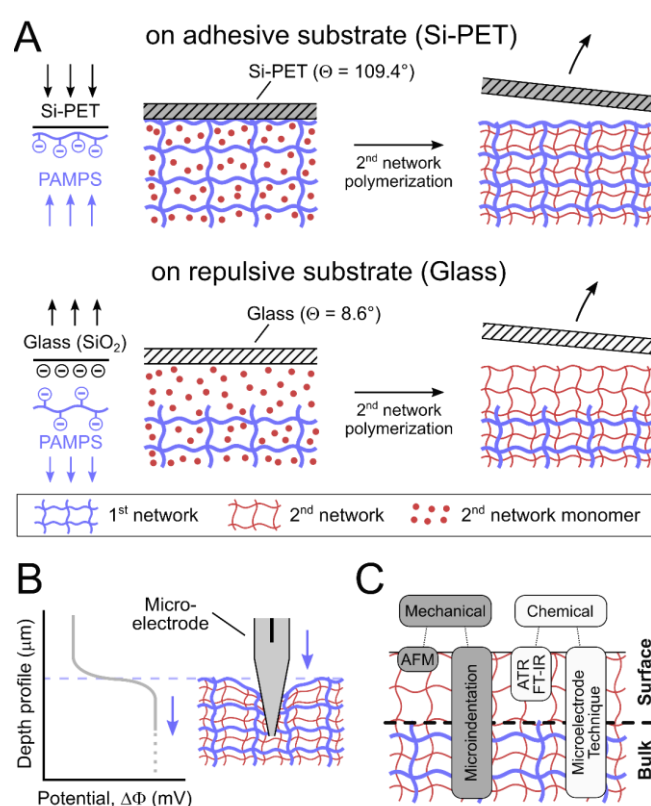

Scheme 1: Strategy to regulate and to analyze the surface-bulk transition of DN hydrogels by using different molds for second network synthesis. (A) DN hydrogels synthesized on the hydrophobic substrate (Si-PET) have surfaces containing both polymer networks due to adhesion of the 1st network on the substrate. DN hydrogels synthesized on the glass substrate are covered with a thin layer of 2nd network polymer due to the osmotic repulsion between the negatively charged glass and the 1st network. (B) The microelectrode technique measures the electric potential of the hydrogel depth profile (blue dotted line represents the hydrogel-solution interface). (C) Summary of the deployed mechanical and chemical characterization methods used to analyze the surface-bulk transition of DN hydrogels.

Experimental Section

Materials

The 1st network monomer 2-acrylamido-2-methylpropanesulfonic acid (AMPS) (Toagosei Co., Ltd., Japan) was used as received. The 2nd network monomer acrylamide (AAM), crosslinker N,N'-methylenebis(acrylamide) (MBAA) and initiator 2-oxoglutaric acid were used as obtained from Wako Pure Chemical Industries, Ltd., Japan. The molding surfaces for the 2nd network polymerization, such as borosilicate glass substrate (Asahi Glass Co., Ltd., Japan), were heat treated at 500 °C for 2 hours prior to use and silicone coated polyethylene film (Si-PET), SP-PET-03-38-Bu (Mitsui Chemicals Tohcello. Inc., Japan) was used as purchased. Unless otherwise noticed, all chemicals and solvents used in cell culture were purchased from Sigma-Aldrich Inc, United States. The human mesenchymal stem cell (MSC) line derived from umbilical cord blood (UCB) (JCRB1110 UCB408E6E7TERT-33) was obtained from the Japanese Collection of Research Bioresources Cell Bank (JCRB Cell Bank, Japan).

Surface energy of molding substrates

To characterize the surface energy of the molding substrates used in the 2nd network polymerization step, the static water contact angles (Θ) of the glass substrate and the Si-PET film were measured with double distilled water (ddH₂O, droplet volume 2 μ L) on a Drop Master 300 (Kyowa Interface Science Co., Ltd.). The contact angle images are found in the supplementary information in Figure S1.

Single and double network hydrogel synthesis

The DN hydrogel synthesis was modified from Gong et.al⁴⁶ and sample codes and formulations are found in Table 1. Briefly, in the first step, aqueous precursor solutions of AMPS monomer (C_{M1}), crosslinker MBAA (X_{X1}) and initiator 2-oxoglutaric acid (X_{I1}) were poured into glass molds with a spacer thickness of 0.5 to 2 mm (h_0) and free-radical polymerization was initiated by irradiated of 365 nm UV light in argon atmosphere (2.5 mbar) for 8 hours to obtain 1st network PAMPS hydrogels. This first

polymerization process was followed by 3-day immersion of the freshly synthesized hydrogels in the 2nd network precursor solution composed of AAm monomer (C_{M2}), crosslinker MBAA (X_{X2}) and initiator 2-oxoglutaric acid (X_{I2}). In the second step, the PAMPS hydrogels soaked in the 2nd network precursor solution, were sandwiched between glass plates (hereafter referred as DN/Glass) or Si-PET film (referred as DN/Si-PET) and compressed by 0.1 – 0.3 kPa. For the DN sample group DN/Glass-C, the PAMPS hydrogels were sandwiched between glass plates and compressed by 50 kPa (Figure S5A). For the thickness gradient DN hydrogels, the PAMPS hydrogel was sandwiched between glass plates in a mold with a gradual increase in spacer thicknesses (Scheme S1). The hydrogel-mold assemblies were incubation in the argon atmosphere for 1 hour, and the 2nd network was polymerized within the PAMPS network by UV irradiation for 8 hours.

Single network (SN) hydrogels corresponding to the 1st or 2nd network were synthesized in a similar manner to the 1st network polymerization of DN hydrogels from aqueous solutions of either AMPS or AAm monomer with various crosslinker densities of MBAA. Prior to hydrogel characterization, the synthesized SN and DN hydrogels were equilibrated in double distilled water (ddH₂O) for at least for 7 days.

Table 1: Hydrogel sample codes and formulations

Sample code	PAMPS - 1 st network			PAAm - 2 nd network		
	Monomer	Crosslinker*	Initiator*	Monomer	Crosslinker*	Initiator*
	C_{M1} (M)	X_{X1} (mol%)	X_{I1} (mol%)	C_{M2} (M)	X_{X2} (mol%)	X_{I2} (mol%)
PAMPS (C_{M1} - X_{X1} - X_{I1})	1	1.5, 2, 3, 5, 9	1	-	-	-
PAAm (C_{M2} - X_{X2} - X_{I2})	-	-	-	2	0.1 – 4	0.1
DN(C_{M1} - X_{X1} - X_{I1} / C_{M2} - X_{X2} - X_{I2})	1	1.5, 2, 3, 5, 9	1	2	0.1	0.1

*mol% of X_{X1} , X_{I1} and X_{X2} , X_{I2} are relative to the amount of C_{M1} and C_{M2} , respectively.

Hydrogel swelling and polymer weight fraction

The bulk volumetric swelling degree of PAMPS hydrogels, $Q = (h/h_0)^3$, was determined from the thickness of PAMPS hydrogels swollen in double distilled water (ddH₂O) or 2nd network precursor solution (h), and that in the as-prepared-state (h_0) after polymerization. The polymer weight fraction, W_{M1} and W_{M2} (wt%) of SN hydrogel was determined by the gravimetric wet (m)/dry (m_0) ratio ($\times 100$)

of hydrogel equilibrated in ddH₂O (m), and after vacuum oven drying procedure at 75°C and reduced pressure of 1 bar for at least 2 days (m_0).

Polymer surface density via ATR/FT-IR

To analyze polymer surface density of the 1st and 2nd network at the SN and DN hydrogel surface, attenuated total reflection Fourier transform infrared spectroscopy (ATR/FT-IR) on a FT-IR 6600 spectrometer (Jasco, Japan) with diamond prism was performed. Prior to analysis, hydrogel discs were immersed in D₂O for 12 h and hydrogel spectra were measured in full contact with the prism for wavenumbers of 1800 – 800 cm⁻¹, at 16x accumulation and resolution of 2 cm⁻¹. Absorbance maxima⁴⁷, (A_{max}) of the characteristic sulfonic group peak ($\nu_{S=O}$) of PAMPS at 1042 cm⁻¹, and carbonyl group peak ($\nu_{C=O}$) for PAAm at 1640 cm⁻¹ were determined using the manufacturers software. Since infrared absorption peak height resembles polymer surface density, a calibration curve that relates IR absorption peak height and polymer weight fraction of SN hydrogel allows the detection of 1st and 2nd network at the DN hydrogel surface (Table S1, Figure S3, Figure S4). Since the gels slightly swelled in deuterium oxide compared to water, the relative swelling ratio (Q_r) was used as a correction factor for the polymer surface density calibration. The $Q_r = (h_{H_2O}/h_{D_2O})^3$ was determined by the hydrogel thickness in ddH₂O (h_{H_2O}) relative to thickness in deuterium oxide (h_{D_2O}), (Figure S4). Polymer surface densities were expressed as weight fractions and as PAMPS to PAAm molar concentration ratio, C_{M1}/C_{M2} (M/M).

Depth profiling via microelectrode technique

The surface layer thickness (t) at which the hydrogel structure transitions from the surface to bulk was evaluated by a microelectrode insertion technique previously described⁴⁵. Here the thickness is based on the displacement of the microelectrode moving at a constant speed and the shift in electric potential ($\Delta\Phi$) due to the relative change in the local small ion concentration. Equilibrated in 10⁻⁴ M NaCl solution, hydrogels were probed with a microelectrode made from a glass capillary with a fiber filament (outer diameter = 180 nm, inner diameter = 128 nm) fabricated with a P-1000 capillary puller (Sutter Instrument Co., U.S.), at an insertion speed of 0.5 – 2 μ m/s. Firstly the surface electric potentials

($\Delta\Phi_s$) were estimated from the 1st derivative of the electric potential curves and secondly the peak distance measured from the first valley to the last hill of the 2nd derivative was used to estimate the surface layer thickness (t) of hydrogels (Figure S2). The 1st and 2nd derivative curves were processed via smoothing and y-axis scaling in Origin (OriginLab Corp.) software. The Debye length of the bath solution (10^{-4} M NaCl) is 30.4 nm⁴⁵.

Mechanical characterization of hydrogels

The surface elastic modulus ($E_{Surface}$) was tested on an atomic force microscope (AFM, Nanowizard 4, Bruker, U.S.) mounted to an inverted microscope (Nikon Eclipse TE 300, Japan) in aqueous conditions at 25°C. The spring constants of 0.079 - 0.083 N/m were obtained by thermal tuning prior to each 4 x 4 force-distance curve array in force mapping-mode on the SFM (QITM - mode) for the used pyramid shaped cantilever (A triangular, MLCT series, Bruker, U.S.). The peak force setpoint was normalized to 0.2 nN. The bulk elastic modulus (E_{Bulk}) was determined by indentation method using a tensile-compressive mechanical tester (Autograph AG-X, Shimadzu Co., Japan) in air at 25°C. A sphere-shaped micro-indenter ($r = 250$ μ m, material: stainless steel) probed the hydrogel at a deformation velocity of 250 μ m/min. By applying the Hertzian model⁴⁸ for rigid sphere indenters, with an assumed Poisson's ratio for the hydrogels of 0.5 the elastic modulus (E) was estimated from the AFM and micro-indentation loading curves.

Hydrogel cross-section structure observation

The swollen DN hydrogel sample with a surface layer thickness gradient was frozen in liquid N₂ and fractured to expose the cross section and freeze-dried (Advantage XL-70, VirTis freeze dryer). After gold sputtering (E-1010, Hitachi, Japan), the structure of the hydrogel cross-section was analyzed on a scanning electron microscope (SEM, JSM-6010LA, JEOL Ltd., Japan).

230 *In vitro* cell culture and morphology

231 Hydrogel membranes were equilibrated and sterilized in HEPES-buffer and then incubated in culture
232 medium overnight. The Dulbecco's modified Eagle's culture media was supplemented with 10% fetal
233 bovine serum (Thermo Fisher Sci.), 1% Penicillin/Streptomycin and 1% L-glutamine. The mesenchymal
234 stem cells were expanded on polystyrene dishes prior to cell seeding on hydrogel membranes. On day
235 0, trypsinized single-cell suspensions of stem cells were tested by trypan blue dye live/dead exclusion.
236 Cell cultures with a viability over 95% were seeded onto hydrogel membranes at a concentration of 1
237 $\times 10^5$ cells/mL and incubated for 3 days at 37°C and 5% CO₂ in humidified atmosphere. Cell cultivation
238 was stopped on day 3 and cell morphologies were imaged through phase-contrast microscopy
239 (OLYMPUS - IX73, Japan).

240

Results and Discussion

Chemical and mechanical properties of the surface-bulk transition region

First, we characterized the surface chemical compositions of DN hydrogels prepared on different substrates using ATR/FT-IR which reveals the chemistry of the topmost surface of the hydrogels. PAMPS has a sulfonic group and PAAm has an amide carbonyl group (Figure 1A) that can be characterized by ATR/FT-IR. On the absorption spectra (Figure 1B), a sharp peak at 1042 cm^{-1} , characteristic for the sulfonic group ($\nu_{\text{S=O}}$) of the PAMPS network, and a strong sharp absorption peak around 1640 cm^{-1} , from the primary amide carbonyl group ($\nu_{\text{C=O}}$) of PAAm, were observed on the spectra for the SN PAMPS (1-3-1) gel and PAAm (2-0.1-0.1) gel, respectively. On the PAMPS hydrogel, a peak at 1640 cm^{-1} is also observable since the molecular structure of PAMPS contains a primary amide carbonyl group ($\nu_{\text{C=O}}$). However, the signal is much weaker compared to PAAm and therefore it is neglectable. The spectrum of the DN/Si-PET, exhibits both strong absorption peaks at 1042 cm^{-1} for the sulfonic group and at 1640 cm^{-1} for the primary amide carbonyl group, while the DN/Glass hydrogel only exhibits absorption at 1640 cm^{-1} due to the amide carbonyl group. These ATR/FT-IR results indicate that both PAMPS and PAAm are present on the surface of the DN/Si-PET hydrogel while only the 2nd network PAAm is present on the surface of the DN/Glass hydrogel. Based on this analysis, we infer that there is a surface layer of PAAm on the DN/Glass hydrogel.

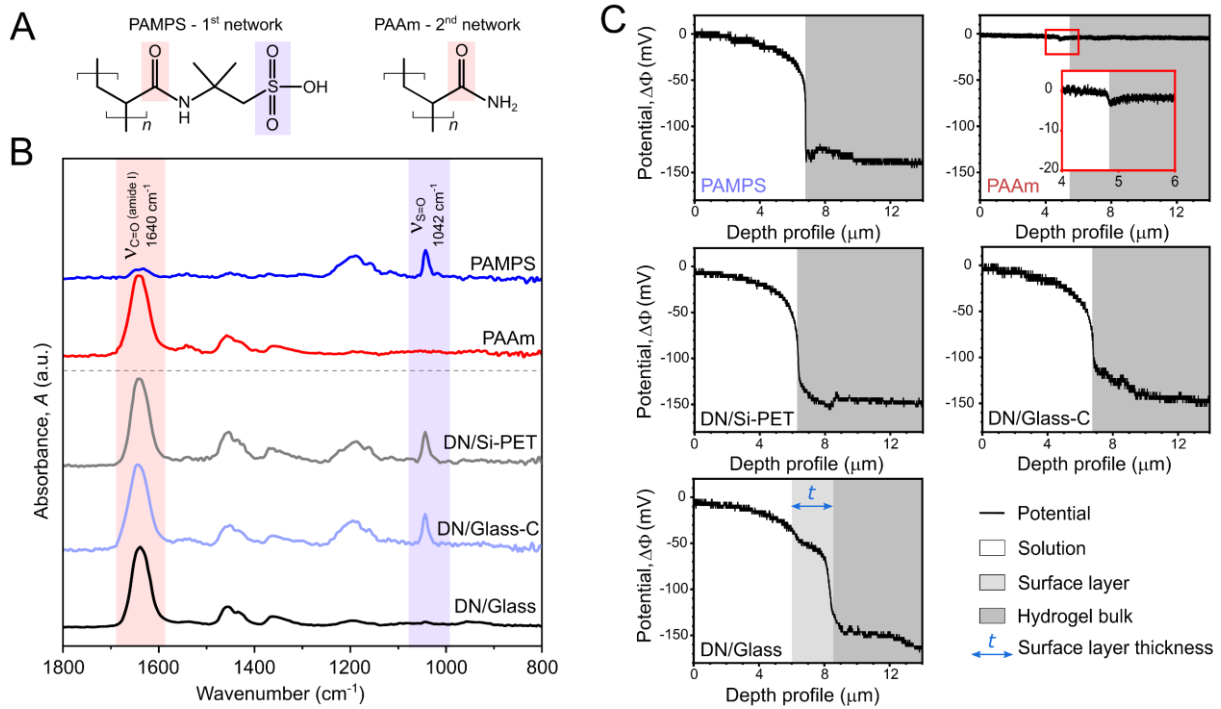


Figure 1: Analysis of the surface structure of DN hydrogels where the 2nd network was synthesized on different substrates. (A) The molecular structures of the 1st and 2nd network polymers. The red and blue background represent the IR bond absorptions, used to characterize the hydrogels. (B) The ATR/FT-IR absorption spectra and (C) the electric potential depth profiles ($\Delta\Phi$) of SN PAMPS (1-3-1), SN PAAm (2-0.1-0.1) and corresponding DN hydrogels (1-3-1/2-0.1-0.1) synthesized on Si-PET (DN/Si-PET) and glass substrates (DN/Glass), and on glass under compression (DN/Glass-C, Figure S5).

To characterize the thickness of the surface layer on the DN/Glass hydrogel, we probed the depth profile of the electric potential near the surface of the hydrogels by the microelectrode technique. A charged hydrogel generates an electric potential ($\Delta\Phi$) relative to the bath aqueous solution due to the Donnan effect⁴⁹.

$$\Delta\Phi = - \frac{2.3RT}{zF} \log \left(\frac{C_g}{C_s} \right) \quad (1)$$

Here, C_g and C_s are the mobile counter-ion concentrations in the hydrogel and in the bath solution, respectively. z is the valence of the mobile counter-ion, F the Faraday constant, R the gas constant, and T the absolute temperature. The covalent bound ions on the polymer network guide the mobile counter-ion concentration to keep neutrality in a thermodynamic equilibrium state. As a result, by probing the local electric potential, we can detect the local structure of the hydrogel. For the PAMPS hydrogel, that carries immobile negative charges on the polymer network, the potential shifts to a negative value relative to the bath solution since the hydrogel traps high numbers of positively charged

mobile ions (z is positive), while the PAAm hydrogel has almost zero potential since its polymer network carries a negligible amount of charge. Accordingly, we can probe the surface layer thickness of the DN/Glass hydrogels via the electric potential depth profiling.

As shown in Figure 1C, the microelectrode, inserted into a SN PAMPS hydrogel, measures an initial gradual drop of electric potential until the displacement of $6.8\ \mu\text{m}$, which is followed by an abrupt drop to a large negative value of $-150\ \text{mV}$. The initial potential drop is due to the deformation before the penetration of the electrode into the hydrogel. Like the piezoelectric effect, the compression at the probe tip increases the local polymer charge density and decreases the electric potential. The large potential shift ($\Delta\Phi$) to $-150\ \text{mV}$ indicates that a high amount of Na^+ ions ($z = +1$) are deployed as counterions to neutralize the fixed negative charges of the sulfonic groups of PAMPS. In contrast, only a very small potential shift of $-4\ \text{mV}$ is measured for the neutral SN PAAm hydrogel. The potential depth profile of the DN/Si-PET hydrogel, where the 2nd network was synthesized on adhesive Si-PET (contact angle to ddH₂O $\Theta = 109.4 \pm 0.8^\circ$, Figure S1), shows an immediate drop of the potential to $-150\ \text{mV}$ after the initial drop coming from the compression before electrode penetration, indicating the absence of the surface layer, in good agreement with the ATR/FT-IR result.

In contrast, the depth profiles of the DN/Glass hydrogel (1-3-1/2-0.1-0.1), where the 2nd network was synthesized on repulsive glass (contact angle to ddH₂O, $\Theta = 8.5 \pm 1.5^\circ$, Figure S1), also shows an initial drop of electric potential to a probe displacement of $6.1\ \mu\text{m}$, like the SN PAMPS hydrogel before the probe penetration to the hydrogel. Different from the profile of the SN PAMPS hydrogel, a small hump with a change in potential of $-50\ \text{mV}$ appears at the displacement of $6.1\ \mu\text{m} \sim 8.5\ \mu\text{m}$, indicating the presence of a weakly charged surface layer. At a displacement larger than $8.5\ \mu\text{m}$, the potential shifts drastically to $-150\ \text{mV}$, indicating the transition from the surface layer to the bulk material composition of PAMPS/PAAm because the shift intensity is like that of the corresponding PAMPS SN hydrogel. From the 2nd derivative of the depth profile, a surface layer of thickness $t = 2.23\ \mu\text{m}$ on the DN/Glass hydrogel was determined (Figure S2).

The microelectrode results reveal the presence of a surface layer on the DN/Glass hydrogel while no surface layer is formed on the DN/Si-PET hydrogel. These results are consistent with the ATR/FT-IR results. However, the microelectrode method reveals that the surface layer on the DN/Glass hydrogel has a larger electric potential (-50 mV) than that of the corresponding PAAm hydrogel (-4 mV), indicating that the surface layer of the DN/Glass hydrogel is not pure PAAm, which is not consistent with the ATR/FT-IR measurement that shows no signal from PAMPS. This discrepancy is due to the relatively poor sensitivity of the ATR/FT-IR. From the potential shift of -50 mV in relation to the bath solution containing 10^{-4} M NaCl, the concentration of mobile Na^+ ion in the surface layer of the DN/Glass gel is estimated as 7×10^{-4} M by using Equation 1. The presence of this excess number of mobile ions in the surface layer of the DN/Glass hydrogel suggests that a very small amount of AMPS monomers, as residue from the 1st network synthesis, of 7×10^{-4} M in concentration, is copolymerized in the 2nd PAAm polymerization to form a copolymer. Such a small amount of AMPS in the surface layer of the DN/Glass could not be detected by the ATR/FT-IR method that has a lower detection limit for PAMPS of 9.4×10^{-4} M (Figure S3).

The PAAm surface layer formation on the DN/Glass hydrogel is presumably caused by the counter ions osmotic repulsion between negatively charged PAMPS hydrogel and the glass substrate during the 2nd network polymerization. To verify the hypothesis, we tried to eliminate the surface layer by applying compression (50 kPa) to the 1st network hydrogel during the synthesis of the 2nd network to counteract the osmotic repulsion (Figure S5A). The ATR/FT-IR spectra show both peaks from PAAm (1640 cm^{-1}) and PAMPS (1042 cm^{-1}) (Figure 1B), indicating no surface layer formation on the DN/Glass-C hydrogel. The electric potential depth profile also confirms no surface layer formation. These results demonstrate that we can switch on or off the surface layer of DN gels by either substrate chemistry or compression during the 2nd network polymerization.

We further analyzed the surface structure and modulus, in comparison with the bulk quantities for DN/Glass, DN/Si-PET and DN/Glass-C hydrogels synthesized by different formulations, and the results are summarized in Figure 2 and 3. Figure 2A shows that the polymer surface density of SN PAMPS and

SN PAAm hydrogels increases with the crosslinking degree (X_{x1} , X_{x2}), due to the decrease of the
 volumetric swelling degree (Q) at increased crosslinking degree. The polymer densities can be tuned
 in a range of 0.2 ~ 4.5 wt% and 4.2 ~15.2 wt% for PAMPS (W_{M1}) and PAAm (W_{M2}), respectively, by
 adjusting the crosslinking degree. Due to its polyelectrolyte nature, the swelling degree of PAMPS
 hydrogels is much higher than that of the neutral PAAm hydrogels even at a high crosslinking degree.
 The swelling degree of PAMPS in 2nd network precursor solution is almost the same to that of PAMPS
 in water because the AAm monomer is neutral³⁸.

The changes in surface polymer density and electric potential of DN gels in accordance to the 1st
 network crosslinking degree (X_{x1}) is shown in Figure 2B. On DN hydrogels, the PAMPS surface densities
 (W_{M1}) between DN/Glass, DN/Si-PET and DN/Glass-C is different because of the presence or absence
 of the surface layer (upper left side). As the 1st network crosslinking (X_{x1}) increases, the PAMPS surface
 densities of DN/Si-PET and DN/Glass-C hydrogels increased, in agreement with that of the SN PAMPS
 hydrogel. However, on the DN/Glass hydrogel surface, the PAMPS density is below a weight fraction
 of 1 wt% regardless of the change in the X_{x1} for the whole crosslinking range. The PAAm surface density
 on DN/Si-PET and DN/Glass-C hydrogels slightly increases with increasing PAMPS network crosslinking
 (X_{x1}), though the amount of crosslinker for the PAAm network for all DN hydrogels was kept constant
 (X_{x2} : 0.1 mol%). However, on the DN/Glass hydrogel, the PAAm surface density is higher than that of
 the DN/Si-PET and DN/Glass-C hydrogels, showing almost a constant value, independent of the change
 in X_{x1} . The increase in the PAAm density with X_{x1} on DN/Si-PET and DN/Glass-C gels is because the
 swelling of the PAAm is constrained by the presence of PAMPS. The higher the X_{x1} of the 1st network,
 the more the PAAm network is constrained¹⁵. The surface molar ratio of PAMPS to PAAm (C_{M1}/C_{M2})
 increases with the increase in the 1st network crosslinking degree for DN/Si-PET and DN/Glass-C gels
 while it keeps a low but constant value for DN/Glass gels (Figure 2B, lower left side). By cutting the
 surface hydrogel we exposed the bulk material so that a comparison between the surface and the bulk
 molar ratio C_{M1}/C_{M2} is possible (Figure 2B, upper right side). While the bulk values were in good
 agreement with the theoretical values, the surface molar ratio C_{M1}/C_{M2} is about 2 times higher than

the bulk values. The theoretical values were estimated from, $C_{M1}/C_{M2} = Q^{-1}C_{M1}/C_{M2}$, where C_{M1} and C_{M2} are the feed monomer concentrations of the 1st network and the 2nd network, respectively, and Q is volumetric swelling degree of PAMPS hydrogels in AAm solution. The high molar ratio on the surface compared to the bulk probably originates from the faster polymerization of the PAMPS hydrogels near the glass substrates in relation to the central region due to the higher UV intensity at the surface regions. The increase in the amount of crosslinker (X_{X1}) reduces the swelling of the PAMPS hydrogel in the 2nd network precursor solution and consequently increases the number of negative charges through the PAMPS density. Therefore, the electric surface potential ($\Delta\Phi_s$), defined as the initial drastic potential drop at the hydrogel surface (Figure S2), of the DN/Si-PET and DN/Glass-C hydrogels increased up to a value of -180 mV at 9 mol% crosslinker (X_{X1}), with a molar ratio C_{M1}/C_{M2} of 0.2 (Figure 2B, lower right side). Similar increase in surface electric potential was published previously, when crosslinker density increased in SN PAMPS hydrogels⁴⁵. The DN/glass hydrogel reaches a value of -75 mV at 9 mol% crosslinker (X_{X1}) and is arguably related to the increased incorporation of unreacted AMPS because of a low conversion rate in the polymerization of highly crosslinked PAMPS.

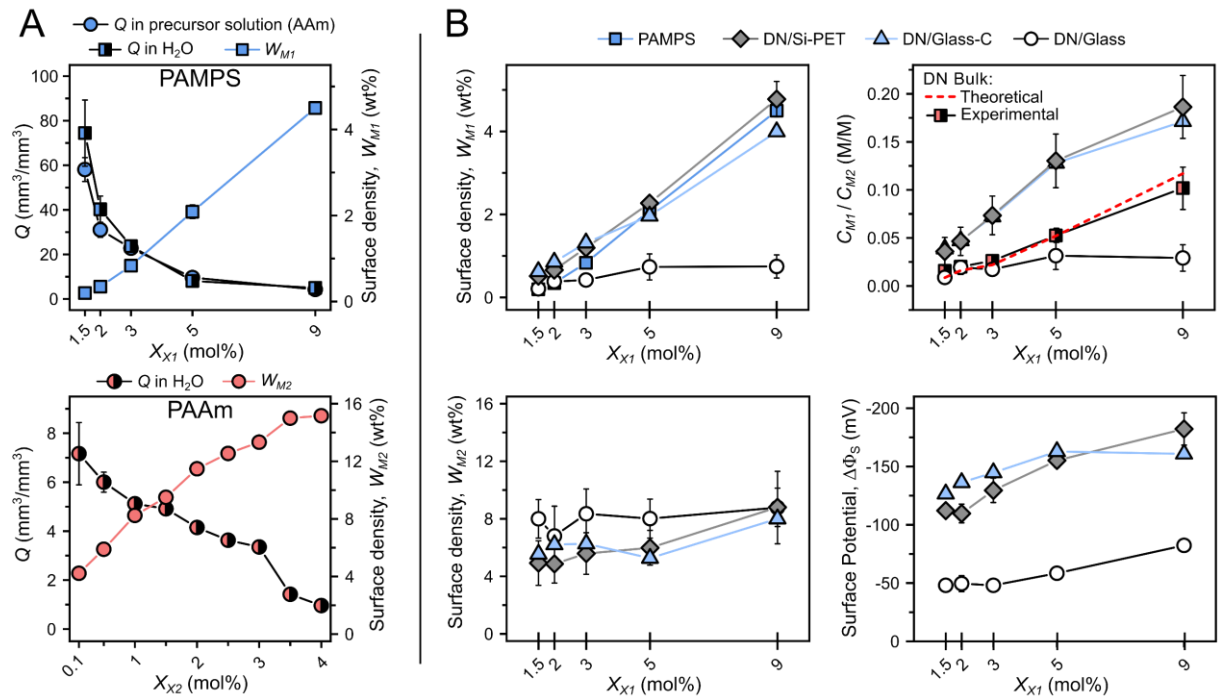


Figure 2: Regulation of polymer surface density (W_{M1} , W_{M2}) by crosslinking degree (X_{X1} , X_{X2}) of the first network. (A) The volumetric swelling degree (Q) and the corresponding surface polymer density (W_{M1} , W_{M2}) of SN PAMPS and PAAm hydrogels (mean $\pm$ SD, $n = 3$ hydrogels per symbol) for varied crosslinking degree (X_{X1} , X_{X2}). (B) DN hydrogel surface polymer density (W_{M1} , W_{M2}), the corresponding

molar concentration ratio (C_{M1}/C_{M2}), and the surface potential ($\Delta\Phi_s$) for DN gels prepared with various 1st network crosslinking degree (X_{X1}) (mean $\pm$ SD, sample groups SN PAMPS, DN/Si-PET, DN/Glass contained sample sizes of $n = 3 - 6$ hydrogels per symbol, and for DN/Glass-C $n = 1$ hydrogel per symbol). The standard deviations (SD) of the PAAm density values tend to be high because the low accuracy of the ATR/FT-IR data used for the quantitative analysis resulted in a poorly fitted calibration curve (Figure S3, Figures S4).

As Figure 3A demonstrates, in the case of DN/Glass hydrogels the surface layer thickness is between 3 - 4 μm for different X_{X1} . Because of the presence of the surface layer, the elastic modulus at the surface is lower than the bulk in the case of the DN/Glass hydrogel, and only weakly increased with X_{X1} . However, the bulk modulus of the DN/Glass hydrogel increases with increasing 1st network crosslinking (X_{X1}), showing the same values as the bulk elastic modulus of DN/Si-PET hydrogels. For SN PAMPS and DN/Si-PET hydrogels, the surface and the bulk elastic modulus both increase with X_{X1} .

From the above results, we can tune the bulk modulus while keeping the same surface chemistry. As shown in Figure 3B, when the bulk elastic modulus of DN/Glass and DN/Si-PET was changed through the 1st network crosslinking degree, the polymer surface densities evolved differently, depending on the presence or absence of the surface layer. When no surface layer is present, the chemical structure at the surface is controlled through the PAMPS/PAAm ratio and the swelling in the 2nd network precursor solution. However, when there is a surface layer, the surface chemical structure depends on the formulation of the 2nd network precursor solution and is independent of the bulk elastic modulus. As shown for the SN PAAm hydrogels, polymer surface density and modulus increase with crosslinking density X_{X2} . By varying X_{X1} and X_{X2} of the DN/Glass hydrogel, it is possible to individually tune the surface layer polymer density (or modulus) and the bulk polymer density (or modulus).

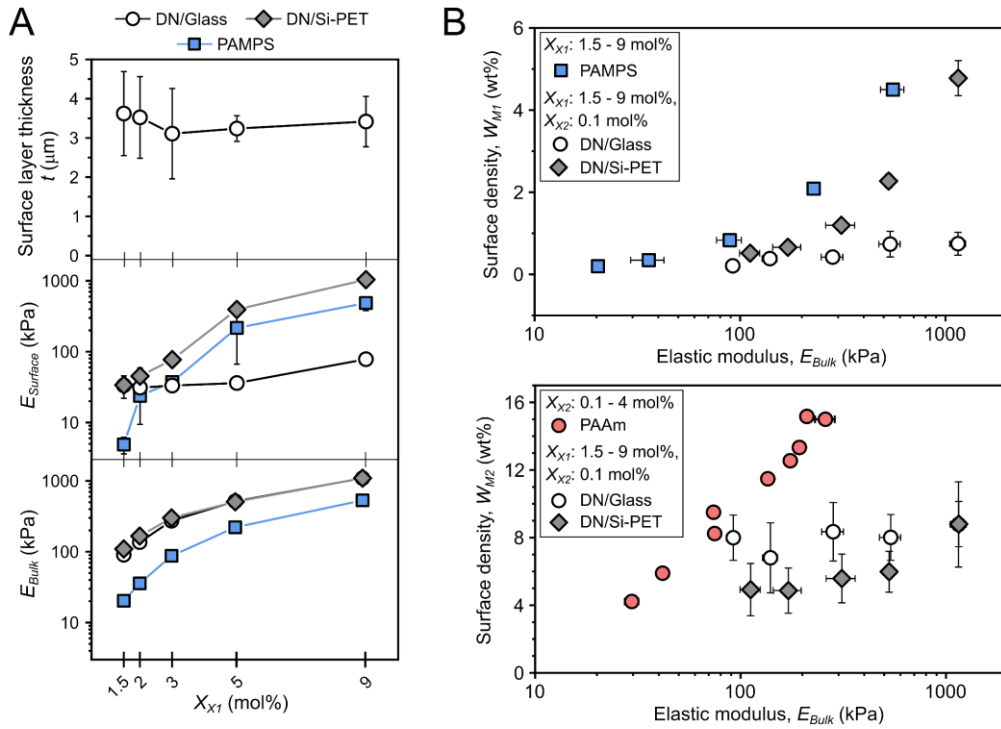


Figure 3: Effect of Surface layer thickness on elastic modulus. (A) The surface layer of 3 – 4 μm thickness (t) on the DN/Glass hydrogel affects the elastic modulus at the surface (E_{Surface}), (mean $\pm$ SD, $n = 15 - 48$ technical replicates per symbol) but not the bulk (E_{Bulk}). The sample groups SN PAMPS, SN PAAm, DN/Glass and DN/Si-PET contained sample sizes of $n = 3 - 6$ hydrogels per symbol (mean $\pm$ SD). (B) Independent tuning of bulk modulus and polymer surface densities (W_{M1} , W_{M2}) by DN hydrogel synthesis.

Control of the surface layer thickness

To develop DN hydrogels with spatially modulated surface properties, the DN hydrogel was synthesized in a polymerization mold where the glass substrate was tilted which allows the regulation of the surface layer thickness, and through that, the control of the surface electric potential (Figure 4A). During the 2nd network synthesis, the 1st network hydrogel was partially compressed on one side, through a spacer of height h_1 , thinner than the hydrogel thickness h , to reach a maximum compression of 50 kPa (Scheme S1). On the other side, a spacer of height h_2 , thicker than the hydrogel was used, where the gap between the PAMPS network and the glass substrate was filled with excess AAm solution. The maximum gap distance creates a surface layer thickness of 0.9 mm ($t \sim h_2 - h_1$) in the as-prepared state. Because of the spacer height difference, a structural change at the surface-bulk transition zone through sample preparation should be induced. The cross-section view of the DN hydrogel shows that there is a clear difference in structure of the surface layer and the bulk region, as

414 shown by the microscopic observations at position 8 cm (Figure 4A). The position is determined as the
415 distance of the sampling position to the edge of the compressed hydrogel side. While the surface layer
416 of $t \sim 800 \mu\text{m}$ thick (Figure 4A, 1) shows a big porous structure, in the bulk material (Figure 4A, 3) a
417 hierarchical structure of big pores filled with smaller ones is observed. The transition between the
418 surface layer and the bulk is a clear cut (Figure 4A, 2, white dotted line), with a transition zone thinner
419 than $20 \mu\text{m}$. Even if there is a structural difference between the surface layer and the bulk observable,
420 it must be noted that the observed porous structure is not resembling the native hydrogel structure
421 because it is obtained through a freeze-drying process. The electric potential depth profiles measured
422 at different positions reveal the gradual increase of the surface layer thickness with increasing distance
423 to the compressed side of the DN hydrogel. Three typical depth profiles are shown in Figure 4B. The
424 electric potential between the gel and the bath solution on the compressed side is above -100 mV
425 (Distance: 0 cm), related to the DN bulk potential. At positions of 2 cm and 6 cm , the surface layer
426 thickness increased so that the surface potential is weakened to a value of -20 mV , related to the PAAm
427 surface layer. The increase in surface thickness along the distance from the compressed side, analyzed
428 by the electric potential depth profiles, is summarized in Figure 4C. On the compressed side (Position:
429 0 cm), no surface layer is formed, and the surface potential of the gel is the same as the bulk, showing
430 a value of -120 mV . The surface potential abruptly changes from -120 mV to -20 mV between positions
431 of 1 and 2 cm , due to the formation of surface layer. With the increase of the distance to the
432 compressed side, the surface layer thickness gradually increases and reaches values higher than 1 mm
433 at the position of 9 cm , while the surface potential remains constant at -20 mV . Consequently, we
434 obtained a hydrogel surface with a strong negatively charged region ($\Delta\Phi_s = -120 \text{ mV}$, blue) that
435 switches within 1 cm to an almost neutral ($\Delta\Phi_s = -20 \text{ mV}$, red) region. Since the surface layer thickness
436 increases with the distance from the compressed side, the surface modulus integrated from the
437 surface layer and the bulk might change with the distance as well⁵⁰. Such a surface might be used for
438 studying the modulus effect on cells with a constant surface chemistry.

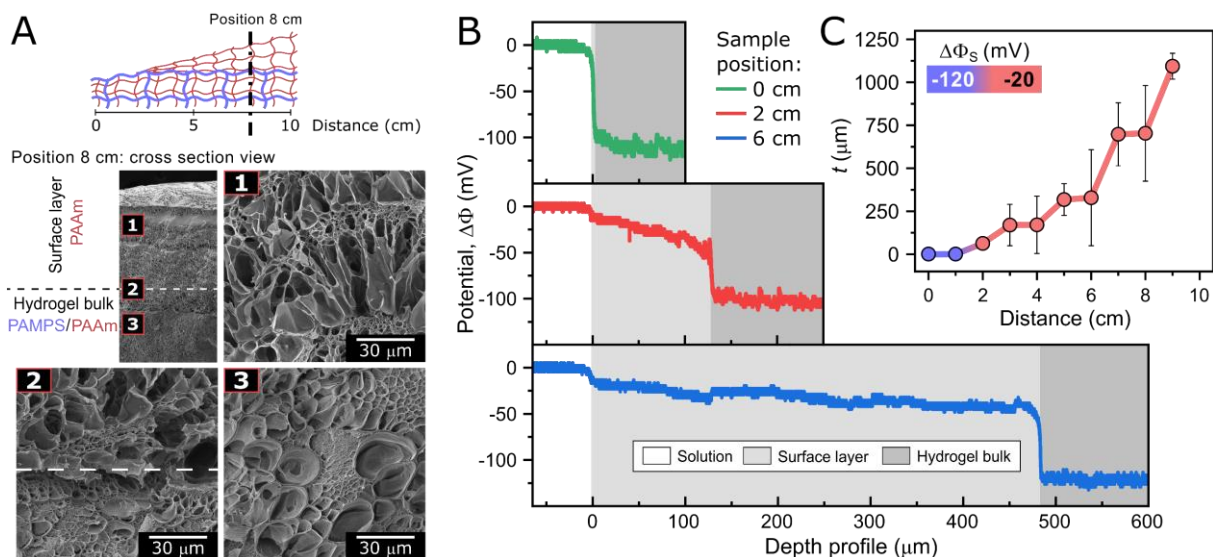


Figure 4: Control of PAAm layer thickness on the DN/Glass surface from micro-to-macro scale. (A) The 2nd network polymerization setup where the spacer heights (Scheme S1) and the compressive stress regulate the surface layer thickness of the DN hydrogel (PAMPS/PAAm, 1-3-1/2-0.1-0.1). The DN hydrogel SEM cross-sectional view reveals a surface layer with thickness $t \sim 800 \mu\text{m}$, with structural details on the PAAm surface layer (1), the transition zone (2, white dotted line represents the surface-bulk transition) and the DN bulk structure (3). (B) Selected electric potential depth profiles of the DN hydrogel at specific positions showing the surface layer thickness gradient. (C) Position profile of surface layer thickness and the corresponding surface potential ($\Delta\Phi_s$) visualized by a blue (strong charged) and red (weak charged) color map ($n = 2 - 5$ measurements per position).

Cell adhesion to DN hydrogels with varied surface potential

The independent tuning of the surface and bulk properties of DN hydrogels by the surface-bulk structure transition allows us to control the surface potential of DN gels. Here, we investigate how the surface potentials of the hydrogels influence the cell attachment. As an example, mesenchymal stem cell attachment on various types of synthesized DN hydrogels was monitored in a cell culture experiment.

Figure 5 shows the morphology of the mesenchymal stem cells after 3 days of incubation on various hydrogels with different surface potentials. When the hydrogel surface potential was weaker than -60 mV, as seen on PAAm and DN/Glass hydrogels, cells did not adhere to the surface, instead they aggregated to multicellular spheroids. On hydrogels with surface potential stronger than -100 mV, as seen on PAMPS, DN/Glass-C, and DN/Si-PET hydrogels, cells started to adhere. On the SN PAMPS hydrogel the individual cells were circularly spread, while on the DN/Glass-C and DN/Si-PET hydrogels

the cell shapes are more irregular and spindle-like (shown by white arrows in Figure 5). In case of DN/Si-PET hydrogels, on the low crosslinked sample (X_{X1} 1.5 mol%) dome-shaped adherent cell aggregates were observed, but as the crosslinking degree increased the cells gradually become slightly more spread and the dome-shaped aggregates were not observable anymore. The cell-substrate adhesion is usually guided by protein adsorption^{51,52}. However, cell adhesion is a highly complex process and it was found that cell morphological changes are influenced by substrate roughness⁵³ and mechanical properties^{25,26,50} as well. The results shown in Figure 5 suggests that the surface electric potential is a major factor regulating cell morphology and it should be noted that the critical surface potential for cell adhesion varies from cell line to cell line³³.

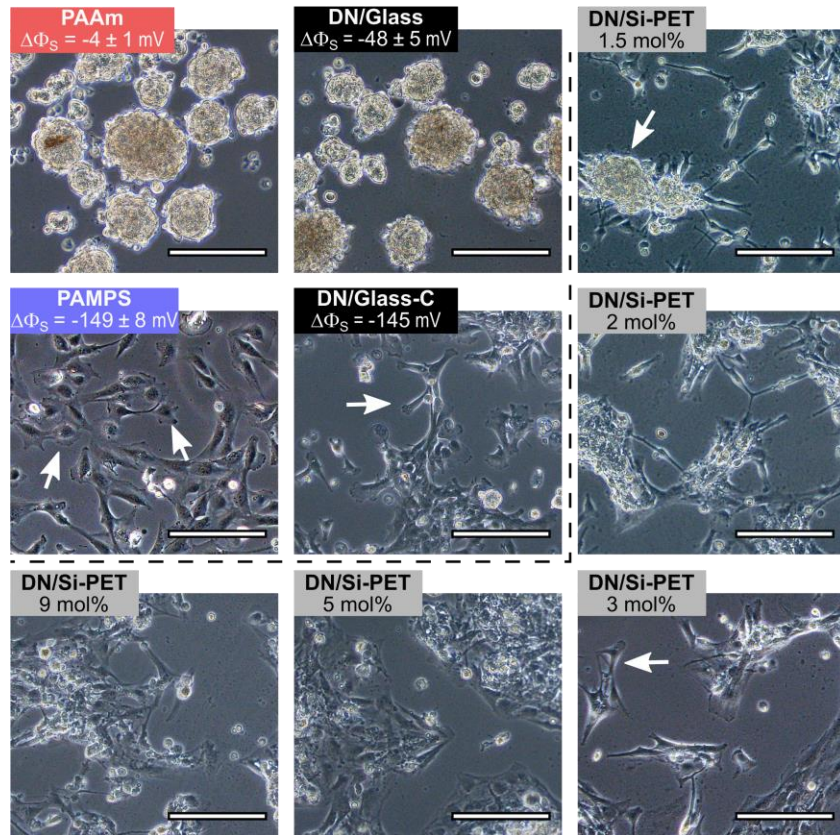


Figure 5: Increasing hydrogel surface potential induces cell attachment. Phase-contrast microscopic images (10 x magnification) of mesenchymal stem cells cultured on hydrogels for 3 days. Low surface electric potential facilitates stem cell aggregation (SN PAAm and DN/Glass) while high surface electric potential results in cell-hydrogel adhesion (SN PAMPS, DN/Glass-C, and DN/Si-PET). The scale bars represent 180 μ m. The surface electric potentials for the DN/Si-PET hydrogels are shown in Figure 2B.

Summary and Conclusion

The surface energy and charge of substrates used in 2nd network synthesis play a crucial role in determining DN hydrogel surface chemistry and surface stiffness. While the use of a low energy molding substrate facilitates the synthesis of DN hydrogels with both networks present at the surface, the electrostatic interactions between glass and like-charged polyelectrolyte hydrogels are responsible for the formation of a 2nd network polymer surface layer. The regulation of the DN hydrogel surface potential is mainly related to the 2nd network surface layer thickness that is modifiable through molding substrate surface energy or normal compression during synthesis. If no surface layer is present, a secondary regulation of the surface potential is possible via the molar ratio between the polyelectrolyte and neutral polymer. Usually, DN hydrogels made from two chemically crosslinked networks are synthesized in a two-step approach, which is time consuming and work intensive. However, with the here-proposed modifications, the second synthesis step is an easily accessible technique that fabricates not just a tough hydrogel but simultaneously functionalizes the hydrogel surface, which will be useful in controllable surface friction, cell scaffolding, and in vivo applications.

The combination of the ATR/FT-IR and the microelectrode technique has proven to be a powerful approach for characterizing hydrogel surfaces since each technique makes up for the disadvantage of the other technique. The microelectrode technique, which is highly sensitive in detecting electric potentials but has a poor spatial resolution in the depth profile, complements the ATR/FT-IR technique, which gives structural information on the topmost hydrogel layer with lower sensitivity.

The cell experiment proves that the previously observed phenomena, where cells do not adhere to DN hydrogels, is not valid for DN hydrogels in general, but is a consequence of the synthesis condition. Above a critical value, the surface PAMPS/PAAm ratios, applying to a wide range of DN hydrogel compositions, have just a minor impact on the surface electric potential and the cell morphology. This makes clear that publications investigating the interactions between cells and DN hydrogels must explicitly describe the utilized polymerization substrate and the related surface potentials, since it

drastically changes the hydrogels cell-adhesive properties. Recently, there is evidence that the induced stem cell state, of interest to cell therapies, is enhanced by cell aggregation. Therefore, the detailed hydrogel characterization and physicochemical decoupling based on the regulation of the surface-bulk transition described here could be applied to investigation how the morphological stem cell changes alter gene expression. Regarding such studies, additional evaluation of hydrogel-protein adsorption and cell viabilities on the synthesized hydrogels is necessary in the future.

Acknowledgements

This research was supported by Grant-in-Aid for Scientific Research (S) (No. 17H06144). The Institute for Chemical Reaction Design and Discovery (ICReDD) was established by the World Premier International Research Initiative (WPI), MEXT, Japan. M. Frauenlob thanks MEXT, Japan for the provided scholarship to conduct his PhD study, A. Giustiniani as well as D. Schenz for the constructive discussions regarding figure design and Y. Z. Guo and T. Sedlacik for the experimental support.

Supporting information

The supporting information contains Scheme S1, Table S1 and Figure S1 – 5 related to this article.

References

- (1) Matsuda, T.; Kawakami, R.; Namba, R.; Nakajima, T.; Gong, J. P. Mechanoresponsive Self-Growing Hydrogels Inspired by Muscle Training. *Science* **2019**, *363* (6426), 504–508. <https://doi.org/10.1126/science.aau9533>.
- (2) Liu, S.; Li, L. Ultrastretchable and Self-Healing Double-Network Hydrogel for 3D Printing and Strain Sensor. *ACS Appl. Mater. Interfaces* **2017**, *9* (31), 26429–26437. <https://doi.org/10.1021/acsami.7b07445>.
- (3) King, D. R.; Sun, T. L.; Huang, Y.; Kurokawa, T.; Nonoyama, T.; Crosby, A. J.; Gong, J. P. Extremely Tough Composites from Fabric Reinforced Polyampholyte Hydrogels. *Mater. Horizons* **2015**, *2* (6), 584–591. <https://doi.org/10.1039/C5MH00127G>.
- (4) Nonoyama, T.; Wada, S.; Kiyama, R.; Kitamura, N.; Mredha, M. T. I.; Zhang, X.; Kurokawa, T.;

- 526 Nakajima, T.; Takagi, Y.; Yasuda, K.; et al. Double-Network Hydrogels Strongly Bondable to
527 Bones by Spontaneous Osteogenesis Penetration. *Adv. Mater.* **2016**, *28* (31), 6740–6745.
528 <https://doi.org/10.1002/adma.201601030>.
- 529 (5) Yan, Y.; Li, M.; Yang, D.; Wang, Q.; Liang, F.; Qu, X.; Qiu, D.; Yang, Z. Construction of Injectable
530 Double-Network Hydrogels for Cell Delivery. *Biomacromolecules* **2017**, *18* (7), 2128–2138.
531 <https://doi.org/10.1021/acs.biomac.7b00452>.
- 532 (6) Kiyama, R.; Nonoyama, T.; Wada, S.; Semba, S.; Kitamura, N.; Nakajima, T.; Kurokawa, T.;
533 Yasuda, K.; Tanaka, S.; Gong, J. P. Micro Patterning of Hydroxyapatite by Soft Lithography on
534 Hydrogels for Selective Osteoconduction. *Acta Biomater.* **2018**, *81*, 60–69.
535 <https://doi.org/10.1016/j.actbio.2018.10.002>.
- 536 (7) Zhao, Y.; Nakajima, T.; Yang, J. J.; Kurokawa, T.; Liu, J.; Lu, J.; Mizumoto, S.; Sugahara, K.;
537 Kitamura, N.; Yasuda, K.; et al. Proteoglycans and Glycosaminoglycans Improve Toughness of
538 Biocompatible Double Network Hydrogels. *Adv. Mater.* **2014**, *26* (3), 436–442.
539 <https://doi.org/10.1002/adma.201303387>.
- 540 (8) Ajiro, H.; Watanabe, J.; Akashi, M. Cell Adhesion and Proliferation on Poly(N-Vinylacetamide)
541 Hydrogels and Double Network Approaches for Changing Cellular Affinities.
542 *Biomacromolecules* **2008**, *9* (2), 426–430. <https://doi.org/10.1021/bm701221c>.
- 543 (9) Higa, K.; Kitamura, N.; Kurokawa, T.; Goto, K.; Wada, S.; Nonoyama, T.; Kanaya, F.; Sugahara,
544 K.; Gong, J. P.; Yasuda, K. Fundamental Biomaterial Properties of Tough Glycosaminoglycan-
545 Containing Double Network Hydrogels Newly Developed Using the Molecular Stent Method.
546 *Acta Biomater.* **2016**, *43*, 38–49. <https://doi.org/10.1016/j.actbio.2016.07.023>.
- 547 (10) Wada, S.; Kitamura, N.; Nonoyama, T.; Kiyama, R.; Kurokawa, T.; Gong, J. P.; Yasuda, K.
548 Hydroxyapatite-Coated Double Network Hydrogel Directly Bondable to the Bone: Biological
549 and Biomechanical Evaluations of the Bonding Property in an Osteochondral Defect. *Acta*
550 *Biomater.* **2016**, *44*, 125–134. <https://doi.org/10.1016/j.actbio.2016.08.016>.
- 551 (11) Ye, Y. N.; Frauenlob, M.; Wang, L.; Tsuda, M.; Sun, T. L.; Cui, K.; Takahashi, R.; Zhang, H. J.;
552 Nakajima, T.; Nonoyama, T.; et al. Tough and Self-Recoverable Thin Hydrogel Membranes for
553 Biological Applications. *Adv. Funct. Mater.* **2018**, *28* (31), 1801489.
554 <https://doi.org/10.1002/adfm.201801489>.
- 555 (12) Yin, H.; Akasaki, T.; Lin Sun, T.; Nakajima, T.; Kurokawa, T.; Nonoyama, T.; Taira, T.; Saruwatari,
556 Y.; Ping Gong, J. Double Network Hydrogels from Polyzwitterions: High Mechanical Strength
557 and Excellent Anti-Biofouling Properties. *J. Mater. Chem. B* **2013**, *1* (30), 3685–3693.

- 558 <https://doi.org/10.1039/C3TB20324G>.
- 559 (13) Gong, J. P. Why Are Double Network Hydrogels so Tough? *Soft Matter* **2010**, 6 (12), 2583.
560 <https://doi.org/10.1039/b924290b>.
- 561 (14) Nakajima, T.; Furukawa, H.; Tanaka, Y.; Kurokawa, T.; Osada, Y.; Gong, J. P. True Chemical
562 Structure of Double Network Hydrogels. *Macromolecules* **2009**, 42 (6), 2184–2189.
563 <https://doi.org/10.1021/ma802148p>.
- 564 (15) Ahmed, S.; Nakajima, T.; Kurokawa, T.; Anamul Haque, M.; Gong, J. P. Brittle–Ductile
565 Transition of Double Network Hydrogels: Mechanical Balance of Two Networks as the Key
566 Factor. *Polymer (Guildf)*. **2014**, 55 (3), 914–923.
567 <https://doi.org/10.1016/j.polymer.2013.12.066>.
- 568 (16) Sun, J.-Y.; Zhao, X.; Illeperuma, W. R. K.; Chaudhuri, O.; Oh, K. H.; Mooney, D. J.; Vlassak, J. J.;
569 Suo, Z. Highly Stretchable and Tough Hydrogels. *Nature* **2012**, 489 (7414), 133–136.
570 <https://doi.org/10.1038/nature11409>.
- 571 (17) Kwon, H. J.; Yasuda, K.; Ohmiya, Y.; Honma, K. ichi; Chen, Y. M.; Gong, J. P. In Vitro
572 Differentiation of Chondrogenic ATDC5 Cells Is Enhanced by Culturing on Synthetic Hydrogels
573 with Various Charge Densities. *Acta Biomater*. **2010**, 6 (2), 494–501.
574 <https://doi.org/10.1016/j.actbio.2009.07.033>.
- 575 (18) Chen, Y. M.; Tanaka, M.; Gong, J. P.; Yasuda, K.; Yamamoto, S.; Shimomura, M.; Osada, Y.
576 Platelet Adhesion to Human Umbilical Vein Endothelial Cells Cultured on Anionic Hydrogel
577 Scaffolds. *Biomaterials* **2007**, 28 (10), 1752–1760.
578 <https://doi.org/10.1016/j.biomaterials.2006.12.005>.
- 579 (19) Chen, Y. M.; Shiraishi, N.; Satokawa, H.; Kakugo, A.; Narita, T.; Gong, J. P.; Osada, Y.;
580 Yamamoto, K.; Ando, J. Cultivation of Endothelial Cells on Adhesive Protein-Free Synthetic
581 Polymer Gels. *Biomaterials* **2005**, 26 (22), 4588–4596.
582 <https://doi.org/10.1016/j.biomaterials.2004.11.025>.
- 583 (20) Inagaki, Y.; Kitamura, N.; Kurokawa, T.; Tanaka, Y.; Gong, J. P.; Yasuda, K.; Tohyama, H. Effects
584 of Culture on PAMPS/PDMAAm Double-Network Gel on Chondrogenic Differentiation of
585 Mouse C3H10T1/2 Cells: In Vitro Experimental Study. *BMC Musculoskelet. Disord*. **2014**, 15
586 (1), 320. <https://doi.org/10.1186/1471-2474-15-320>.
- 587 (21) Kitamura, N.; Kurokawa, T.; Fukui, T.; Gong, J. P.; Yasuda, K. Hyaluronic Acid Enhances the
588 Effect of the PAMPS/PDMAAm Double-Network Hydrogel on Chondrogenic Differentiation of
589 ATDC5 Cells. *BMC Musculoskelet. Disord*. **2014**, 15 (1), 222. <https://doi.org/10.1186/1471->

590 2474-15-222.

591 (22) Maeda, E.; Tsutsumi, T.; Kitamura, N.; Kurokawa, T.; Ping Gong, J.; Yasuda, K.; Ohashi, T.
592 Significant Increase in Young's Modulus of ATDC5 Cells during Chondrogenic Differentiation
593 Induced by PAMPS/PDMAAm Double-Network Gel: Comparison with Induction by Insulin. *J.*
594 *Biomech.* **2014**, *47* (13), 3408–3414. <https://doi.org/10.1016/j.jbiomech.2014.07.021>.

595 (23) Yasuda, K.; Kitamura, N.; Gong, J. P.; Arakaki, K.; Kwon, H. J.; Onodera, S.; Chen, Y. M.;
596 Kurokawa, T.; Kanaya, F.; Ohmiya, Y.; et al. A Novel Double-Network Hydrogel Induces
597 Spontaneous Articular Cartilage Regeneration in Vivo in a Large Osteochondral Defect.
598 *Macromol. Biosci.* **2009**, *9* (4), 307–316. <https://doi.org/10.1002/mabi.200800223>.

599 (24) Higa, K.; Kitamura, N.; Goto, K.; Kurokawa, T.; Gong, J. P.; Kanaya, F.; Yasuda, K. Effects of
600 Osteochondral Defect Size on Cartilage Regeneration Using a Double-Network Hydrogel. *BMC*
601 *Musculoskelet. Disord.* **2017**, *18* (1), 210. <https://doi.org/10.1186/s12891-017-1578-1>.

602 (25) Engler, A. J.; Sen, S.; Sweeney, H. L.; Discher, D. E. Matrix Elasticity Directs Stem Cell Lineage
603 Specification. *Cell* **2006**, *126* (4), 677–689. <https://doi.org/10.1016/j.cell.2006.06.044>.

604 (26) Das, R. K.; Gocheva, V.; Hammink, R.; Zouani, O. F.; Rowan, A. E. Stress-Stiffening-Mediated
605 Stem-Cell Commitment Switch in Soft Responsive Hydrogels. *Nat. Mater.* **2016**, *15* (3), 318–
606 325. <https://doi.org/10.1038/nmat4483>.

607 (27) Riedl, A.; Schleder, M.; Pudelko, K.; Stadler, M.; Walter, S.; Unterleuthner, D.; Unger, C.;
608 Kramer, N.; Hengstschläger, M.; Kenner, L.; et al. Comparison of Cancer Cells in 2D vs 3D
609 Culture Reveals Differences in AKT–MTOR–S6K Signaling and Drug Responses. *J. Cell Sci.* **2017**,
610 *130* (1), 203–218. <https://doi.org/10.1242/jcs.188102>.

611 (28) Wang, W.; Itaka, K.; Ohba, S.; Nishiyama, N.; Chung, U.; Yamasaki, Y.; Kataoka, K. 3D Spheroid
612 Culture System on Micropatterned Substrates for Improved Differentiation Efficiency of
613 Multipotent Mesenchymal Stem Cells. *Biomaterials* **2009**, *30* (14), 2705–2715.
614 <https://doi.org/10.1016/j.biomaterials.2009.01.030>.

615 (29) Schneider, G. B.; English, A.; Abraham, M.; Zaharias, R.; Stanford, C.; Keller, J. The Effect of
616 Hydrogel Charge Density on Cell Attachment. *Biomaterials* **2004**, *25* (15), 3023–3028.
617 <https://doi.org/10.1016/j.biomaterials.2003.09.084>.

618 (30) Han, L.; Mao, Z.; Wu, J.; Zhang, Y.; Gao, C. Influences of Surface Chemistry and Swelling of
619 Salt-Treated Polyelectrolyte Multilayers on Migration of Smooth Muscle Cells. *J. R. Soc.*
620 *Interface* **2012**, *9* (77), 3455–3468. <https://doi.org/10.1098/rsif.2012.0546>.

- 621 (31) Lampin, M.; Warocquier-Clerout, R.; Legris, C.; Degrange, M.; Sigot-Luizard, M. F. Correlation
622 between Substratum Roughness and Wettability, Cell Adhesion, and Cell Migration. *J. Biomed.*
623 *Mater. Res.* **1997**, *36* (1), 99–108. [https://doi.org/10.1002/\(SICI\)1097-](https://doi.org/10.1002/(SICI)1097-4636(199707)36:1<99::AID-JBM12>3.0.CO;2-E)
624 [4636\(199707\)36:1<99::AID-JBM12>3.0.CO;2-E](https://doi.org/10.1002/(SICI)1097-4636(199707)36:1<99::AID-JBM12>3.0.CO;2-E).
- 625 (32) Charras, G.; Sahai, E. Physical Influences of the Extracellular Environment on Cell Migration.
626 *Nat. Rev. Mol. Cell Biol.* **2014**, *15* (12), 813–824. <https://doi.org/10.1038/nrm3897>.
- 627 (33) Chen, Y. M.; Gong, J. P.; Tanaka, M.; Yasuda, K.; Yamamoto, S.; Shimomura, M.; Osada, Y.
628 Tuning of Cell Proliferation on Tough Gels by Critical Charge Effect. *J. Biomed. Mater. Res. Part*
629 *A* **2009**, *88A* (1), 74–83. <https://doi.org/10.1002/jbm.a.31869>.
- 630 (34) Tan, F.; Liu, J.; Liu, M.; Wang, J. Charge Density Is More Important than Charge Polarity in
631 Enhancing Osteoblast-like Cell Attachment on Poly(Ethylene Glycol)-Diacrylate Hydrogel.
632 *Mater. Sci. Eng. C* **2017**, *76*, 330–339. <https://doi.org/10.1016/j.msec.2017.03.051>.
- 633 (35) Chang, H.-Y.; Kao, W.-L.; You, Y.-W.; Chu, Y.-H.; Chu, K.-J.; Chen, P.-J.; Wu, C.-Y.; Lee, Y.-H.;
634 Shyue, J.-J. Effect of Surface Potential on Epithelial Cell Adhesion, Proliferation and
635 Morphology. *Colloids Surfaces B Biointerfaces* **2016**, *141*, 179–186.
636 <https://doi.org/10.1016/j.colsurfb.2016.01.049>.
- 637 (36) Gong, J. P.; Kagata, G.; Osada, Y. Friction of Gels. 4. Friction on Charged Gels. *J. Phys. Chem. B*
638 **1999**, *103* (29), 6007–6014. <https://doi.org/10.1021/jp990256v>.
- 639 (37) Volkov, A. G.; Markin, V. S. Electric Properties of Oil/Water Interfaces. **2004**, *4*, 91–182.
640 [https://doi.org/10.1016/S1573-4285\(04\)80006-1](https://doi.org/10.1016/S1573-4285(04)80006-1).
- 641 (38) *Polyelectrolyte Gels*; Harland, R. S., Prud'homme, R. K., Eds.; ACS Symposium Series; American
642 Chemical Society: Washington, DC, 1992. <https://doi.org/10.1021/bk-1992-0480>.
- 643 (39) Gong, P.; Genzer, J.; Szleifer, I. Phase Behavior and Charge Regulation of Weak Polyelectrolyte
644 Grafted Layers. *Phys. Rev. Lett.* **2007**, *98* (1), 018302.
645 <https://doi.org/10.1103/PhysRevLett.98.018302>.
- 646 (40) Erbaş, A.; Olvera de la Cruz, M. Interactions between Polyelectrolyte Gel Surfaces.
647 *Macromolecules* **2016**, *49* (23), 9026–9034. <https://doi.org/10.1021/acs.macromol.6b01416>.
- 648 (41) Sokoloff, J. B. Theory of Hydrostatic Lubrication for Two Like-Charge Polymer Hydrogel Coated
649 Surfaces. *Soft Matter* **2010**, *6* (16), 3856. <https://doi.org/10.1039/c000252f>.
- 650 (42) Gong, J. P. Friction and Lubrication of Hydrogels—Its Richness and Complexity. *Soft Matter*
651 **2006**, *2* (7), 544–552. <https://doi.org/10.1039/B603209P>.

- 652 (43) Maréchal, Y. IR Spectroscopy of an Exceptional H-Bonded Liquid: Water. *J. Mol. Struct.* **1994**,
653 322 (C), 105–111. [https://doi.org/10.1016/0022-2860\(94\)87025-X](https://doi.org/10.1016/0022-2860(94)87025-X).
- 654 (44) Yezek, L. P.; van Leeuwen, H. P. An Electrokinetic Characterization of Low Charge Density
655 Cross-Linked Polyacrylamide Gels. *J. Colloid Interface Sci.* **2004**, 278 (1), 243–250.
656 <https://doi.org/10.1016/j.jcis.2004.05.026>.
- 657 (45) Guo, H.; Kurokawa, T.; Takahata, M.; Hong, W.; Katsuyama, Y.; Luo, F.; Ahmed, J.; Nakajima,
658 T.; Nonoyama, T.; Gong, J. P. Quantitative Observation of Electric Potential Distribution of
659 Brittle Polyelectrolyte Hydrogels Using Microelectrode Technique. *Macromolecules* **2016**, 49
660 (8), 3100–3108. <https://doi.org/10.1021/acs.macromol.6b00037>.
- 661 (46) Gong, J. P.; Katsuyama, Y.; Kurokawa, T.; Osada, Y. Double-Network Hydrogels with Extremely
662 High Mechanical Strength. *Adv. Mater.* **2003**, 15 (14), 1155–1158.
663 <https://doi.org/10.1002/adma.200304907>.
- 664 (47) Furniss, B. S.; Hannaford, A. J.; Smith, P. W. G.; Tatchell, A. R. *Vogel's Textbook of Practical*
665 *Organic Chemistry*, 5th ed.; Harlow: Longman, 1989.
- 666 (48) Hertz, H. On the Contact of Elastic Solids. *J. Reine Angew. Math.* **1881**, 92, 156–171.
- 667 (49) Eisenberg, D. S.; Crothers, D. M. *Physical Chemistry: With Applications to the Life Sciences*;
668 Benjamin/Cummings Publishing Company Inc.: San Francisco, 1979.
- 669 (50) Hadden, W. J.; Young, J. L.; Holle, A. W.; McFetridge, M. L.; Kim, D. Y.; Wijesinghe, P.; Taylor-
670 Weiner, H.; Wen, J. H.; Lee, A. R.; Bieback, K.; et al. Stem Cell Migration and
671 Mechanotransduction on Linear Stiffness Gradient Hydrogels. *Proc. Natl. Acad. Sci.* **2017**, 114
672 (22), 5647–5652. <https://doi.org/10.1073/pnas.1618239114>.
- 673 (51) Arias, C. J.; Surmaitis, R. L.; Schlenoff, J. B. Cell Adhesion and Proliferation on the “Living”
674 Surface of a Polyelectrolyte Multilayer. *Langmuir* **2016**, 32 (21), 5412–5421.
675 <https://doi.org/10.1021/acs.langmuir.6b00784>.
- 676 (52) Arias, C. J.; Keller, T. C. S.; Schlenoff, J. B. Quasi-Spherical Cell Clusters Induced by a
677 Polyelectrolyte Multilayer. *Langmuir* **2015**, 31 (23), 6436–6446.
678 <https://doi.org/10.1021/acs.langmuir.5b00678>.
- 679 (53) Razafiarison, T.; Holenstein, C. N.; Stauber, T.; Jovic, M.; Vertudes, E.; Loparic, M.; Kaweck,
680 M.; Bernard, L.; Silvan, U.; Snedeker, J. G. Biomaterial Surface Energy-Driven Ligand Assembly
681 Strongly Regulates Stem Cell Mechanosensitivity and Fate on Very Soft Substrates. *Proc. Natl.*
682 *Acad. Sci.* **2018**, 115 (18), 4631–4636. <https://doi.org/10.1073/pnas.1704543115>.