



Title	Synthesis of Sulfide Solid Electrolytes from Li ₂ S and P ₂ S ₅ in Anisole
Author(s)	Maniwa, Riku; Galpa, Marcela; Rosero Navarro, Nataly Carolina et al.
Citation	Journal of Materials Chemistry A, 9(1), 400–405 https://doi.org/10.1039/D0TA08658D
Issue Date	2021-01-07
Doc URL	https://hdl.handle.net/2115/83765
Type	journal article
File Information	Supporting_4.pdf



Supplementary Information

Synthesis of Sulfide Solid Electrolytes from Li_2S and P_2S_5 in Anisole

Riku Maniwa^a, Marcela Calpa^{a,b}, Nataly Carolina Rosero-Navarro^{b*}, Akira Miura^{b*}, and

Kiyoharu Tadanaga^b

^a Graduate School of Chemical Sciences and Engineering, Hokkaido University, Sapporo,

Hokkaido 060-8628, Japan

^b Division of Applied Chemistry, Faculty of Engineering, Hokkaido University, Sapporo,

Hokkaido 060-8628, Japan

* Corresponding author

E-mail address: amiura@eng.hokudai.ac.jp; rosero@eng.hokudai.ac.jp

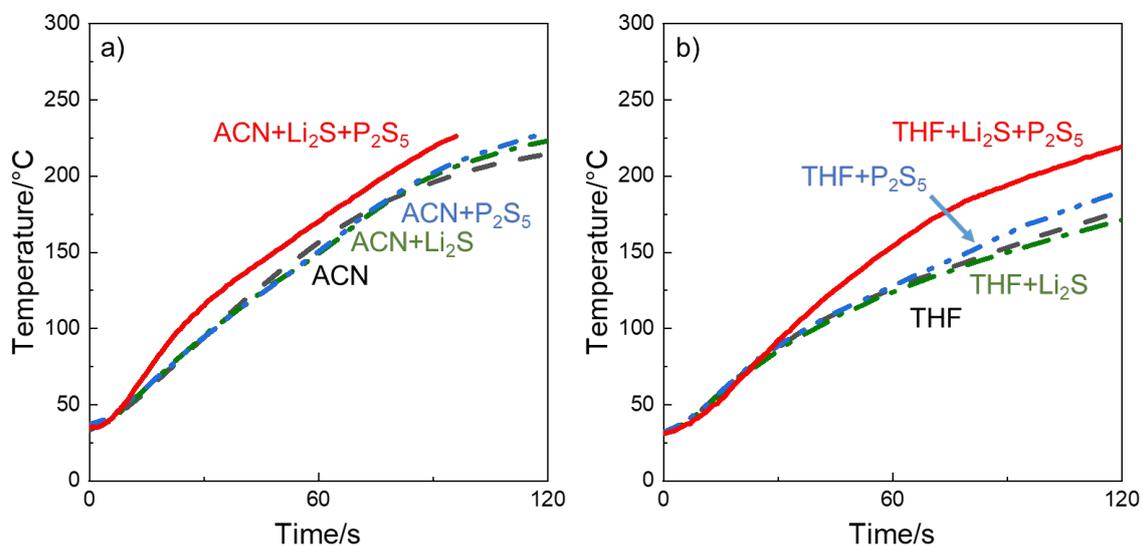


Figure S1. The temperature change during microwave irradiation a) in ACN b) in THF. The output power of microwave was 100 W.

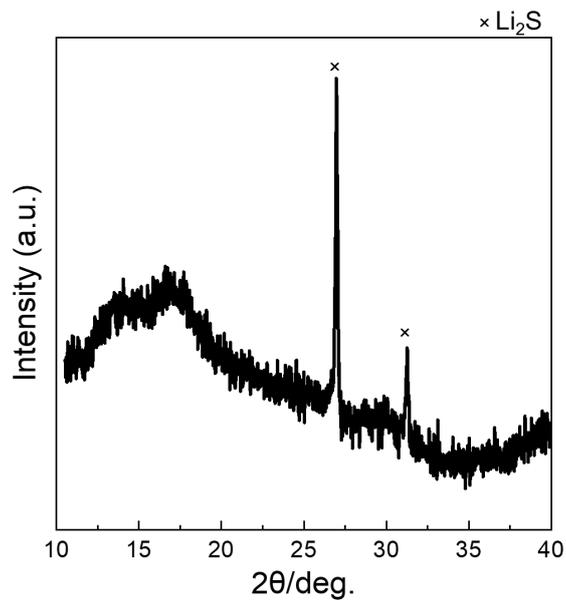


Figure S2. The XRD pattern of the precipitation of suspension (Li₂S:Lawesson's reagents = 75:25) using anisole after microwave irradiation.

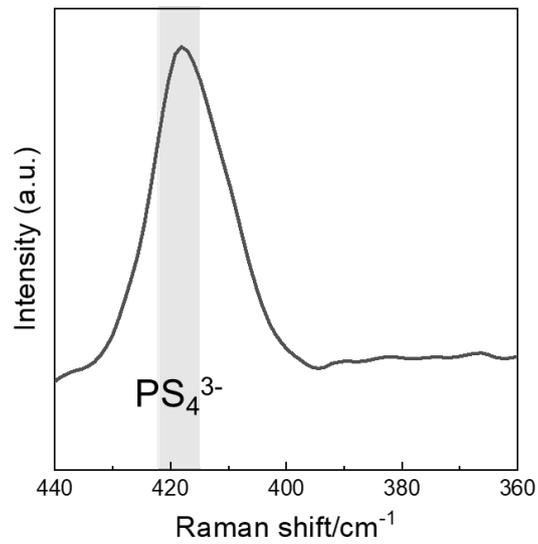


Figure S3. Anisole+Li₂S+P₂S₅ raman spectrum after microwave irradiation used a SiC vial.

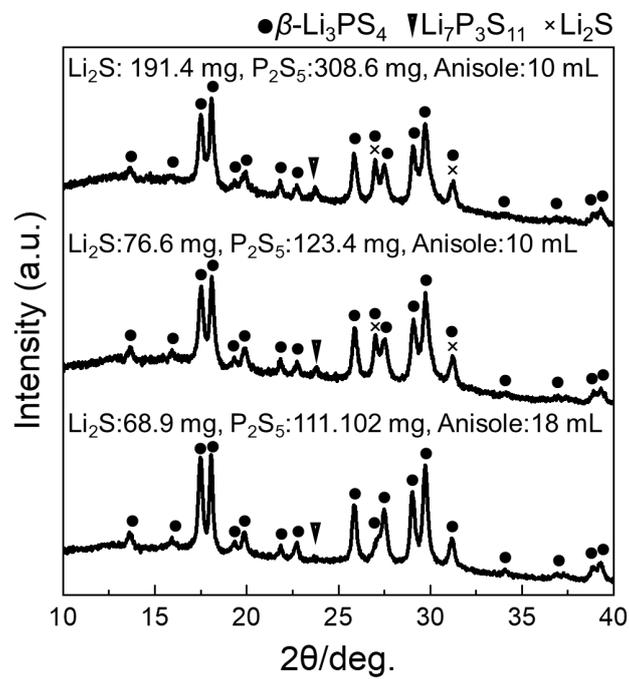


Figure S4. The XRD patterns of the solid electrolytes with varying ratio of reagent to solvent. The ratio of Li₂S to P₂S₅ was fixed at 75:25. Ball-milled Li₂S was used. The microwave irradiation was applied until the temperature reached 220 °C

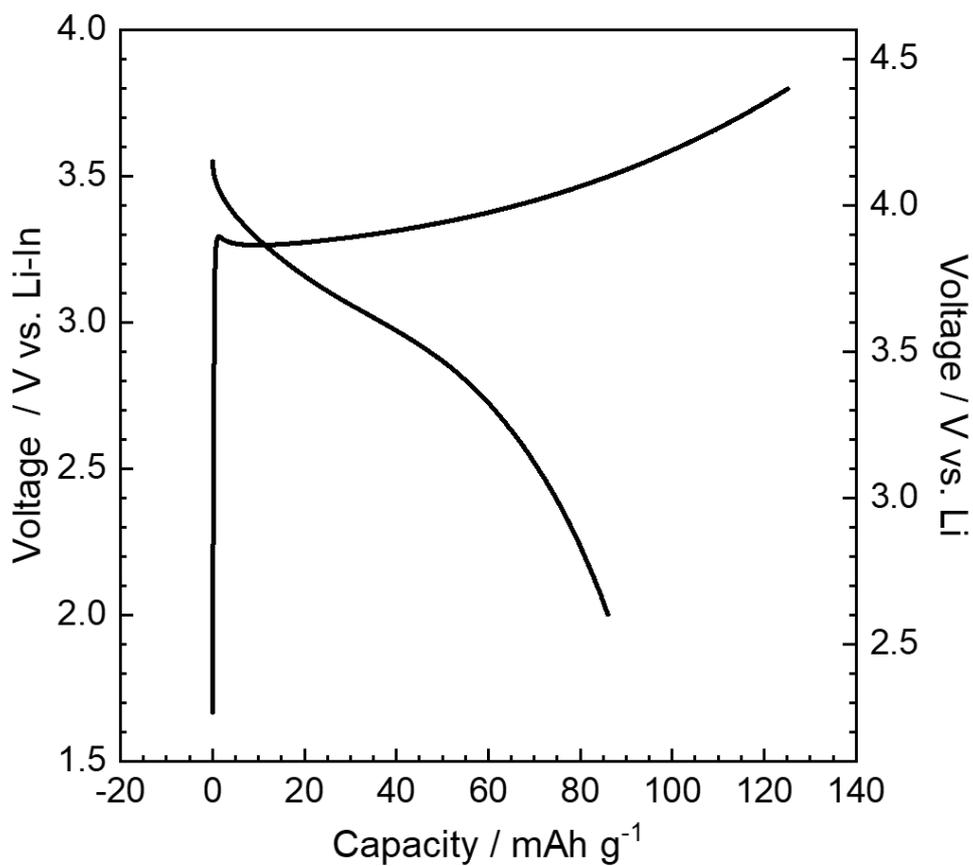


Figure S5 Discharge-charge profile of all-solid-state battery with the cathode composite composed of $\text{Li}_7\text{P}_3\text{S}_{11}$ synthesized using anisole. The ratio of the composite was LiNbO_3 -coated $\text{LiNi}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3}\text{O}_2$ (NMC): synthesized solid electrolyte: Vapor Grown Carbon Fiber (VGCF) = 69:29:2 (mass %). The battery was fabricated according to the literature [M Calpa, et al., *Electrochimica Acta*, 2019, **219**, 473-480.].

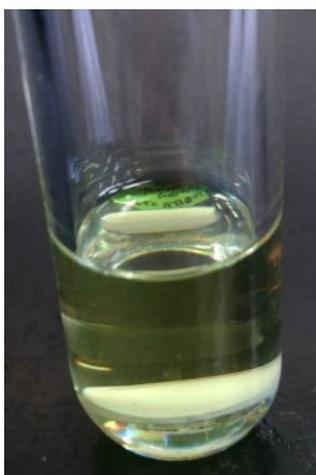


Figure S6. The photo of P_2S_5 and anisole solution after microwave irradiation.

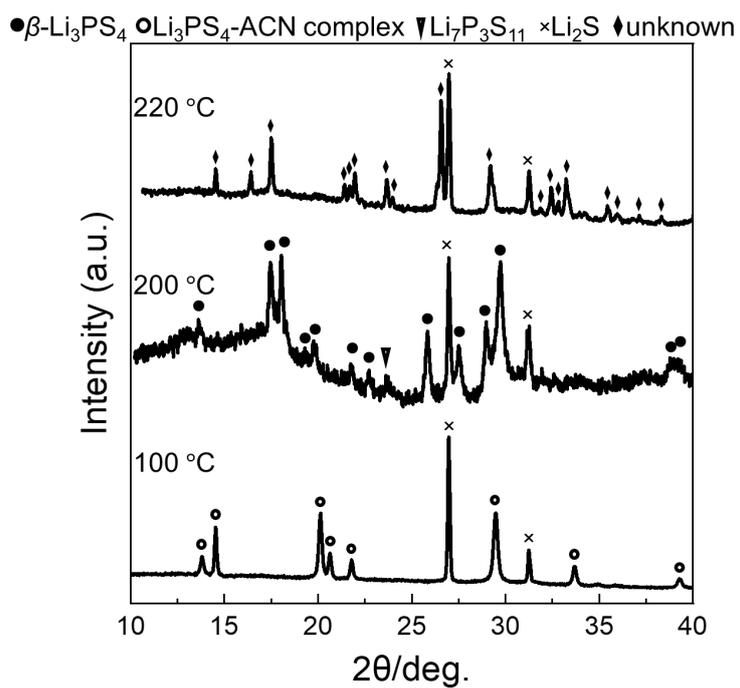


Figure S7. The XRD pattern of the precipitation of suspension ($Li_2S:P_2S_5 = 75:25$) using ACN after microwave irradiation.

Table S1. Detailed reagent and solvent amounts of Figure 3–5, S2–S4, S6.

Exp. #	Figure #	Li ₂ S (without ball milling)/mg	Li ₂ S (with ball milling)/mg	P ₂ S ₅ /mg	Lawweson's reagents/mg	LiCl/mg	Anisole/mL	ACN/mL	Microwave heating/°C	Post heating/°C
1	3	68.9	-	111.1	-	-	18	-	100	-
2	3	68.9	-	111.1	-	-	18	-	180	-
3	3	68.9	-	111.1	-	-	18	-	200	-
4	3	68.9	-	111.1	-	-	18	-	220	-
5	3	68.9	-	111.1	-	-	18	-	240	-
6	3	68.9	-	111.1	-	-	18	-	260	-
7	3	68.9	-	111.1	-	-	18	-	280	-
8	3	68.9	-	111.1	-	-	18	-	300	-
9	4	58.6	-	121.4	-	-	18	-	260	-
10	5	68.9	-	111.1	-	-	18	-	220	200
11	5	-	68.9	111.1	-	-	18	-	220	200
12	5	58.6	-	121.4	-	-	18	-	260	300
13	5	85.6	-	82.8	-	31.6	14	-	220	180
14	5	85.6	-	82.8	-	31.6	14	-	220	550
15	S2	25.6	-	-	74.6	-	18	-	300	-
16	S3	23.0	-	37.0	-	-	6	-	260	-
17	S4	-	68.9	111.1	-	-	18	-	220	200
18	S4	-	76.6	123.4	-	-	10	-	220	200
19	S4	-	191.4	308.6	-	-	10	-	220	200
20	S6	137.8	-	222.2	-	-	-	18	100	-
21	S6	137.8	-	222.2	-	-	-	18	200	-
22	S6	137.8	-	222.2	-	-	-	18	220	-