HOKKAIDO UNIVERSITY

Title	Unique crack propagation of double network hydrogels under high stretch
Author(s)	Zhang, Ye; Fukao, Kazuki; Matsuda, Takahiro et al.
Citation	Extreme Mechanics Letters, 51, 101588 https://doi.org/10.1016/j.eml.2021.101588
Issue Date	2022-02
Doc URL	https://hdl.handle.net/2115/87819
Rights	©2022. This manuscript version is made available under the CC-BY-NC-ND 4.0 license http://creativecommons.org/licenses/by-nc-nd/4.0/
Rights(URL)	https://creativecommons.org/licenses/by-nc-nd/4.0/
Type	journal article
File Information	SI_EML_rivise.pdf

Hokkaido University Collection of Scholarly and Academic Papers : HUSCAP

Supporting Information

Unique Crack Propagation of Double Network Hydrogels under High Stretch

Ye Zhang[a], Kazuki Fukao[a], Takahiro Matsuda[b], Tasuku Nakajima[b,c,d], Katsuhiko Tsunoda[e], Takayuki Kurokawa[b], and Jian Ping Gong[b,c]*

[a]Graduate School of Life Science, Hokkaido University, Sapporo 001-0021, Japan

[b]Faculty of Advanced Life Science, Hokkaido University, Sapporo 001-0021, Japan

[c]Institute for Chemical Reaction Design and Discovery, Hokkaido University, Sapporo 001-0021, Japan

[d]Japan Science and Technology Agency, PRESTO

[e]Advanced Materials Division, Bridgestone Corporation, Tokyo 187-8531, Japan

*Corresponding author

Email: gong@sci.hokudai.ac.jp (J. P. Gong)

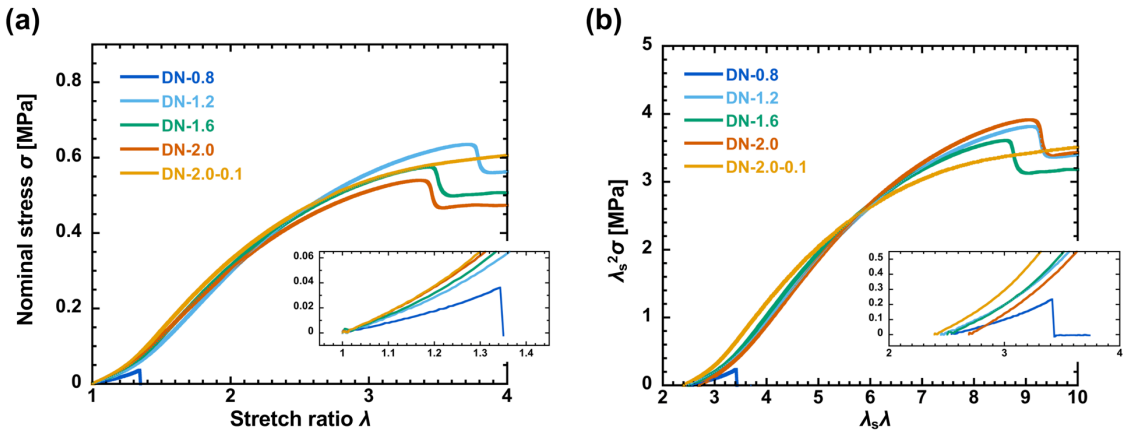


Fig. S1. (a) Uniaxial tensile stress–stretch ratio curves of all DN gels in relatively small stretching regimes. (b) Curves normalized by the pre-stretch ratio of the first network λ_s. The inset shows a magnified image of the curves of brittle DN-0.8.

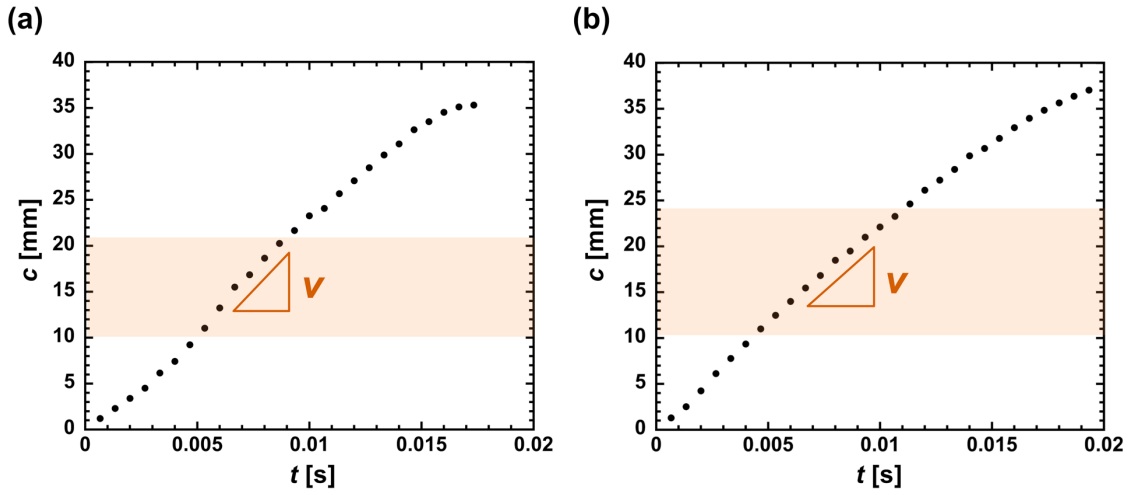


Fig. S2. Representative relationship between time t and cut length c during crack propagation in the case of (a) the fast-mode crack propagation of SN-2.0 (G = 5.23 × 10^2 J/m^2, v = 2.7 m/s) and (b) the fast-mode crack propagation of DN-2.0 (G = 1.63 × 10^3 J/m^2, v = 2.0 m/s). The crack growth velocity v was estimated from the region highlighted in orange where the crack propagated at a constant speed.

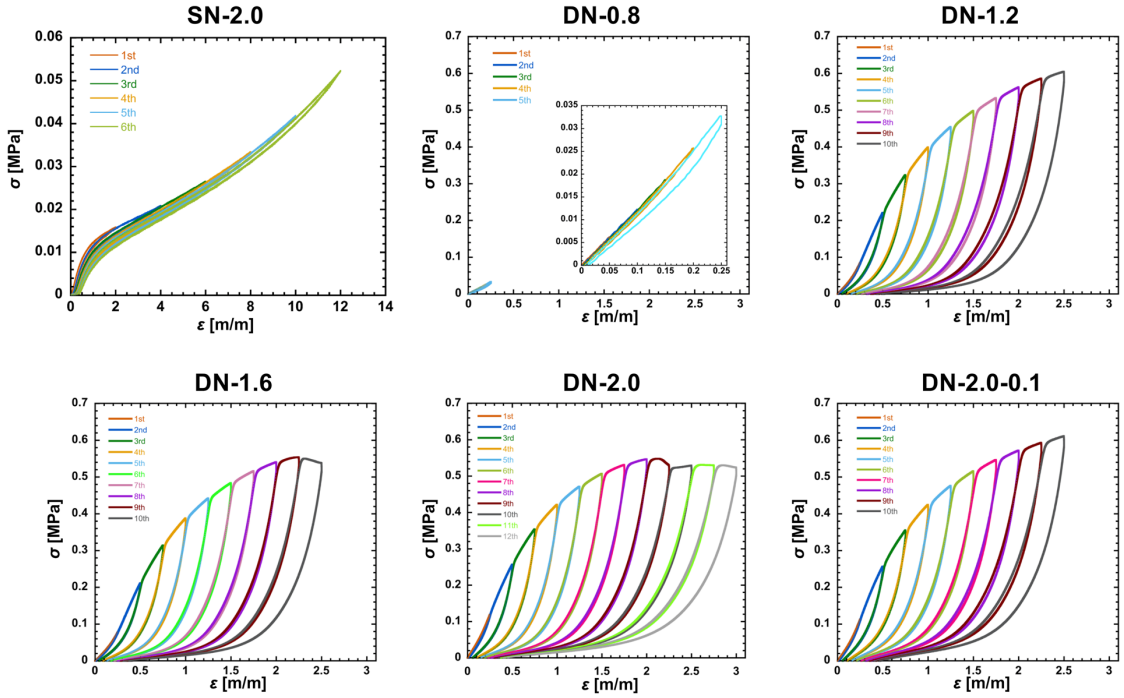


Fig. S3. Cyclic tensile stress–strain curves of the unnotched samples measured in pure shear geometries, as shown in Fig. 1a. The strain ε ($= \varepsilon_{\max,n} = n\Delta\varepsilon$) was increased stepwise with an increment ($\Delta\varepsilon$) from $n = 1$ to n$^{\text{th}}$ cycle. $\Delta\varepsilon = 2.0$, $n = 6$ for SN-2.0, $\Delta\varepsilon = 0.05$, $n = 5$ for brittle DN-0.8, $\Delta\varepsilon = 0.25$, $n = 12$ for necking DN-2.0, and $\Delta\varepsilon = 0.25$, $n = 10$ for other DN gels. The inset in the graph of brittle DN-0.8 shows magnified plots of the curves.

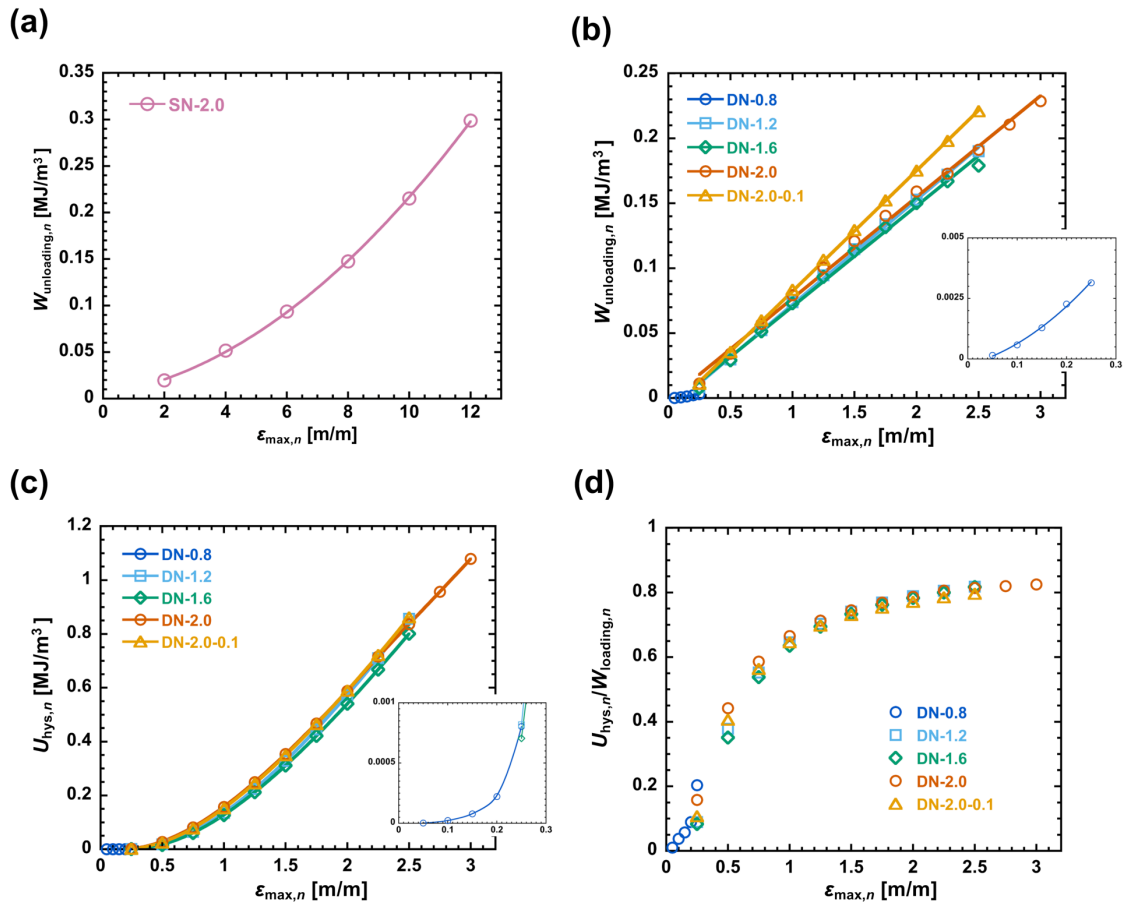


Fig. S4. (a) Dependence of $W_{\text{unloading}}$ on loading strain, $\varepsilon_{\text{max},n}$, of SN-2.0. As the SN gel was loosely cross-linked, it showed a small amount of hysteresis (~5% to W_{loading}) due to rearrangement of polymer chains during loading. (b) Dependence of $W_{\text{unloading}}$ on $\varepsilon_{\text{max},n}$ of all DN samples. The inset shows magnified plots of brittle DN-0.8. Brittle DN-0.8 that broke at a very small strain (~ 0.25) demonstrated a very weak mechanical hysteresis. In contrast, the $W_{\text{unloading},n}$–$\varepsilon_{\text{max},n}$ relations of necking and unnecking DN gels could be fitted by linear regression. (c) Dependence of dissipated energy, $U_{\text{hys},n}$, on $\varepsilon_{\text{max},n}$ of all DN samples. The inset shows magnified plots of brittle DN-0.8. (d) Dependence of ratio of the dissipated energy to the loading work, $U_{\text{hys},n}/W_{\text{loading},n}$, on $\varepsilon_{\text{max},n}$ of all DN samples. Here, $U_{\text{hys},n}$ and the loading work $W_{\text{loading},n} = W_{\text{unloading},n} + U_{\text{hys},n}$ were calculated from Fig.S3 in the same way as our previous work [1].

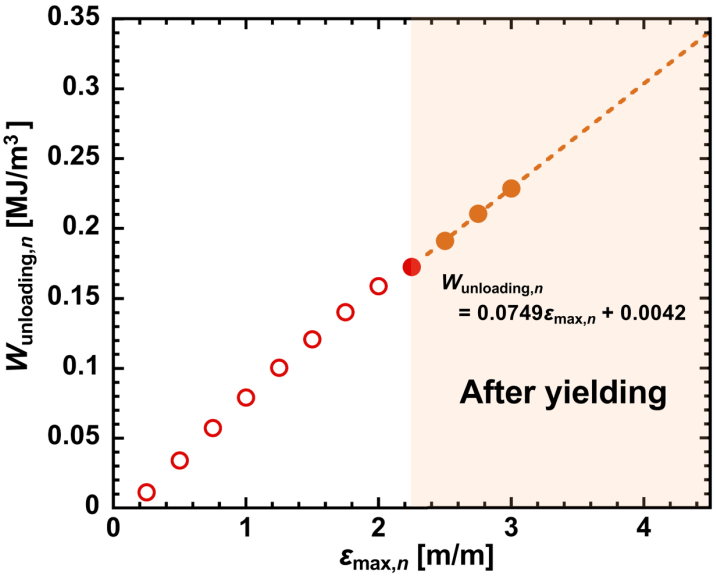


Fig. S5. Extrapolation of the $W_{unloading,n}$–$\varepsilon_{max,n}$ relation of DN-2.0 for the calculation of the G of samples with smaller l_0 under large preset strain ε (> 3) in Fig. 5. Our previous work demonstrated that, for a typical DN hydrogel, $U_{hys,n}/W_{loading,n}$ keeps constant after yielding point during cyclic tensile test [1]. If we assumed that $W_{loading,n}$ linearly increases with $\varepsilon_{max,n}$ after yielding, where the stress–strain curve shows plateau region, $W_{unloading,n} = W_{loading,n} - U_{hys} = W_{loading,n}(1 - U_{hys,n}/W_{loading,n})$ also should linearly increase with $\varepsilon_{max,n}$. Therefore, $W_{unloading}(\varepsilon)$ at large ε could be obtained by extrapolating the $W_{unloading,n}$–$\varepsilon_{max,n}$ relation in the after-yielding region ($\varepsilon_y \sim 2.25$ as shown in Fig. S3).

Reference

[1] T. Nakajima, T. Kurokawa, S. Ahmed, W. Wu, J. P. Gong, Characterization of Internal Fracture Process of Double Network Hydrogels under Uniaxial Elongation, Soft Matter 9 (2013) 1955–1966. https://doi.org/10.1039/C2SM27232F.