



HOKKAIDO UNIVERSITY

Title	Crystallinity improvements in cellulose II after multiple posttreatment cycles with a dilute NaOH solution
Author(s)	Kugo, Yuki; Nomura, Satoshi; Isono, Takuya et al.
Citation	Polymer journal, 56(5), 517-527 https://doi.org/10.1038/s41428-024-00890-0
Issue Date	2024-05
Doc URL	https://hdl.handle.net/2115/92967
Rights	This version of the article has been accepted for publication, after peer review (when applicable) and is subject to Springer Nature' s AM terms of use, but is not the Version of Record and does not reflect post-acceptance improvements, or any corrections. The Version of Record is available online at: http://dx.doi.org/10.1038/s41428-024-00890-0
Type	journal article
File Information	PJ2023404R_SI_kugo240122-1.pdf



Supporting Information

Crystallinity Improvements in Cellulose II after Multiple Posttreatment Cycles with a Dilute NaOH Solution

Yuki Kugo¹, Satoshi Nomura¹, Takuya Isono², Masashi Fujiwara²,

Toshifumi Satoh^{2,3}, Hirofumi Tani², Tomoki Erata², and Kenji Tajima^{2}*

¹Graduate School of Chemical Sciences and Engineering, Hokkaido University, N13W8, Kita-ku, Sapporo 060-8628, Japan

²Faculty of Engineering, Hokkaido University, N13W8, Kita-ku, Sapporo 060-8628, Japan

³ICReDD List-PF, Hokkaido University, N21W10, Kita-ku, Sapporo 001-0021, Japan

*Corresponding Author: Email: ktajima@eng.hokudai.ac.jp

Results

Multicycle posttreatments

Fig. S1 shows the XRD profiles of mercerized initial cellulose II and the samples obtained by one to three cycles of posttreatment. The widths of peaks at 12° , 19° , and 21° were wider as the number of post-treatment cycles increased, indicating that the crystal sizes in the $(1\bar{1}0)$, (110) , and (020) planes increased as the number of posttreatment cycles increased.



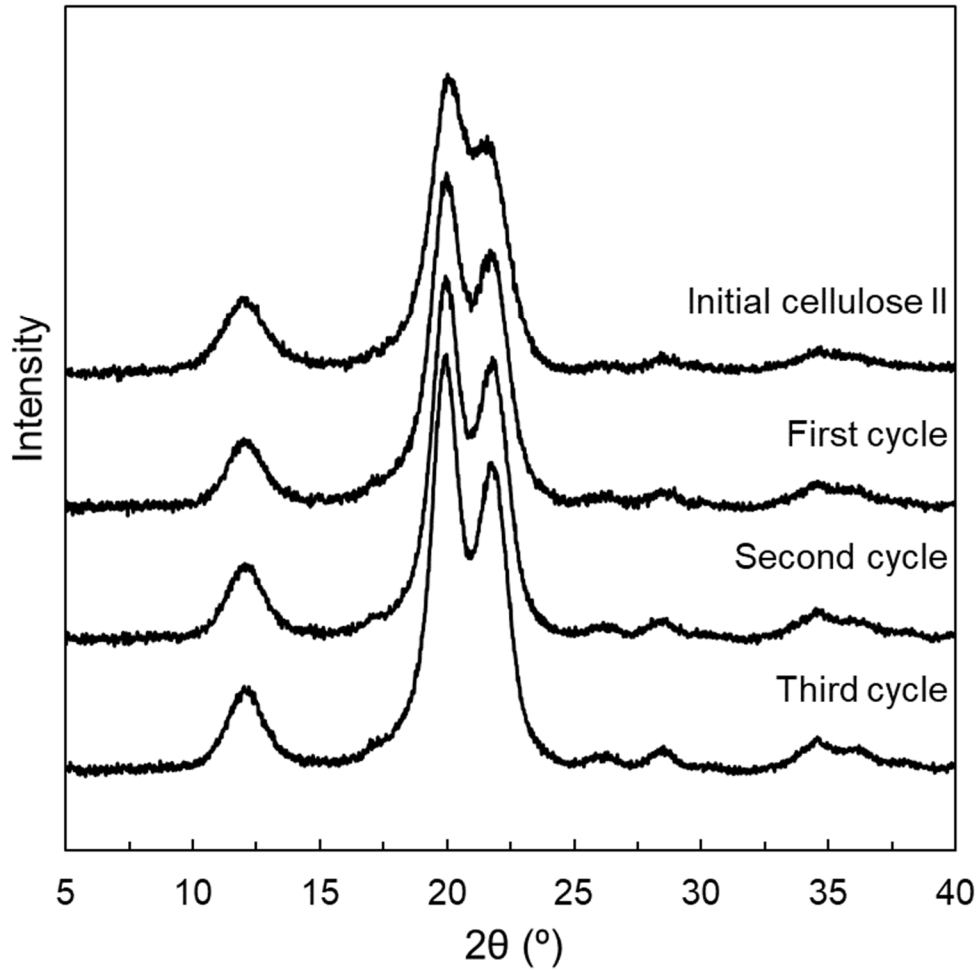


Fig. S1. XRD profiles of the mercerized initial cellulose II and the samples obtained by one to three cycles of posttreatment.

Highly efficient posttreatment method for improving crystallinity

Figs. S2(a) and S2(b) present the proportions of crystalline regions, accessible surfaces, and inaccessible surfaces/amorphous regions of samples prepared with total posttreatment times of 8 and 10 h, respectively. These results confirmed that when the posttreatment time for the first cycle was sufficiently long and the posttreatment time for the second cycle was relatively short, the crystallinity of the sample tended to increase with fewer posttreatment cycles for total treatment times of 8 and 10 h, similar to the multicycle posttreatment for a total treatment time for 6 h, as shown in Fig. 12.

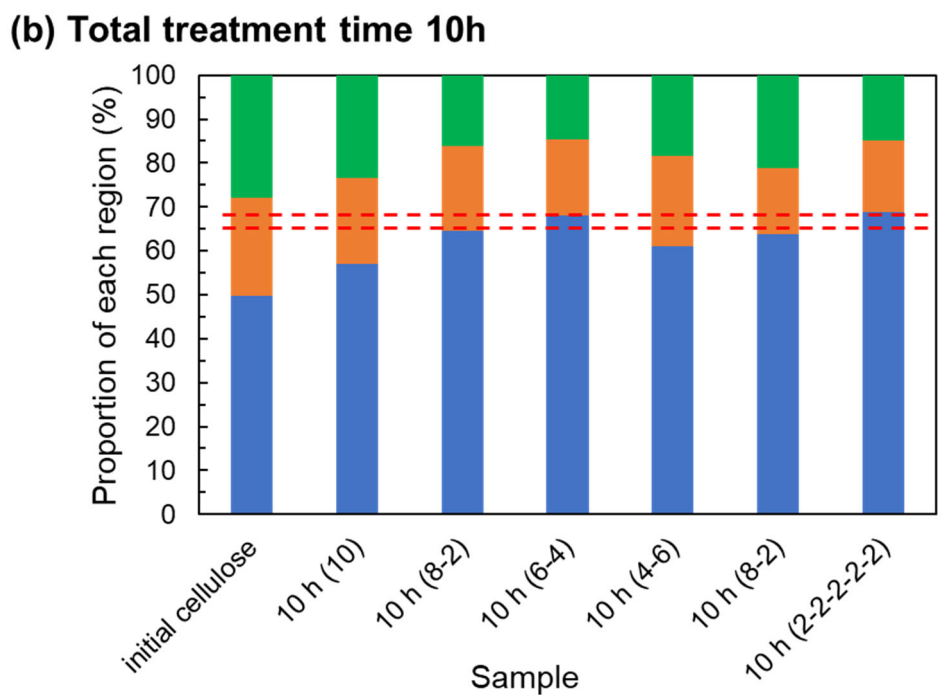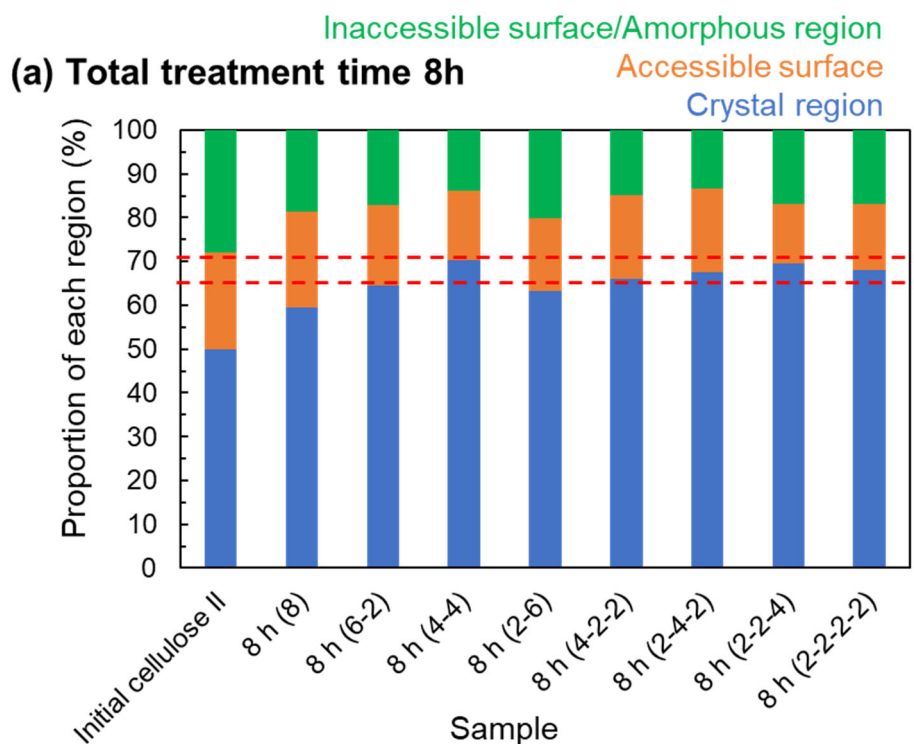

28

29 Fig. S2. Proportions of crystalline regions (blue bar), accessible surfaces (orange bar), and inaccessible
 30 surfaces/amorphous regions (green bar) evaluated from the solid-state ^{13}C CP/MAS NMR spectra of
 31 samples subjected to multicycle post-treatment with total posttreatment times of (a) 8 and (b) 10 h.