HOKKAIDO UNIVERSITY

Title	Structural Color Materials with Color Mixing Effect Using Noble Metal-Free Plasmonic Particles in SiO2-ZrN System
Author(s)	Noguchi, Shinji; Lama, Milena; Fujii, Yuta et al.
Citation	Advanced optical materials, 12(19), 2400287 https://doi.org/10.1002/adom.202400287
Issue Date	2024-07-05
Doc URL	https://hdl.handle.net/2115/94031
Rights	This is the peer reviewed version of the following article: S. Noguchi, M. Lama, Y. Fujii, A. Miura, K. Tadanaga, Structural Color Materials with Color Mixing Effect Using Noble Metal-Free Plasmonic Particles in SiO2-ZrN System. Adv. Optical Mater. 2024, 12, 2400287, which has been published in final form at https://doi.org/10.1002/adom.202400287. This article may be used for non-commercial purposes in accordance with Wiley Terms and Conditions for Use of Self-Archived Versions. This article may not be enhanced, enriched or otherwise transformed into a derivative work, without express permission from Wiley or by statutory rights under applicable legislation. Copyright notices must not be removed, obscured or modified. The article must be linked to Wiley's version of record on Wiley Online Library and any embedding, framing or otherwise making available the article or pages thereof by third parties from platforms, services and websites other than Wiley Online Library must be prohibited.
Type	journal article
File Information	Supporting information_Structural Color Materials with Color Mixing Effect Using Noble Metal-free Plasmonic Particles in SiO2-ZrN System.pdf

Hokkaido University Collection of Scholarly and Academic Papers : HUSCAP

Supporting Information

Structural Color Materials with Color Mixing Effect Using Noble Metal-free Plasmonic Particles in SiO_2–ZrN System

*Shinji Noguchi, Milena Lama, Yuta Fujii, Akira Miura, Kiyoharu Tadanaga**

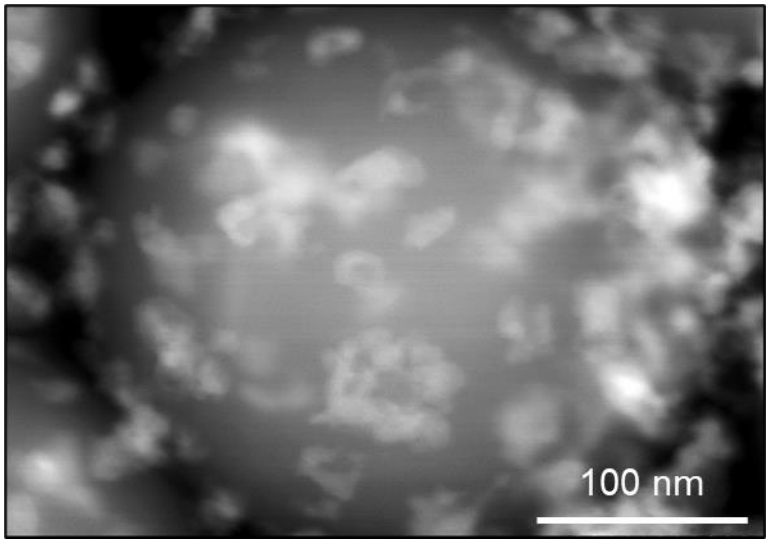

Figure S1. HAADF STEM micrograph of one SiO_2–ZrN core–shell particles.

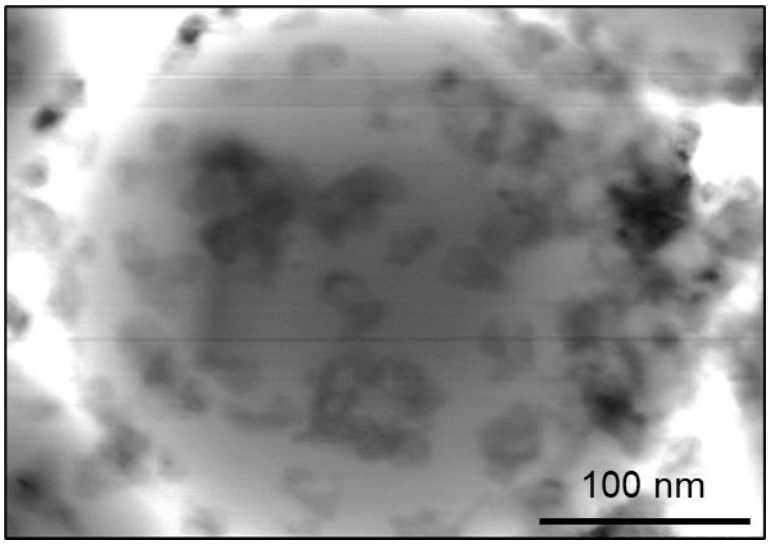

Figure S2. BF STEM micrograph of one SiO_2–ZrN core–shell particles.

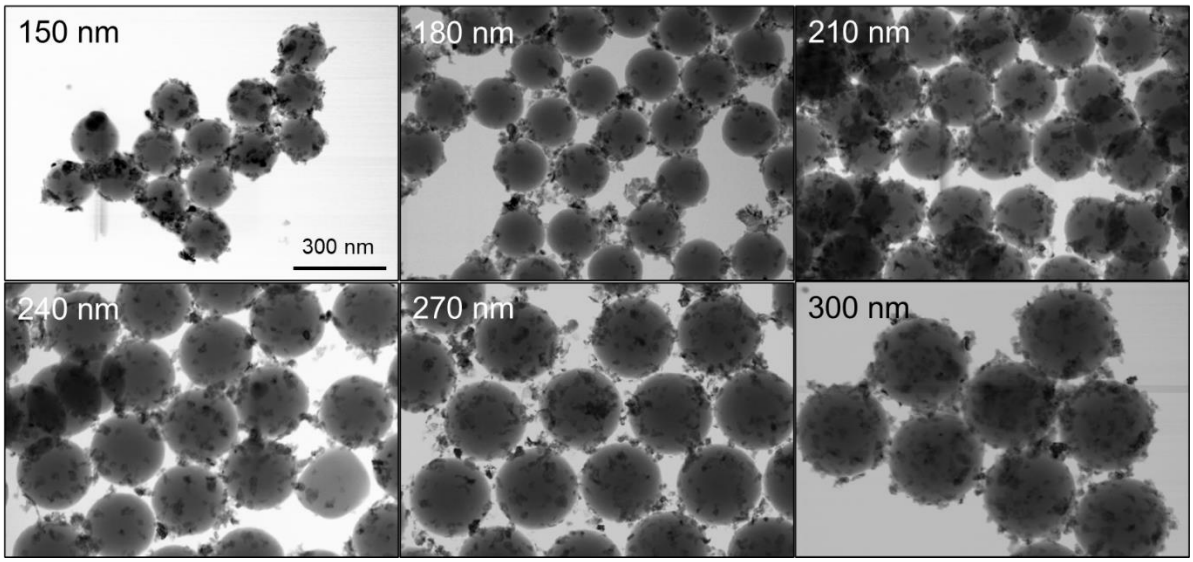

Figure S3. BF STEM images of the SiO_2–ZrN core-shell particles containing SiO_2 core particles of 150, 180, 210, 240, 270, and 300 nm.

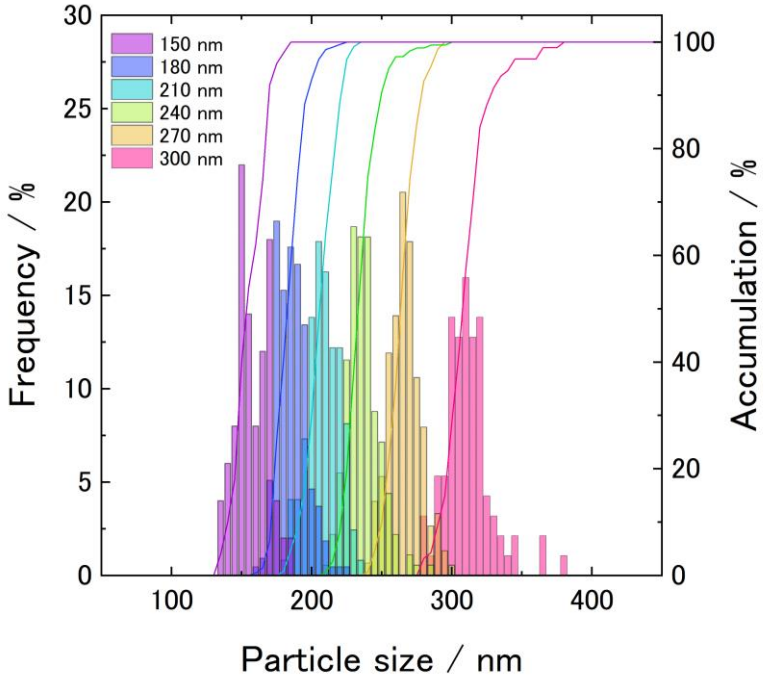

Figure S4. The particle size distribution diagram of produced SiO_2–ZrN core–shell particles containing 150–300 nm SiO_2 particle as the core. The particle size distribution is derived from STEM images of produced SiO_2–ZrN core–shell particles. The Coefficient of Variation (CV) values, which indicate the monodispersity of the particles, for core particles with sizes of 150, 180, 210, 240, 270, and 300 nm are respectively 7.2, 5.7, 5.3, 5.3, 4.1, 5.5 %. The Coefficient of Variation (CV) values are derived by dividing the standard deviation of the particle size by the mean value.

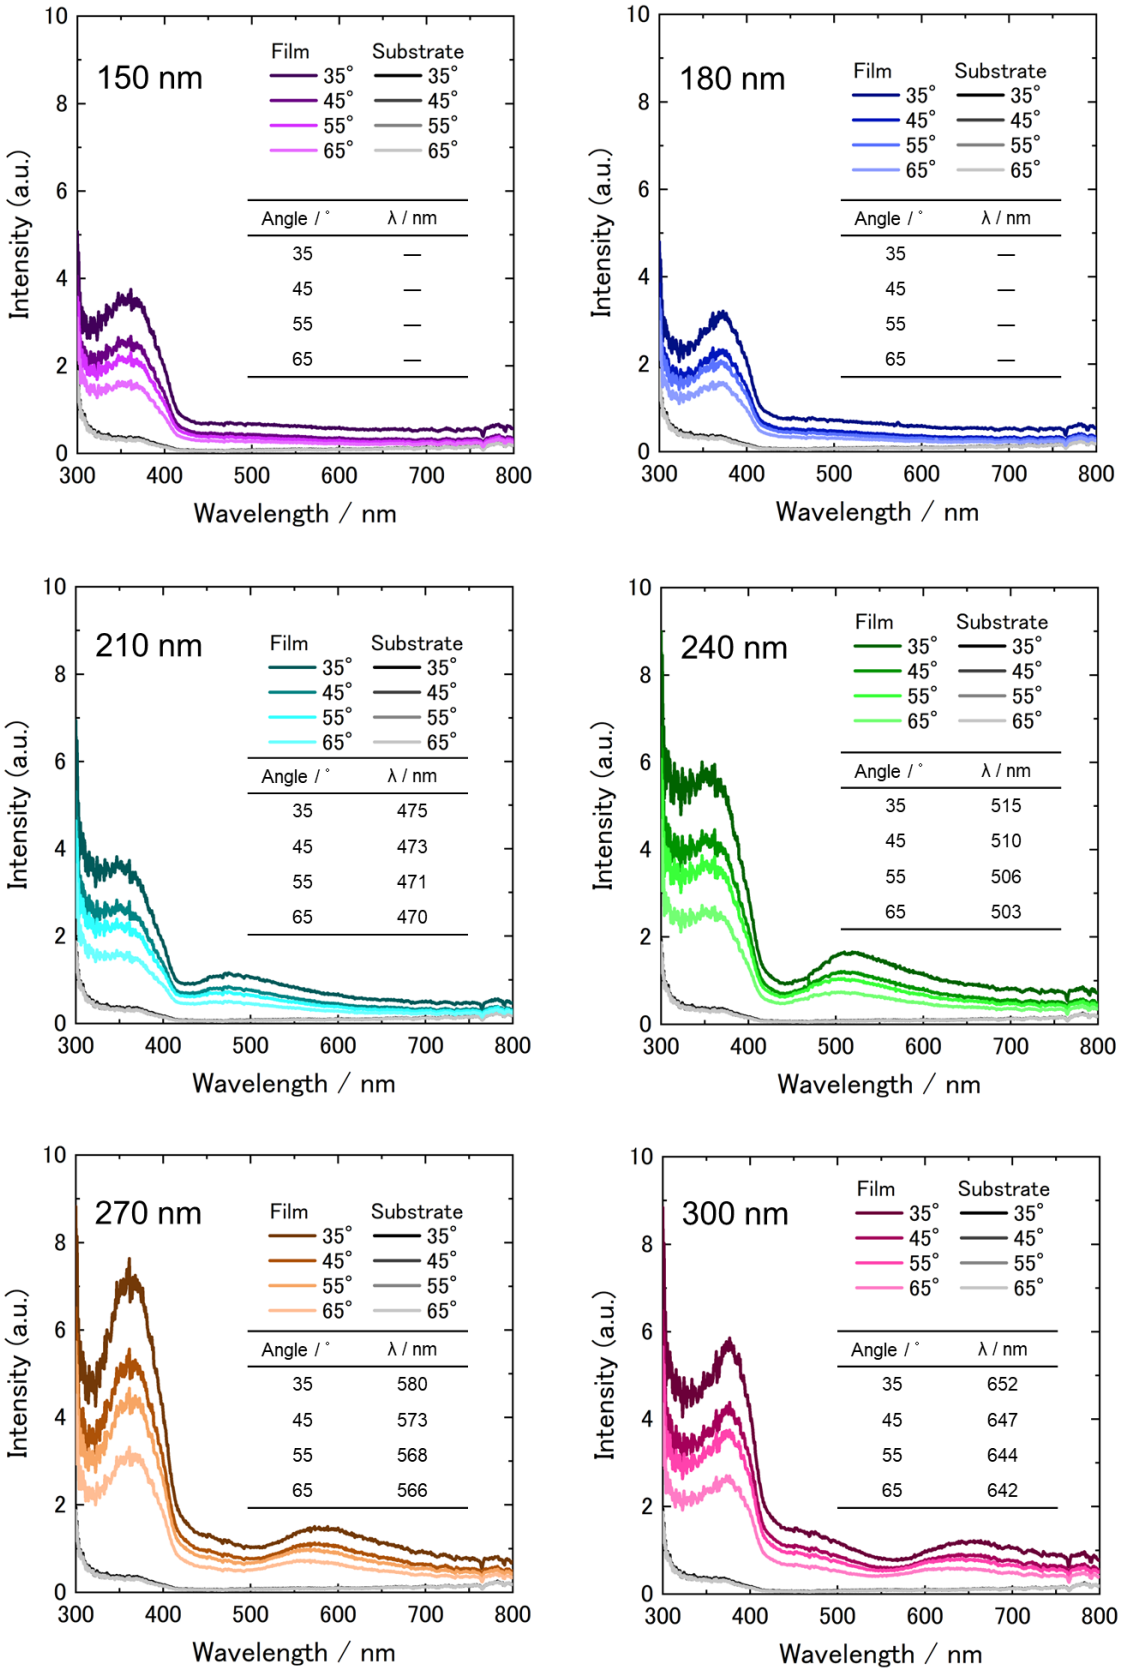

Figure S5. Angular dependence of reflection spectra of particle-stacked films comprising SiO_2–ZrN core–shell particles with core particles of 150, 180, 210, 240, 270, and 300 nm.

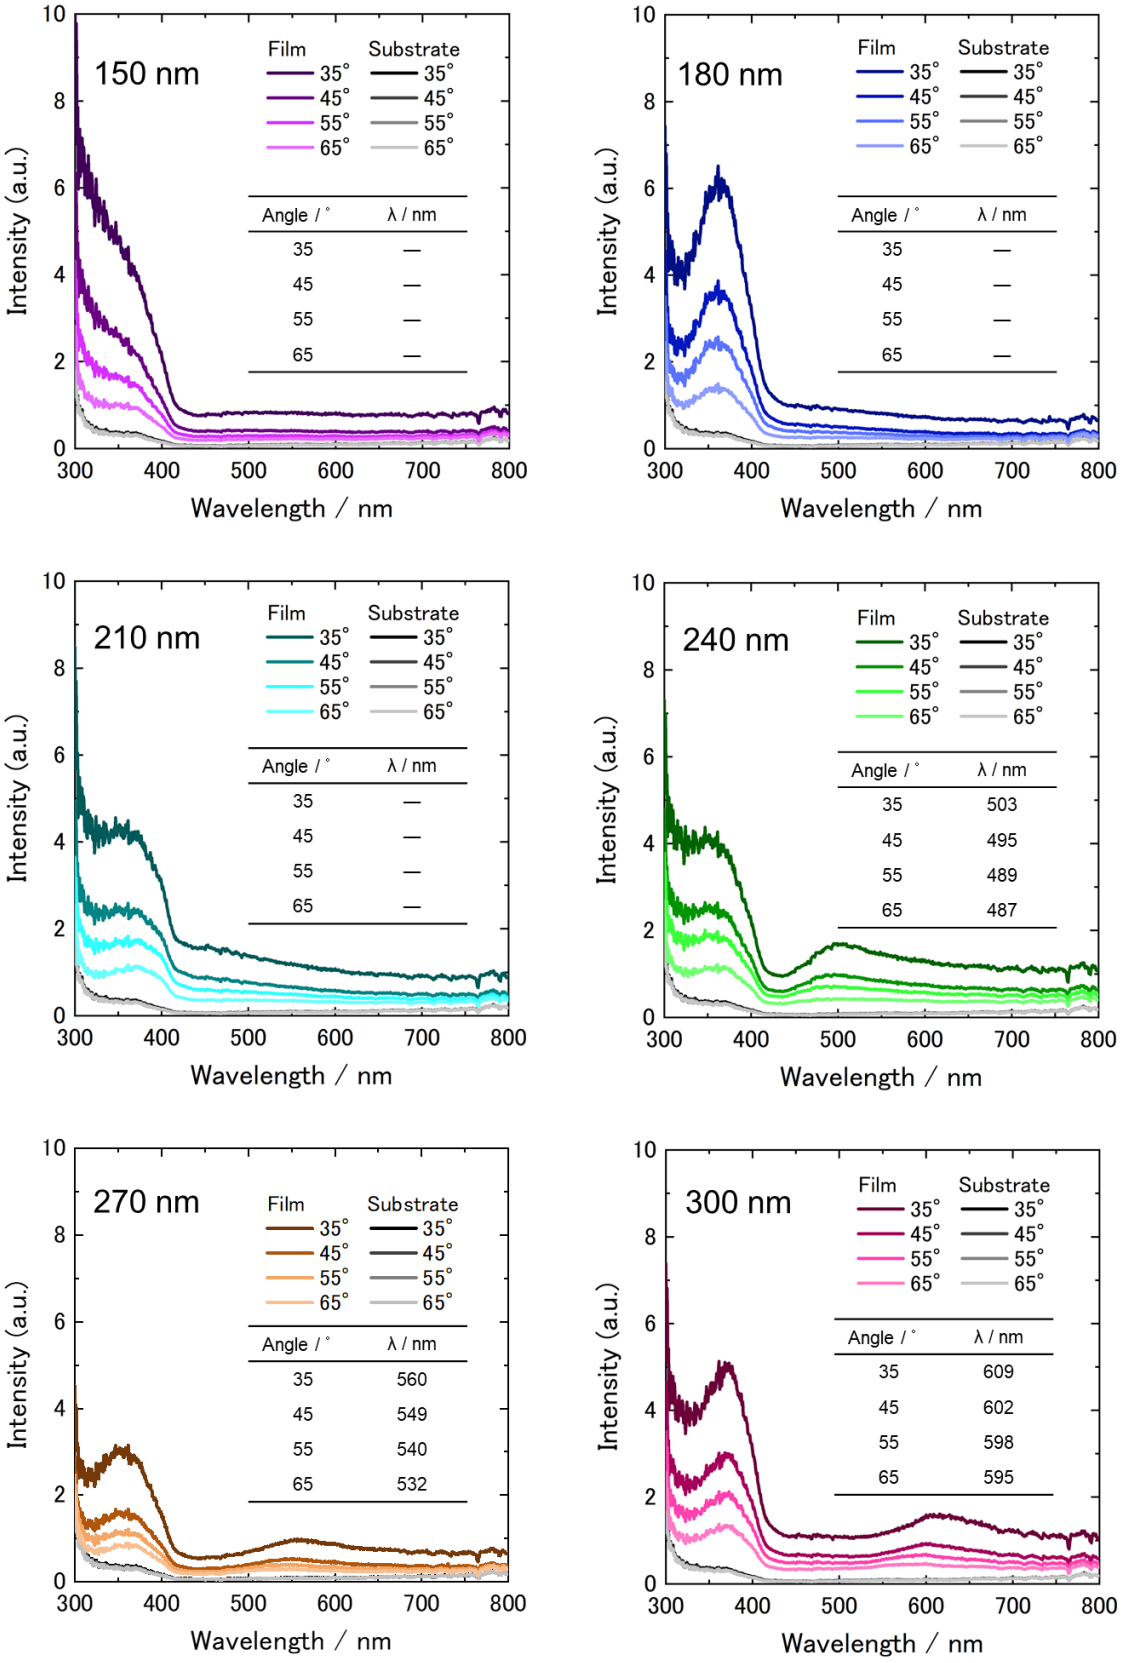

Figure S6. Angular dependence of reflection spectra of particle-stacked films comprising SiO_2 particles with particle size o 150, 180, 210, 240, 270, and 300 nm.

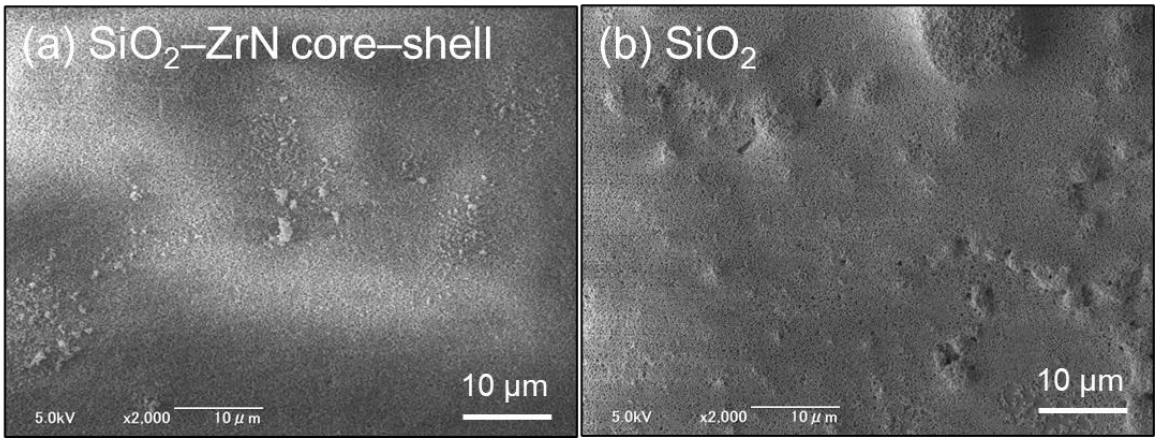

Figure S7. The low magnification FE-SEM images of particle-stacked film surface. (a) The particle-stacked films are composed of SiO_2–ZrN core–shell particles with core particles of 270 nm, and (b) 270 nm SiO_2 particles.

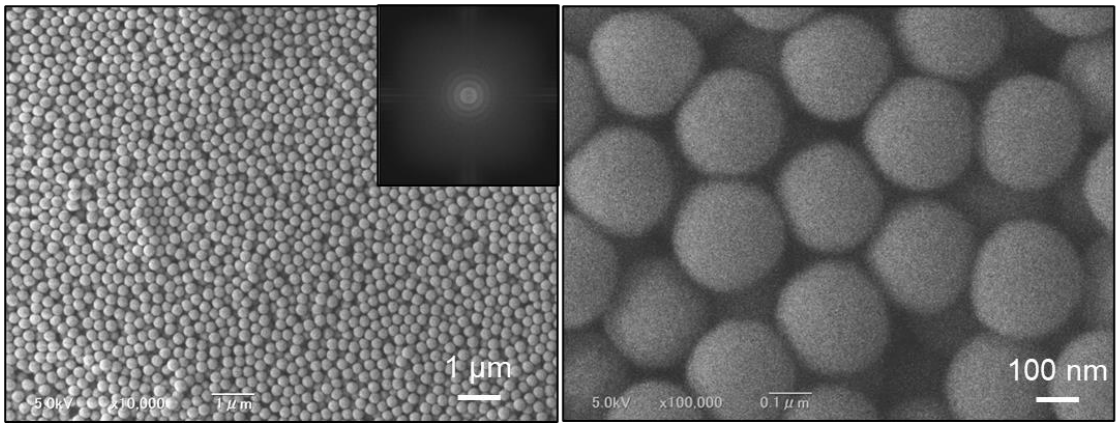

Figure S8. The surface FE-SEM images of particle-stacked films composed of 270 nm SiO_2 particles and Fourier transform image.

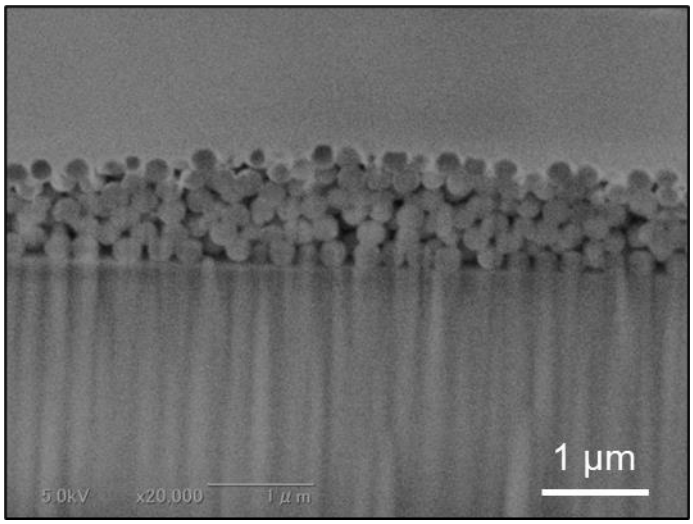

Figure S9. Cross-sectional FE-SEM images of particle-stacked films composed of 270 nm SiO_2 particles.

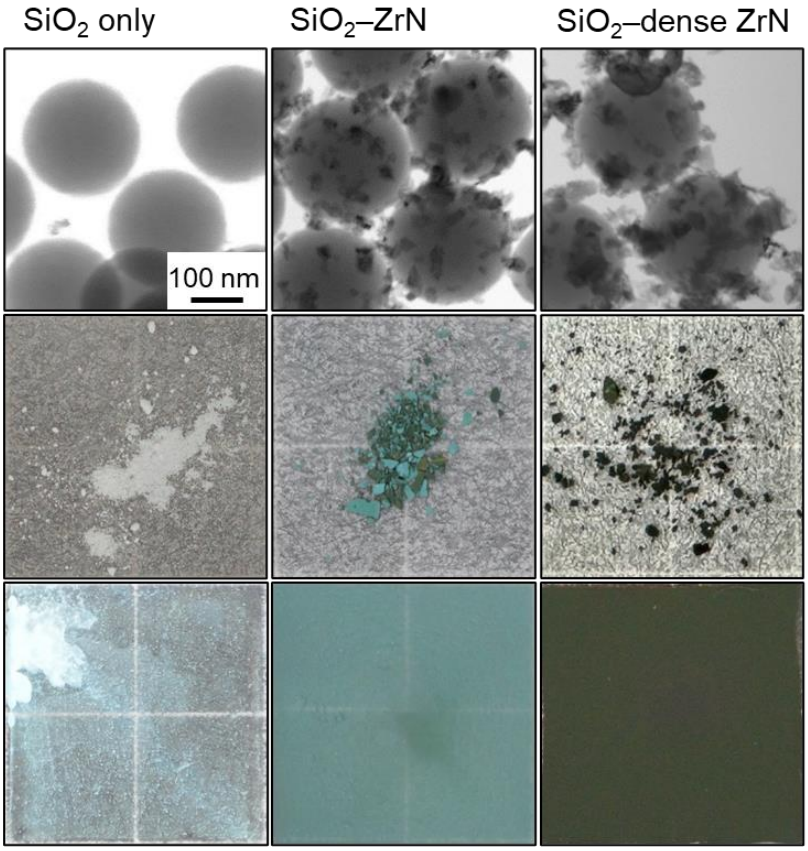

Figure S10. BF-STEM images, photographs of the obtained powder, and photographs of the particle-stacked films are presented for the following samples: 240 nm SiO_2 particles, SiO_2–ZrN core–shell particles containing 240 nm SiO_2 particles as the core, and SiO_2–ZrN core–shell particles with a dense ZrN as shell and 240 nm SiO_2 particles as the core.

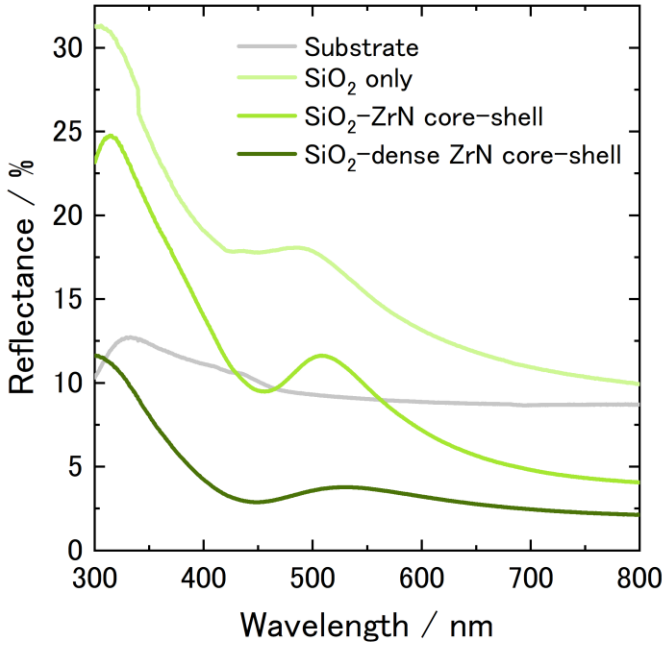

Figure S11. Reflection spectra of the particle-stacked films composed of 240 nm SiO_2 particles, SiO_2–ZrN core–shell particles with core particles of 240 nm, and SiO_2–ZrN core–shell particles with a dense ZrN as shell and 240 nm SiO_2 particles as the core. The light was incident at 5° from the vertical plane of the particle laminated film, with the reflected light detected with an integrating sphere unit.

Table S1. Wavelength of maximum peaks of the short wavelength side (λ_s), wavelength of maximum peaks of the long wavelength side (λ_l), reflectance of the short wavelength side (R_s), reflectance of the short wavelength side (R_l),and reflection intensity ratio ($R_l\,R_s^{-1}$) of the long wavelength side (R_l) to the reflection intensity on the short wavelength (R_s) side in the reflection spectrum of the particle-stacked films using 240 nm SiO_2 particles, SiO_2–ZrN core–shell particles with core particles of 240 nm, and SiO_2–ZrN core–shell particles with a dense ZrN as shell and 240 nm SiO_2 particles as the core.

Type	λ_s / nm	λ_l / nm	R_s / %	R_l / %	$R_l\,R_s^{-1}$ / –
SiO_2 only	306	485	31.31	18.07	0.58
SiO_2–ZrN core–shell	314	509	24.77	11.63	0.47
SiO_2– dense ZrN	301	530	12.92	4.20	0.33

AUTHOR INFORMATION

Corresponding Author

Kiyoharu Tadanaga

[3]Faculty of Engineering, Hokkaido University, Kita-13, Nishi-8, Kita-ku, Sapporo 060-8628, Japan; ORCID: https://orcid.org/0000-0002-3319-4353; Email: tadanaga@eng.hokudai.ac.jp

Author

Shinji Noguchi

[1]Graduate School of Chemical Sciences and Engineering, Hokkaido University, Kita-13, Nishi-8, Kita-ku, Sapporo 060-8628, Japan; ORCID: https://orcid.org/0000-0003-1546-9998; Email: shinji@eis.hokudai.ac.jp

Milena Lama

[2]Institute for Chemical Reaction Design and Discovery (WPI-ICReDD), Hokkaido University, Kita-21, Nishi-11, Kita-ku, Sapporo 001-0021, Japan; ORCID: https://orcid.org/0000-0001-8373-6336; Email: lama@icredd.hokudai.ac.jp

Yuta Fujii

[3]Faculty of Engineering, Hokkaido University, Kita-13, Nishi-8, Kita-ku, Sapporo 060-8628, Japan; ORCID: https://orcid.org/0000-0002-8381-4119; Email: fujii.yuta@eng.hokudai.ac.jp

Akira Miura

[3]Faculty of Engineering, Hokkaido University, Kita-13, Nishi-8, Kita-ku, Sapporo 060-8628, Japan; ORCID: https://orcid.org/0000-0003-0388-9696; Email: amiura@eng.hokudai.ac.jp

Author Contributions

- Shinji Noguchi led the study, including conceiving the study idea, developing the experimental plan, conducting the experiments, drafting the original manuscript, and securing some research funding.
- Milena Lama assisted in developing the experimental plan and conducted some of the experiments.
- Yuta Fujii discussed the results.
- Akira Miura discussed the results.
- Kiyoharu Tadanaga played a multifaceted role, including conceiving the study idea, developing the experimental plan, securing a portion of the research funding, and overseeing the entire study's execution.

All authors reviewed the manuscript draft and revised it critically on intellectual content. All authors approved the final version of the manuscript to be published.

Funding Source

- Hokkaido University “Ambitious Leader’s Program” supported by the Ministry of Education, Culture, Sports, Science and Technology (MEXT), Japan
- JST SPRING (Grant Number JPMJSP2119) from the Japan Science and Technology and Agency (JST)
- Grant-in-Aid for JSPS Fellows (No. 23KJ0014) from the Japan Society for the Promotion of Science (JSPS)
- Advanced Research Infrastructure for Materials and Nanotechnology in Japan (ARIM)” of the MEXT. Grant Number JPMXP1223HK0087 (Hokkaido University)

Notes

The authors declare no competing financial interests.